



# **Cytec Cycom 5250-5 T650 6K-135-5HS fabric 36% RC Qualification Statistical Analysis Report**

**FAA Special Project Number SP4613WI-Q**

**Report Release Date: July 20, 2012**

**NCAMP Test Report Number: NCP-RP-2010-065 N/C**

## **Elizabeth Clarkson, Ph.D.**

National Center for Advanced Materials Performance (NCAMP)  
National Institute for Aviation Research  
Wichita State University  
Wichita, KS 67260-0093

## **Testing Facility:**

National Institute for Aviation Research  
Wichita State University  
1845 N. Fairmount  
Wichita, KS 67260-0093

## **Test Panel Fabrication Facility:**

Northrop Grumman Corporation  
700 N. Douglas St., Building 902  
El Segundo, CA 90245

**Prepared by:** \_\_\_\_\_  
**Elizabeth Clarkson, Ph.D**

**Reviewed by:** \_\_\_\_\_  
**Evelyn Lian**

**Approved by:** \_\_\_\_\_  
**Yeow Ng**

REVISIONS:

Rev	By	Date	Pages Revised or Added
N/C	Elizabeth Clarkson	07/20/2012	Document Initial Release

**DISCONTINUED**

**Table of Contents**

**1. Introduction..... 9**

**1.1 Symbols and Abbreviations ..... 10**

**1.2 Pooling Across Environments..... 12**

**1.3 Basis Value Computational Process..... 12**

**1.4 Modified Coefficient of Variation (CV) Method..... 12**

**2. Background ..... 14**

**2.1 ASAP Statistical Formulas and Computations ..... 14**

    2.1.1 Basic Descriptive Statistics..... 14

    2.1.2 Statistics for Pooled Data..... 14

    2.1.3 Basis Value Computations..... 15

    2.1.4 Modified Coefficient of Variation ..... 16

    2.1.5 Determination of Outliers ..... 17

    2.1.6 The k-Sample Anderson Darling Test for Batch Equivalency ..... 18

    2.1.7 The Anderson Darling Test for Normality..... 19

    2.1.8 Levene’s Test for Equality of Coefficient of Variation ..... 20

**2.2 STAT-17..... 20**

    2.2.1 Distribution Tests..... 20

    2.2.2 Computing Normal Distribution Basis Values ..... 21

    2.2.3 Non-parametric Basis Values..... 25

    2.2.4 Analysis of Variance (ANOVA) Basis Values..... 28

**2.3 Single Batch and Two Batch Estimates using Modified CV ..... 30**

**2.4 Lamina Variability Method (LVM) ..... 30**

**3. Summary of Results..... 32**

**3.1 NCAMP Recommended B-basis Values ..... 32**

**3.2 Lamina and Laminate Summary Tables ..... 35**

**4. Individual Test Summaries, Statistics, Basis Values and Graphs..... 37**

**4.1 Warp (0°) Tension Properties (WT)..... 38**

**4.2 Fill (90°) Tension Properties (FT)..... 40**

**4.3 Warp (0°) Compression Properties (WC)..... 42**

4.4	Fill (90°) Compression Properties (FC).....	44
4.5	Short Beam Strength (SBS) Data .....	46
4.6	In-Plane Shear Properties (IPS) .....	48
4.7	Quasi Isotropic Unnotched Tension Properties (UNT1).....	51
4.8	“Soft” Unnotched Tension Properties (UNT2).....	53
4.9	“Hard” Unnotched Tension Properties (UNT3) .....	55
4.10	Quasi Isotropic Unnotched Compression (UNC1).....	57
4.11	“Soft” Unnotched Compression (UNC2) .....	59
4.12	“Hard” Unnotched Compression (UNC3).....	61
4.13	Laminate Short Beam Strength (SBS1) Data.....	63
4.14	Quasi Isotropic Open Hole Tension Properties (OHT1).....	65
4.15	“Soft” Open Hole Tension Properties (OHT2).....	67
4.16	“Hard” Open Hole Tension Properties (OHT3) .....	69
4.17	Quasi Isotropic Filled Hole Tension (FHT1).....	71
4.18	“Soft” Filled Hole Tension (FHT2).....	73
4.19	“Hard” Filled Hole Tension (FHT3).....	75
4.20	Quasi Isotropic Open Hole Compression (OHC1).....	77
4.21	“Soft” Open Hole Compression (OHC2).....	79
4.22	“Hard” Open Hole Compression (OHC3).....	81
4.23	Quasi Isotropic Filled Hole Compression (FHC1).....	83
4.24	“Soft” Filled Hole Compression (FHC2) .....	85
4.25	“Hard” Filled Hole Compression (FHC3) .....	87
4.26	Quasi Isotropic Single Shear Bearing (SSB1) .....	89
4.27	“Soft” Single Shear Bearing (SSB2).....	91
4.28	“Hard” Single Shear Bearing (SSB3).....	93

4.29 Compression After Impact (CAI)..... 95

4.30 Interlaminar Tension Strength (ILT) and Curved Beam Strength (CBS)..... 96

5. Outliers..... 97

6. References..... 98

**DISCONTINUED**

List of Figures

Figure 4-1 Batch plot for WT normalized strength..... 38  
Figure 4-2: Batch Plot for FT normalized strength..... 40  
Figure 4-3 Batch plot for WC normalized strength..... 42  
Figure 4-4: Batch Plot for FC normalized strength..... 44  
Figure 4-5: Batch plot for SBS strength as-measured..... 46  
Figure 4-6: Batch plot for IPS strength as-measured..... 49  
Figure 4-7: Batch Plot for UNT1 normalized strength..... 51  
Figure 4-8: Batch Plot for UNT2 normalized strength..... 53  
Figure 4-9: Batch Plot for UNT3 normalized strength..... 55  
Figure 4-10: Batch plot for UNC1 normalized strength..... 57  
Figure 4-11: Batch plot for UNC2 normalized strength..... 59  
Figure 4-12: Batch plot for UNC3 normalized strength..... 61  
Figure 4-13: Batch plot for SBS1 strength as-measured..... 63  
Figure 4-14: Batch Plot for OHT1 normalized strength..... 65  
Figure 4-15: Batch Plot for OHT2 normalized strength..... 67  
Figure 4-16: Batch Plot for OHT3 normalized strength..... 69  
Figure 4-17: Batch plot for FHT1 normalized strength..... 71  
Figure 4-18: Batch plot for FHT2 normalized strength..... 73  
Figure 4-19: Batch plot for FHT3 normalized strength..... 75  
Figure 4-20: Batch plot for OHC1 normalized strength..... 77  
Figure 4-21: Batch plot for OHC2 normalized strength..... 79  
Figure 4-22: Batch plot for OHC3 normalized strength..... 81  
Figure 4-23: Batch plot for FHC1 normalized strength..... 83  
Figure 4-24: Batch plot for FHC2 normalized strength..... 85  
Figure 4-25: Batch plot for FHC3 normalized strength..... 87  
Figure 4-26: Batch plot for SSB1 normalized strength..... 89  
Figure 4-27: Batch plot for SSB2 normalized strength..... 91  
Figure 4-28: Batch plot for SSB3 normalized strength..... 93  
Figure 4-29: Plot for Compression After Impact normalized strength..... 95  
Figure 4-30: Plot for Interlaminar Tension and Curved Beam Strength..... 96

DISCONTINUED

## List of Tables

<b>Table 1-1: Test Property Abbreviations .....</b>	<b>10</b>
<b>Table 1-2: Test Property Symbols .....</b>	<b>11</b>
<b>Table 1-3: Environmental Conditions Abbreviations .....</b>	<b>11</b>
<b>Table 2-1: K factors for normal distribution .....</b>	<b>21</b>
<b>Table 2-2: Weibull Distribution Basis Value Factors .....</b>	<b>24</b>
<b>Table 2-3: B-Basis Hanson-Koopmans Table .....</b>	<b>27</b>
<b>Table 2-4: A-Basis Hanson-Koopmans Table .....</b>	<b>28</b>
<b>Table 2-5: B-Basis factors for small datasets using variability of corresponding large dataset .....</b>	<b>31</b>
<b>Table 3-1 : NCAMP Recommended B-basis values for Lamina Test Data .....</b>	<b>33</b>
<b>Table 3-2 : NCAMP Recommended B-basis values for Laminate Test Data .....</b>	<b>35</b>
<b>Table 3-3: Summary of Test Results for Lamina Data .....</b>	<b>35</b>
<b>Table 3-4: Summary of Test Results for Laminate Data .....</b>	<b>36</b>
<b>Table 4-1: Statistics and Basis values for WT Strength Data .....</b>	<b>39</b>
<b>Table 4-2: Statistics from WT Modulus Data .....</b>	<b>39</b>
<b>Table 4-3: Statistics and Basis Values for FT Strength Data .....</b>	<b>41</b>
<b>Table 4-4: Statistics from FT Modulus Data .....</b>	<b>41</b>
<b>Table 4-5: Statistics and Basis Values for WC Strength Data .....</b>	<b>43</b>
<b>Table 4-6: Statistics from WC Modulus Data .....</b>	<b>43</b>
<b>Table 4-7: Statistics and Basis Values for FC Strength Data .....</b>	<b>45</b>
<b>Table 4-8: Statistics from FC Modulus Data .....</b>	<b>45</b>
<b>Table 4-9: Statistics and Basis Values for SBS Strength Data .....</b>	<b>47</b>
<b>Table 4-10: Statistics and Basis Values for IPS Strength Data .....</b>	<b>49</b>
<b>Table 4-11: Statistics and Basis Values for IPS Modulus Data .....</b>	<b>50</b>
<b>Table 4-12: Statistics and Basis Values for UNT1 Strength Data .....</b>	<b>52</b>
<b>Table 4-13: Statistics from UNT1 Modulus Data .....</b>	<b>52</b>
<b>Table 4-14: Statistics and Basis Values for UNT2 Strength Data .....</b>	<b>54</b>
<b>Table 4-15: Statistics from UNT2 Modulus Data .....</b>	<b>54</b>
<b>Table 4-16: Statistics and Basis Values for UNT3 Strength Data .....</b>	<b>56</b>
<b>Table 4-17: Statistics from UNT3 Modulus Data .....</b>	<b>56</b>
<b>Table 4-18: Statistics and Basis Values for UNC1 Strength Data .....</b>	<b>58</b>
<b>Table 4-19: Statistics from UNC1 Modulus Data .....</b>	<b>58</b>
<b>Table 4-20: Statistics and Basis Values for UNC2 Strength Data .....</b>	<b>60</b>
<b>Table 4-21: Statistics from UNC2 Modulus Data .....</b>	<b>60</b>
<b>Table 4-22: Statistics and Basis Values for UNC3 Strength Data .....</b>	<b>62</b>
<b>Table 4-23: Statistics from UNC3 Modulus Data .....</b>	<b>62</b>
<b>Table 4-24: Statistics and Basis Values for SBS1 Strength Data .....</b>	<b>64</b>
<b>Table 4-25: Statistics and Basis Values for OHT1 Strength Data .....</b>	<b>66</b>
<b>Table 4-26: Statistics and Basis Values for OHT2 Strength Data .....</b>	<b>68</b>
<b>Table 4-27: Statistics and Basis Values for OHT3 Strength Data .....</b>	<b>70</b>
<b>Table 4-28: Statistics and Basis Values for FHT1 Strength Data .....</b>	<b>72</b>
<b>Table 4-29: Statistics and Basis Values for FHT2 Strength Data .....</b>	<b>74</b>
<b>Table 4-30: Statistics and Basis Values for FHT3 Strength Data .....</b>	<b>76</b>
<b>Table 4-31: Statistics and Basis Values for OHC1 Strength Data .....</b>	<b>78</b>
<b>Table 4-32: Statistics and Basis Values for OHC2 Strength Data .....</b>	<b>80</b>

**Table 4-33: Statistics and Basis Values for OHC3 Strength Data..... 82**  
**Table 4-34: Statistics and Basis Values for FHC1 Strength Data ..... 84**  
**Table 4-35: Statistics and Basis Values for FHC2 Strength Data ..... 86**  
**Table 4-36: Statistics and Basis Values for FHC3 Strength Data ..... 88**  
**Table 4-37: Statistics and Basis Values for SSB1 Strength Data..... 90**  
**Table 4-38: Statistics and Basis Values for SSB2 Strength Data..... 92**  
**Table 4-39: Statistics and Basis Values for SSB3 Strength Data..... 94**  
**Table 4-40: Statistics for Compression After Impact Strength Data..... 95**  
**Table 4-41: Statistics for ILT and CBS Strength Data ..... 96**  
**Table 5-1: List of outliers ..... 97**

**DISCONTINUED**



## 1. Introduction

This report contains statistical analysis of the Cytec 5250-5 T650 6K-135-5HS fabric 36% RC material property data published in NCAMP Test Report CAM-RP-2010-076 Rev B. The lamina and laminate material property data have been generated with FAA oversight through FAA Special Project Number SP4613WI-Q and also meet the requirements outlined in NCAMP Standard Operating Procedure NSP 100. The test panels, test specimens, and test setups have been conformed by the FAA and the testing has been witnessed by the FAA.

B-Basis values, A-estimates, and B-estimates were calculated using a variety of techniques that are detailed in section two. The qualification material was procured to NCAMP Material Specification NMS 226/2 Rev Initial Release dated June 17, 2007. The qualification test panels were cured in accordance with NCAMP Process Specification NPS 81226 Revision C dated July 23, 2008 with baseline "C" cure cycle. The panels were fabricated at Northrop Grumman, 700 N. Douglas St., Building 902, El Segundo, CA 90245. The NCAMP Test Plan NTP 2262Q1 was used for this qualification program. The testing was performed at the National Institute for Aviation Research (NIAR) in Wichita, Kansas.

Basis numbers are labeled as 'values' when the data meets all the requirements of CMH-17 Rev G. When those requirements are not met, they will be labeled as 'estimates.' When the data does not meet all requirements, the failure to meet these requirements is reported and the specific requirement(s) the data fails to meet is identified. The method used to compute the basis value is noted for each basis value provided. When appropriate, in addition to the traditional computational methods, values computed using the modified coefficient of variation method is also provided.

The material property data acquisition process is designed to generate basic material property data with sufficient pedigree for submission to Complete Documentation sections of the Composite Materials Handbook (CMH-17 Rev G).

The NCAMP shared material property database contains material property data of common usefulness to a wide range of aerospace projects. However, the data may not fulfill all the needs of a project. Specific properties, environments, laminate architecture, and loading situations that individual projects need may require additional testing.

The use of NCAMP material and process specifications do not guarantee material or structural performance. Material users should be actively involved in evaluating material performance and quality including, but not limited to, performing regular purchaser quality control tests, performing periodic equivalency/additional testing, participating in material change management activities, conducting statistical process control, and conducting regular supplier audits.

The applicability and accuracy of NCAMP material property data, material allowables, and specifications must be evaluated on case-by-case basis by aircraft companies and certifying agencies. NCAMP assumes no liability whatsoever, expressed or implied, related to the use of the material property data, material allowables, and specifications.

Part fabricators that wish to utilize the material property data, allowables, and specifications may be able to do so by demonstrating the capability to reproduce the original material properties; a process known as equivalency. More information about this equivalency process including the test statistics and its limitations can be found in Section 6 of DOT/FAA/AR-03/19 and Section 8.4.1 of CMH-17 Rev G. The applicability of equivalency process must be evaluated on program-by-program basis by the applicant and certifying agency. The applicant and certifying agency must agree that the equivalency test plan along with the equivalency process described in Section 6 of DOT/FAA/AR-03/19 and Section 8.4.1 of CMH-17 Rev G are adequate for the given program.

Aircraft companies should not use the data published in this report without specifying NCAMP Material Specification NMS 226/2. NMS 226/2 has additional requirements that are listed in its prepreg process control document (PCD), fiber specification, fiber PCD, and other raw material specifications and PCDs which impose essential quality controls on the raw materials and raw material manufacturing equipment and processes. *Aircraft companies and certifying agencies should assume that the material property data published in this report is not applicable when the material is not procured to NCAMP Material Specification NMS 226/2.* NMS 226/2 is a free, publicly available, non-proprietary aerospace industry material specification.

This report is intended for general distribution to the public, either freely or at a price that does not exceed the cost of reproduction (e.g. printing) and distribution (e.g. postage).

### 1.1 Symbols and Abbreviations

Test Property	Abbreviation
Warp Compression	WC
Warp Tension	WT
Fill Compression	FC
Fill Tension	FT
In-Plane Shear	IPS
Short Beam Strength	SBS
Unnotched Tension	UNT
Unnotched Compression	UNC
Laminate Short Beam Strength	SBS1
Filled Hole Tension	FHT
Filled Hole Compression	FHC
Open Hole Tension	OHT
Open Hole Compression	OHC
Single Shear Bearing	SSB
Interlaminar Tension	ILT
Curved Beam Strength	CBS
Compression After Impact	CAI

**Table 1-1: Test Property Abbreviations**

Test Property	Symbol
Warp Compression Strength	$F_1^{cu}$
Warp Compression Modulus	$E_1^c$
Warp Compression Poisson's Ratio	$\nu_{12}^c$
Warp Tension Strength	$F_1^{tu}$
Warp Tension Modulus	$E_1^t$
Warp Tension Poisson's Ratio	$\nu_{12}^t$
Fill Compression Strength	$F_2^{cu}$
Fill Compression Modulus	$E_2^c$
Fill Compression Poisson's Ratio	$\nu_{21}^c$
Fill Tension Strength	$F_2^{tu}$
Fill Tension Modulus	$E_2^t$
In-Plane Shear Peak Strength before 5% strain	$F_{12}^{shmax}$
In-Plane Shear Strength at 5% strain	$F_{12}^{s5\%}$
In-Plane Shear Strength at 0.2% offset	$F_{12}^{s0.2\%}$
In-Plane Shear Modulus	$G_{12}^s$

Table 1-2: Test Property Symbols

Environmental Condition	Temperature	Abbreviation
Cold Temperature Dry	-65° F	CTD
Room Temperature Dry	70° F	RTD
Elevated Temperature Dry	350° F	ETD
Elevated Temperature Wet	350° F	ETW

Table 1-3: Environmental Conditions Abbreviations

Tests with a number immediately after the abbreviation indicate the lay-up:

- 1 = "Quasi-Isotropic"
- 2 = "Soft"
- 3 = "Hard"

EX: OHT1 is an open hole tension test with a "Quasi-Isotropic" layup

Detailed information about the test methods and conditions used is given in NCAMP Test Report CAM-RP-2010-076 Rev B.

## 1.2 Pooling Across Environments

When pooling across environments was allowable, the pooled co-efficient of variation was used. ASAP (AGATE Statistical Analysis Program) 2008 version 1.0 was used to determine if pooling was allowable and to compute the pooled coefficient of variation for those tests. In these cases, the modified coefficient of variation based on the pooled data was used to compute the basis values.

When pooling across environments was not advisable because the data was not eligible for pooling and engineering judgment indicated there was no justification for overriding the result, then B-Basis values were computed for each environmental condition separately using Stat-17 version 5.

## 1.3 Basis Value Computational Process

The general form to compute engineering basis values is:  $\text{basis value} = \bar{X} - kS$  where  $k$  is a factor based on the sample size and the distribution of the sample data. There are many different methods to determine the value of  $k$  in this equation, depending on the sample size and the distribution of the data. In addition, the computational formula used for the standard deviation,  $S$ , may vary depending on the distribution of the data. The details of those different computations and when each should be used are in section 2.0.

## 1.4 Modified Coefficient of Variation (CV) Method

A common problem with new material qualifications is that the initial specimens produced and tested do not contain all of the variability that will be encountered when the material is being produced in larger amounts over a lengthy period of time. This can result in setting basis values that are unrealistically high. The variability as-measured in the qualification program is often lower than the actual material variability because of several reasons. The materials used in the qualification programs are usually manufactured within a short period of time, typically 2-3 weeks only, which is not representative of the production material. Some raw ingredients that are used to manufacture the multi-batch qualification materials may actually be from the same production batches or manufactured within a short period of time so the qualification materials, although regarded as multiple batches, may not truly be multiple batches so they are not representative of the actual production material variability.

The modified Coefficient of Variation (CV) used in this report is in accordance with section 8.4.4 of working draft CMH-17 Rev G. It is a method of adjusting the original basis values downward in anticipation of the expected additional variation. Composite materials are expected to have a CV of at least 6%. The modified coefficient of variation (CV) method increases the measured coefficient of variation when it is below 8% prior to computing basis values. A higher CV will result in lower or more conservative basis values and lower specification limits. The use of the modified CV method is intended for a temporary period of time when there is minimal data available. When a sufficient number of production batches (approximately 8 to 15) have been produced and tested, the as-measured CV may be used so that the basis values and specification limits may be adjusted higher.

The material allowables in this report are calculated using both the as-measured CV and modified CV, so users have the choice of using either one. When the measured CV is greater than 8%, the modified CV method does not change the basis value. NCAMP recommended values make use of the modified CV method when it is appropriate for the data.

When the data fails the Anderson-Darling K-sample test for batch to batch variability or when the data fails the normality test, the modified CV method is not appropriate and no modified CV basis value will be provided. When the ANOVA method is used, it may produce excessively conservative basis values. When appropriate, a single batch or two batch estimate may be provided in addition to the ANOVA estimate.

In some cases a transformation of the data to fit the assumption of the modified CV resulted in the transformed data passing the ADK test and thus the data can be pooled only for the modified CV method.

NCAMP recommends that if a user decides to use the basis values that are calculated from as-measured CV, the specification limits and control limits be calculated with as-measured CV also. Similarly, if a user decides to use the basis values that are calculated from modified CV, the specification limits and control limits be calculated with modified CV also. This will ensure that the link between material allowables, specification limits, and control limits is maintained.

DISCONTINUED

## 2. Background

Statistical computations are performed with AGATE Statistical Analysis Program (ASAP) when pooling across environments is permissible according to CMH-17 Rev G guidelines. If pooling is not permissible, a single point analysis using STAT-17 is performed for each environmental condition with sufficient test results. If the data does not meet working draft CMH-17 Rev G requirements for a single point analysis, estimates are created by a variety of methods depending on which is most appropriate for the dataset available. Specific procedures used are presented in the individual sections where the data is presented.

### 2.1 ASAP Statistical Formulas and Computations

This section contains the details of the specific formulas ASAP uses in its computations.

#### 2.1.1 Basic Descriptive Statistics

The basic descriptive statistics shown are computed according to the usual formulas, which are shown below:

**Mean:** 
$$\bar{X} = \sum_{i=1}^n \frac{X_i}{n}$$
 **Equation 1**

**Std. Dev.:** 
$$S = \sqrt{\frac{1}{n} \sum_{i=1}^n (X_i - \bar{X})^2}$$
 **Equation 2**

**% Co. Variation:** 
$$\frac{S}{\bar{X}} \times 100$$
 **Equation 3**

Where  $n$  refers to the number of specimens in the sample and  $X_i$  refers to the individual specimen measurements.

#### 2.1.2 Statistics for Pooled Data

Prior to computing statistics for the pooled dataset, the data is normalized to a mean of one by dividing each value by the mean of all the data for that condition. This transformation does not affect the coefficients of variation for the individual conditions.

##### 2.1.2.1 Pooled Standard Deviation

The formula to compute a pooled standard deviation is given below:

**Pooled Std. Dev.  $S_p$**  = 
$$\sqrt{\frac{\sum_{i=1}^k (n_i - 1) S_i^2}{\sum_{i=1}^k (n_i - 1)}}$$
 **Equation 4**

Where  $k$  refers to the number of batches and  $n_i$  refers to the number of specimens in the  $i^{\text{th}}$  sample.

**2.1.2.2 Pooled Coefficient of Variation**

Since the mean for the normalized data is 1.0 for each condition, the pooled normalized data also has a mean of one. The coefficient of variation for the pooled normalized data is the pooled standard deviation divided by the pooled mean, as in equation 3. Since the mean for the pooled normalized data is one, the pooled coefficient of variation is equal to the pooled standard deviation of the normalized data.

$$\text{Pooled Coefficient of Variation} = \frac{S_p}{1} = S_p \tag{Equation 5}$$

**2.1.3 Basis Value Computations**

Basis values are computed using the mean and standard deviation for that environment, as follows: The mean is always the mean for the environment, but if the data meets all requirements for pooling,  $S_p$  can be used in place of the standard deviation for the environment,  $S$ .

$$\begin{aligned} \text{Basis Values: } & A\text{-basis} = \bar{X} - K_a S \\ & B\text{-basis} = \bar{X} - K_b S \end{aligned} \tag{Equation 6}$$

**2.1.3.1 K-factor computations**

$K_a$  and  $K_b$  are computed according to the methodology documented in section 8.3.5 of CMH-17 Rev G. The approximation formulas are given below:

$$K_a = \frac{2.7263}{\sqrt{q(f)}} + \sqrt{\frac{1}{c_A(f) \cdot n_j} + \left(\frac{b_A(f)}{2c_A(f)}\right)^2} - \frac{b_A(f)}{2c_A(f)} \tag{Equation 7}$$

$$K_b = \frac{1.2816}{\sqrt{q(f)}} + \sqrt{\frac{1}{c_B(f) \cdot n_j} + \left(\frac{b_B(f)}{2c_B(f)}\right)^2} - \frac{b_B(f)}{2c_B(f)} \tag{Equation 8}$$

Where

- $r$  = the number of environments being pooled together
- $n_j$  = number of data values for environment  $j$

$$N = \sum_{j=1}^r n_j$$

$$f = N - r$$

$$q(f) = 1 - \frac{2.323}{\sqrt{f}} + \frac{1.064}{f} + \frac{0.9157}{f\sqrt{f}} - \frac{0.6530}{f^2}$$

Equation 9

$$b_B(f) = \frac{1.1372}{\sqrt{f}} - \frac{0.49162}{f} + \frac{0.18612}{f\sqrt{f}}$$

Equation 10

$$c_B(f) = 0.36961 + \frac{0.0040342}{\sqrt{f}} - \frac{0.71750}{f} + \frac{0.19693}{f\sqrt{f}}$$

Equation 11

$$b_A(f) = \frac{2.0643}{\sqrt{f}} - \frac{0.95145}{f} + \frac{0.51251}{f\sqrt{f}}$$

Equation 12

$$c_A(f) = 0.36961 + \frac{0.0026958}{\sqrt{f}} - \frac{0.65201}{f} + \frac{0.011320}{f\sqrt{f}}$$

Equation 13

**2.1.4 Modified Coefficient of Variation**

The coefficient of variation is modified according to the following rules:

$$\text{Modified CV} = CV^* = \begin{cases} .06 & \text{if } CV < .04 \\ \frac{CV}{2} + .04 & \text{if } .04 \leq CV < .08 \\ CV & \text{if } CV \geq .08 \end{cases}$$

Equation 14

This is converted to percent by multiplying by 100%.

CV\* is used to compute a modified standard deviation S\*.

$$S^* = CV^* \cdot \bar{X}$$

Equation 15

To compute the pooled standard deviation based on the modified CV:

$$S_p^* = \sqrt{\frac{\sum_{i=1}^k ((n_i - 1)(CV_i^* \cdot \bar{X}_i)^2)}{\sum_{i=1}^k (n_i - 1)}}$$

Equation 16

The A-basis and B-basis values under the assumption of the modified CV method are computed by replacing S with S\*

**2.1.4.1 Transformation of data based on Modified CV**

In order to determine if the data would pass the diagnostic tests under the assumption of the modified CV, the data must be transformed such that the batch means remain the same while the standard deviation of transformed data (all batches) matches the modified standard deviation.



To accomplish this requires a transformation in two steps:

Step 1: Apply the modified CV rules to each batch and compute the modified standard deviation  $S_i^* = CV^* \cdot \bar{X}_i$  for each batch. Transform the data in each batch as follows:

$$X'_{ij} = C_i (X_{ij} - \bar{X}_i) + \bar{X}_i \tag{Equation 17}$$

$$C_i = \frac{S_i^*}{S_i} \tag{Equation 18}$$

Run the Anderson-Darling k-sample test for batch equivalence (see section 2.1.6) on the transformed data. If it passes, proceed to step 2. If not, stop. The data cannot be pooled.

Step 2: Another transformation is needed as applying the modified CV to each batch leads to a larger CV for the combined data than when applying the modified CV rules to the combined data (due to the addition of between batch variation when combining data from multiple batches). In order to alter the data to match  $S^*$ , the transformed data is transformed again, this time setting using the same value of  $C'$  for all batches.

$$X''_{ij} = C' (X'_{ij} - \bar{X}_i) + \bar{X}_i \tag{Equation 19}$$

$$C' = \sqrt{\frac{SSE^*}{SSE'}} \tag{Equation 20}$$

$$SSE^* = (n-1)(CV^* \cdot \bar{X})^2 - \sum_{i=1}^k n_i (\bar{X}_i - \bar{X})^2 \tag{Equation 21}$$

$$SSE' = \sum_{i=1}^k \sum_{j=1}^{n_i} (X'_{ij} - \bar{X}_i)^2 \tag{Equation 22}$$

Once this second transformation has been completed, the k-sample Anderson Darling test for batch equivalence can be run on the transformed data to determine if the modified co-efficient of variation will permit pooling of the data.

### 2.1.5 Determination of Outliers

All outliers are identified in text and graphics. If an outlier is removed from the dataset, it will be specified and the reason why will be documented in the text. Outliers are identified using the Maximum Normed Residual Test for Outliers as specified in section 8.3.3 of CMH-17 Rev G.

$$MNR = \frac{\max_{all i} |X_i - \bar{X}|}{S}, i = 1 \dots n \tag{Equation 23}$$

$$C = \frac{n-1}{\sqrt{n}} \sqrt{\frac{t^2}{n-2+t^2}} \tag{Equation 24}$$

where t is the  $1 - \frac{.05}{2n}$  quartile of a t distribution with n-2 degrees of freedom.

If  $MNR > C$ , then the  $X_i$  associated with the MNR is considered to be an outlier. If an outlier exists, then the  $X_i$  associated with the MNR is dropped from the dataset and the MNR procedure is applied again. This process is repeated until no outliers are detected. Additional information on this procedure can be found in references 1 and 2.

**2.1.6 The k-Sample Anderson Darling Test for Batch Equivalency**

The k-sample Anderson-Darling test is a nonparametric statistical procedure that tests the hypothesis that the populations from which two or more groups of data were drawn are identical. The distinct values in the combined data set are ordered from smallest to largest, denoted  $z(1), z(2), \dots, z(L)$ , where  $L$  will be less than  $n$  if there are tied observations. These rankings are used to compute the test statistic.

The k-sample Anderson-Darling test statistic is:

$$ADK = \frac{n-1}{n^2(k-1)} \sum_{i=1}^k \left[ \frac{1}{n_i} \sum_{j=1}^L h_j \frac{(nF_{ij} - n_i H_j)^2}{H_j(n - H_j) - \frac{nh_j}{4}} \right] \tag{Equation 25}$$

Where

- $n_i$  = the number of test specimens in each batch
- $n = n_1 + n_2 + \dots + n_k$
- $h_j$  = the number of values in the combined samples equal to  $z(j)$
- $H_j$  = the number of values in the combined samples less than  $z(j)$  plus  $\frac{1}{2}$  the number of values in the combined samples equal to  $z(j)$
- $F_{ij}$  = the number of values in the  $i^{th}$  group which are less than  $z(j)$  plus  $\frac{1}{2}$  the number of values in this group which are equal to  $z(j)$ .

The critical value for the test statistic at  $1-\alpha$  level is computed:

$$ADC = 1 + \sigma_n \left[ z_\alpha + \frac{0.678}{\sqrt{k-1}} + \frac{0.362}{k-1} \right]. \tag{Equation 26}$$

This formula is based on the formula in reference 3 at the end of section 5, using a Taylor's expansion to estimate the critical value via the normal distribution rather than using the t distribution with  $k-1$  degrees of freedom.

$$\sigma_n^2 = VAR(ADK) = \frac{an^3 + bn^2 + cn + d}{(n-1)(n-2)(n-3)(k-1)^2} \tag{Equation 27}$$

With

$$\begin{aligned}
 a &= (4g - 6)(k - 1) + (10 - 6g)S \\
 b &= (2g - 4)k^2 + 8Tk + (2g - 14T - 4)S - 8T + 4g - 6 \\
 c &= (6T + 2g - 2)k^2 + (4T - 4g + 6)k + (2T - 6)S + 4T \\
 d &= (2T + 6)k^2 - 4Tk \\
 S &= \sum_{i=1}^k \frac{1}{n_i} \\
 T &= \sum_{i=1}^{n-1} \frac{1}{i} \\
 g &= \sum_{i=1}^{n-2} \sum_{j=i+1}^{n-1} \frac{1}{(n-i)j}
 \end{aligned}$$

The data is considered to have failed this test (i.e. the batches are not from the same population) when the test statistic is greater than the critical value. For more information on this procedure, see reference 3.

### 2.1.7 The Anderson Darling Test for Normality

**Normal Distribution:** A two parameter ( $\mu, \sigma$ ) family of probability distributions for which the probability that an observation will fall between  $a$  and  $b$  is given by the area under the curve between  $a$  and  $b$ :

$$F(x) = \int_a^b \frac{1}{\sigma\sqrt{2\pi}} e^{-\frac{(x-\mu)^2}{2\sigma^2}} dx \tag{Equation 28}$$

A normal distribution with parameters ( $\mu, \sigma$ ) has population mean  $\mu$  and variance  $\sigma^2$ .

The normal distribution is considered by comparing the cumulative normal distribution function that best fits the data with the cumulative distribution function of the data. Let

$$z_{(i)} = \frac{x_{(i)} - \bar{x}}{s}, \quad \text{for } i = 1, \dots, n \tag{Equation 29}$$

where  $x_{(i)}$  is the smallest sample observation,  $\bar{x}$  is the sample average, and  $s$  is the sample standard deviation.

The Anderson Darling test statistic (AD) is:

$$AD = \sum_{i=1}^n \frac{1-2i}{n} \left\{ \ln [F_0(z_{(i)})] + \ln [1 - F_0(z_{(n+1-i)})] \right\} - n \tag{Equation 30}$$

Where  $F_0$  is the standard normal distribution function. The observed significance level (OSL) is

$$OSL = \frac{1}{1 + e^{-0.48 + 0.78 \ln(AD^*) + 4.58 AD^*}}, \quad AD^* = \left(1 + \frac{0.2}{\sqrt{n}}\right) AD \quad \text{Equation 31}$$

This OSL measures the probability of observing an Anderson-Darling statistic at least as extreme as the value calculated if, in fact, the data are a sample from a normal population. If  $OSL > 0.05$ , the data is considered sufficiently close to a normal distribution.

### 2.1.8 Levene’s Test for Equality of Coefficient of Variation

Levene’s test performs an Analysis of Variance on the absolute deviations from their sample medians. The absolute value of the deviation from the median is computed for each data value.  $w_{ij} = |y_{ij} - \tilde{y}_i|$  An F-test is then performed on the transformed data values as follows:

$$F = \frac{\sum_{i=1}^k n_i (\bar{w}_i - \bar{w})^2 / (k - 1)}{\sum_{i=1}^k \sum_{j=1}^{n_i} (w_{ij} - \bar{w}_i)^2 / (n - k)} \quad \text{Equation 32}$$

If this computed F statistic is less than the critical value for the F-distribution having k-1 numerator and n-k denominator degrees of freedom at the 1- $\alpha$  level of confidence, then the data is not rejected as being too different in terms of the co-efficient of variation. ASAP provides the appropriate critical values for F at  $\alpha$  levels of 0.10, 0.05, 0.025, and 0.01. For more information on this procedure, see references 4 and 5.

## 2.2 STAT-17

This section contains the details of the specific formulas STAT-17 uses in its computations.

The basic descriptive statistics, the maximum normed residual (MNR) test for outliers, and the Anderson Darling K-sample test for batch variability are the same as with ASAP – see sections 2.1.1, 2.1.3.1, and 2.1.5.

Outliers must be dispositioned before checking any other test results. The results of the Anderson Darling k-Sample (ADK) Test for batch equivalency must be checked. If the data passes the ADK test, then the appropriate distribution is determined. If it does not pass the ADK test, then the ANOVA procedure is the only approach remaining that will result in basis values that meet the requirements of CMH-17 Rev G.

### 2.2.1 Distribution Tests

In addition to testing for normality using the Anderson-Darling test (see 2.1.7); Stat17 also tests to see if the Weibull or Lognormal distribution is a good fit for the data.

Each distribution is considered using the Anderson-Darling test statistic which is sensitive to discrepancies in the tail regions. The Anderson-Darling test compares the cumulative distribution function for the distribution of interest with the cumulative distribution function of the data.

An observed significance level (OSL) based on the Anderson-Darling test statistic is computed for each test. The OSL measures the probability of observing an Anderson-Darling test statistic at least as extreme as the value calculated if the distribution under consideration is in fact the underlying distribution of the data. In other words, the OSL is the probability of obtaining a value of the test statistic at least as large as that obtained if the hypothesis that the data are actually from the distribution being tested is true. If the OSL is less than or equal to 0.05, then the assumption that the data are from the distribution being tested is rejected with at most a five percent risk of being in error.

If the normal distribution has an OSL greater than 0.05, then the data is assumed to be from a population with a normal distribution. If not, then if either the Weibull or lognormal distributions has an OSL greater than 0.05, then one of those can be used. If neither of these distributions has an OSL greater than 0.05, a non-parametric approach is used.

In what follows, unless otherwise noted, the sample size is denoted by  $n$ , the sample observations by  $x_1, \dots, x_n$ , and the sample observations ordered from least to greatest by  $x_{(1)}, \dots, x_{(n)}$ .

**2.2.2 Computing Normal Distribution Basis Values**

Stat17 uses a table of values for the k-factors (shown in Table 2-1) when the sample size is less than 16 and a slightly different formula than ASAP to compute approximate k-values for the normal distribution when the sample size is 16 or larger.

Norm. Dist. k Factors for N<16		
N	B-basis	A-basis
2	20.581	37.094
3	6.157	10.553
4	4.163	7.042
5	3.408	5.741
6	3.007	5.062
7	2.756	4.642
8	2.583	4.354
9	2.454	4.143
10	2.355	3.981
11	2.276	3.852
12	2.211	3.747
13	2.156	3.659
14	2.109	3.585
15	2.069	3.520

**Table 2-1: K factors for normal distribution**

**2.2.2.1 One-sided B-basis tolerance factors,  $k_B$ , for the normal distribution when sample size is greater than 15.**

The exact computation of  $k_B$  values is  $1/\sqrt{n}$  times the 0.95th quantile of the noncentral t-distribution with noncentrality parameter  $1.282\sqrt{n}$  and  $n - 1$  degrees of freedom. Since this is not a calculation that Excel can handle, the following approximation to the  $k_B$  values is used:

$$k_B \approx 1.282 + \exp\{0.958 - 0.520 \ln(n) + 3.19/n\} \quad \text{Equation 33}$$

This approximation is accurate to within 0.2% of the tabulated values for sample sizes greater than or equal to 16.

**2.2.2.2 One-sided A-basis tolerance factors,  $k_A$ , for the normal distribution**

The exact computation of  $k_B$  values is  $1/\sqrt{n}$  times the 0.95th quantile of the noncentral t-distribution with noncentrality parameter  $2.326\sqrt{n}$  and  $n - 1$  degrees of freedom (Reference 11). Since this is not a calculation that Excel can handle easily, the following approximation to the  $k_B$  values is used:

$$k_A \approx 2.326 + \exp\{1.34 - 0.522 \ln(n) + 3.87/n\} \quad \text{Equation 34}$$

This approximation is accurate to within 0.2% of the tabulated values for sample sizes greater than or equal to 16.

**2.2.2.3 Two-parameter Weibull Distribution**

A probability distribution for which the probability that a randomly selected observation from this population lies between  $a$  and  $b$  ( $0 < a < b < \infty$ ) is given by

$$e^{-(a/\alpha)^\beta} - e^{-(b/\alpha)^\beta} \quad \text{Equation 35}$$

where  $\alpha$  is called the scale parameter and  $\beta$  is called the shape parameter.

In order to compute a check of the fit of a data set to the Weibull distribution and compute basis values assuming Weibull, it is first necessary to obtain estimates of the population shape and scale parameters (Section 2.2.2.3.1). Calculations specific to the goodness-of-fit test for the Weibull distribution are provided in section 2.2.2.3.2.

**2.2.2.3.1 Estimating Weibull Parameters**

This section describes the *maximum likelihood* method for estimating the parameters of the two-parameter Weibull distribution. The maximum-likelihood estimates of the shape and scale parameters are denoted  $\hat{\beta}$  and  $\hat{\alpha}$ . The estimates are the solution to the pair of equations:

$$\hat{\alpha}\hat{\beta}n - \frac{\hat{\beta}}{\hat{\alpha}^{\hat{\beta}-1}} \sum_{i=1}^n x_i^{\hat{\beta}} = 0 \quad \text{Equation 36}$$

$$\frac{n}{\hat{\beta}} - n \ln \hat{\alpha} + \sum_{i=1}^n \ln x_i - \sum_{i=1}^n \left[ \frac{x_i}{\hat{\alpha}} \right]^{\hat{\beta}} (\ln x_i - \ln \hat{\alpha}) = 0 \quad \text{Equation 37}$$

Stat17 solves these equations numerically for  $\hat{\beta}$  and  $\hat{\alpha}$  in order to compute basis values.

**2.2.2.3.2 Goodness-of-fit test for the Weibull distribution**

The two-parameter Weibull distribution is considered by comparing the cumulative Weibull distribution function that best fits the data with the cumulative distribution function of the data. Using the shape and scale parameter estimates from section 2.2.2.3.1, let

$$z_{(i)} = \left[ x_{(i)} / \hat{\alpha} \right]^{\hat{\beta}}, \text{ for } i = 1, \dots, n \tag{Equation 38}$$

The Anderson-Darling test statistic is

$$AD = \sum_{i=1}^n \frac{1-2i}{n} \left[ \ln \left[ 1 - \exp(-z_{(i)}) \right] - z_{(n+1-i)} \right] - n \tag{Equation 39}$$

and the observed significance level is

$$OSL = 1 / \left\{ 1 + \exp[-0.10 + 1.24 \ln(AD^*) + 4.48 AD^*] \right\} \tag{Equation 40}$$

where

$$AD^* = \left( 1 + \frac{0.2}{\sqrt{n}} \right) AD \tag{Equation 41}$$

This OSL measures the probability of observing an Anderson-Darling statistic at least as extreme as the value calculated if in fact the data is a sample from a two-parameter Weibull distribution. If  $OSL \leq 0.05$ , one may conclude (at a five percent risk of being in error) that the population does not have a two-parameter Weibull distribution. Otherwise, the hypothesis that the population has a two-parameter Weibull distribution is not rejected. For further information on these procedures, see reference 6.

**2.2.2.3.3 Basis value calculations for the Weibull distribution**

For the two-parameter Weibull distribution, the B-basis value is

$$B = \hat{q} e^{\left( \frac{-V}{\hat{\beta} \sqrt{n}} \right)} \tag{Equation 42}$$

where

$$\hat{q} = \hat{\alpha} (0.10536)^{1/\hat{\beta}} \tag{Equation 43}$$

To calculate the A-basis value, substitute the equation below for the equation above.

$$\hat{q} = \hat{\alpha} (0.01005)^{1/\hat{\beta}} \tag{Equation 44}$$

V is the value in Table 2-2. when the sample size is less than 16. For sample sizes of 16 or larger, a numerical approximation to the V values is given in the two equations immediately below.

$$V_B \approx 3.803 + \exp \left[ 1.79 - 0.516 \ln(n) + \frac{5.1}{n-1} \right] \quad \text{Equation 45}$$

$$V_A \approx 6.649 + \exp \left[ 2.55 - 0.526 \ln(n) + \frac{4.76}{n} \right] \quad \text{Equation 46}$$

This approximation is accurate within 0.5% of the tabulated values for n greater than or equal to 16.

N	B-basis	A-basis
2	690.804	1284.895
3	47.318	88.011
4	19.836	36.895
5	13.145	24.45
6	10.392	19.329
7	8.937	16.623
8	8.047	14.967
9	7.449	13.855
10	6.711	12.573
11	6.477	12.093
12	6.286	11.701
13	6.127	11.375
14	5.992	11.098
15	5.875	10.861

Table 2-2: Weibull Distribution Basis Value Factors

**2.2.2.4 Lognormal Distribution**

A probability distribution for which the probability that an observation selected at random from this population falls between a and b ( $0 < a < b < \infty$ ) is given by the area under the normal distribution between  $\ln(a)$  and  $\ln(b)$ .

The lognormal distribution is a positively skewed distribution that is simply related to the normal distribution. If something is lognormally distributed, then its logarithm is normally distributed. The natural (base e) logarithm is used.

**2.2.2.4.1 Goodness-of-fit test for the Lognormal distribution**

In order to test the goodness-of-fit of the lognormal distribution, take the logarithm of the data and perform the Anderson-Darling test for normality from Section 2.1.7. Using the natural logarithm, replace the linked equation above with linked equation below:

$$z_{(i)} = \frac{\ln(x_{(i)}) - \bar{x}_L}{s_L}, \quad \text{for } i = 1, \dots, n \quad \text{Equation 47}$$

where  $x_{(i)}$  is the  $i^{\text{th}}$  smallest sample observation,  $\bar{x}_L$  and  $s_L$  are the mean and standard deviation of the  $\ln(x_i)$  values.



The Anderson-Darling statistic is then computed using the linked equation above and the observed significance level (OSL) is computed using the linked equation above. This OSL measures the probability of observing an Anderson-Darling statistic at least as extreme as the value calculated if in fact the data are a sample from a lognormal distribution. If  $OSL \leq 0.05$ , one may conclude (at a five percent risk of being in error) that the population is not lognormally distributed. Otherwise, the hypothesis that the population is lognormally distributed is not rejected. For further information on these procedures, see reference 6.

#### 2.2.2.4.2 Basis value calculations for the Lognormal distribution

If the data set is assumed to be from a population with a lognormal distribution, basis values are calculated using the equation above in section 2.1.3. However, the calculations are performed using the logarithms of the data rather than the original observations. The computed basis values are then transformed back to the original units by applying the inverse of the log transformation.

### 2.2.3 Non-parametric Basis Values

Non-parametric techniques do not assume any particularly underlying distribution for the population the sample comes from. It does require that the batches be similar enough to be grouped together, so the ADK test must have a positive result. While it can be used instead of assuming the normal, lognormal or Weibull distribution, it typically results in lower basis values. One of following two methods should be used, depending on the sample size.

#### 2.2.3.1 Non-parametric Basis Values for large samples

The required sample sizes for this ranking method differ for A and B basis values. A sample size of at least 29 is needed for the B-basis value while a sample size of 299 is required for the A-basis.

To calculate a B-basis value for  $n > 28$ , the value of  $r$  is determined with the following formulas:

For B-basis values:

$$r_B = \frac{n}{10} - 1.645 \sqrt{\frac{9n}{100}} + 0.23 \quad \text{Equation 48}$$

For A-Basis values:

$$r_A = \frac{n}{100} - 1.645 \sqrt{\frac{99n}{10,000}} + 0.29 + \frac{19.1}{n} \quad \text{Equation 49}$$

The formula for the A-basis values should be rounded to the nearest integer. This approximation is exact for most values and for a small percentage of values (less than 0.2%), the approximation errs by one rank on the conservative side.

The B-basis value is the  $r_B^{\text{th}}$  lowest observation in the data set, while the A-basis values are the  $r_A^{\text{th}}$  lowest observation in the data set. For example, in a sample of size  $n = 30$ , the lowest ( $r = 1$ )

observation is the B-basis value. Further information on this procedure may be found in reference 7.

### 2.2.3.2 Non-parametric Basis Values for small samples

The Hanson-Koopmans method (references 8 and 9) is used for obtaining a B-basis value for sample sizes not exceeding 28 and A-basis values for sample sizes less than 299. This procedure requires the assumption that the observations are a random sample from a population for which the logarithm of the cumulative distribution function is concave, an assumption satisfied by a large class of probability distributions. There is substantial empirical evidence that suggests that composite strength data satisfies this assumption.

The Hanson-Koopmans B-basis value is:

$$B = x_{(r)} \left[ \frac{x_{(1)}}{x_{(r)}} \right]^k \quad \text{Equation 50}$$

The A-basis value is:

$$A = x_{(n)} \left[ \frac{x_{(1)}}{x_{(n)}} \right]^k \quad \text{Equation 51}$$

where  $x_{(n)}$  is the largest data value,  $x_{(1)}$  is the smallest, and  $x_{(r)}$  is the  $r^{\text{th}}$  largest data value. The values of  $r$  and  $k$  depend on  $n$  and are listed in Table 2-3. This method is not used for the B-basis value when  $x_{(r)} = x_{(1)}$ .

The Hanson-Koopmans method can be used to calculate A-basis values for  $n$  less than 299. Find the value  $k_A$  corresponding to the sample size  $n$  in Table 2-4. For an A-basis value that meets all the requirements of CMH-17 Rev G, there must be at least five batches represented in the data and at least 55 data points. For a B-basis value, there must be at least three batches represented in the data and at least 18 data points.

B-Basis Hanson-Koopmans Table		
n	r	k
2	2	35.177
3	3	7.859
4	4	4.505
5	4	4.101
6	5	3.064
7	5	2.858
8	6	2.382
9	6	2.253
10	6	2.137
11	7	1.897
12	7	1.814
13	7	1.738
14	8	1.599
15	8	1.540
16	8	1.485
17	8	1.434
18	9	1.354
19	9	1.311
20	10	1.253
21	10	1.218
22	10	1.184
23	11	1.143
24	11	1.114
25	11	1.087
26	11	1.060
27	11	1.035
28	12	1.010

Table 2-3: B-Basis Hanson-Koopmans Table

DISCONTINUED

A-Basis Hanson-Koopmans Table					
n	k	n	k	n	k
2	80.00380	38	1.79301	96	1.32324
3	16.91220	39	1.77546	98	1.31553
4	9.49579	40	1.75868	100	1.30806
5	6.89049	41	1.74260	105	1.29036
6	5.57681	42	1.72718	110	1.27392
7	4.78352	43	1.71239	115	1.25859
8	4.25011	44	1.69817	120	1.24425
9	3.86502	45	1.68449	125	1.23080
10	3.57267	46	1.67132	130	1.21814
11	3.34227	47	1.65862	135	1.20620
12	3.15540	48	1.64638	140	1.19491
13	3.00033	49	1.63456	145	1.18421
14	2.86924	50	1.62313	150	1.17406
15	2.75672	52	1.60139	155	1.16440
16	2.65889	54	1.58101	160	1.15519
17	2.57290	56	1.56184	165	1.14640
18	2.49660	58	1.54377	170	1.13801
19	2.42833	60	1.52670	175	1.12997
20	2.36683	62	1.51053	180	1.12226
21	2.31106	64	1.49520	185	1.11486
22	2.26020	66	1.48063	190	1.10776
23	2.21359	68	1.46675	195	1.10092
24	2.17067	70	1.45352	200	1.09434
25	2.13100	72	1.44089	205	1.08799
26	2.09419	74	1.42881	210	1.08187
27	2.05991	76	1.41724	215	1.07595
28	2.02790	78	1.40614	220	1.07024
29	1.99791	80	1.39549	225	1.06471
30	1.96975	82	1.38525	230	1.05935
31	1.94324	84	1.37541	235	1.05417
32	1.91822	86	1.36592	240	1.04914
33	1.89457	88	1.35678	245	1.04426
34	1.87215	90	1.34796	250	1.03952
35	1.85088	92	1.33944	275	1.01773
36	1.83065	94	1.33120	299	1.00000
37	1.81139				

Table 2-4: A-Basis Hanson-Koopmans Table

**2.2.4 Analysis of Variance (ANOVA) Basis Values**

ANOVA is used to compute basis values when the batch to batch variability of the data does not pass the ADK test. Since ANOVA makes the assumption that the different batches have equal variances, the data is checked to make sure the assumption is valid. Levene’s test for equality of variance is used (see section 2.1.8). If the dataset fails Levene’s test, the basis values computed are likely to be conservative. Thus this method can still be used but the values produced will be listed as estimates.

**2.2.4.1 Calculation of basis values using ANOVA**

The following calculations address batch-to-batch variability. In other words, the only grouping is due to batches and the k-sample Anderson-Darling test (Section 2.1.6) indicates that the batch to batch variability is too large to pool the data. The method is based on the one-way analysis of variance random-effects model, and the procedure is documented in reference 10.

ANOVA separates the total variation (called the sum of squares) of the data into two sources: between batch variation and within batch variation.

First, statistics are computed for each batch, which are indicated with a subscript  $(n_i, \bar{x}_i, s_i^2)$  while statistics that were computed with the entire dataset do not have a subscript. Individual data values are represented with a double subscript, the first number indicated the batch and the second distinguishing between the individual data values within the batch.  $k$  stands for the number of batches in the analysis. With these statistics, the Sum of Squares Between batches (SSB) and the Total Sum of Squares (SST) are computed:

$$SSB = \sum_{i=1}^k n_i \bar{x}_i^2 - n \bar{x}^2 \tag{Equation 52}$$

$$SST = \sum_{i=1}^k \sum_{j=1}^{n_i} x_{ij}^2 - n \bar{x}^2 \tag{Equation 53}$$

The within-batch, or error, sum of squares (SSE) is computed by subtraction

$$SSE = SST - SSB \tag{Equation 54}$$

Next, the mean sums of squares are computed:

$$MSB = \frac{SSB}{k-1} \tag{Equation 55}$$

$$MSE = \frac{SSE}{n-k} \tag{Equation 56}$$

Since the batches need not have equal numbers of specimens, an ‘effective batch size,’ is defined as

$$n' = \frac{n - \frac{1}{n} \sum_{i=1}^k n_i^2}{k-1} \tag{Equation 57}$$

Using the two mean squares and the effective batch size, an estimate of the population standard deviation is computed:

$$S = \sqrt{\frac{MSB}{n'} + \left(\frac{n'-1}{n'}\right)MSE} \tag{Equation 58}$$

Two k-factors are computed using the methodology of section 2.2.2 using a sample size of  $n$  (denoted  $k_0$ ) and a sample size of  $k$  (denoted  $k_1$ ). Whether this value is an A- or B-basis value depends only on whether  $k_0$  and  $k_1$  are computed for A or B-basis values.

Denote the ratio of mean squares by

$$u = \frac{MSB}{MSE} \quad \text{Equation 59}$$

If  $u$  is less than one, it is set equal to one. The tolerance limit factor is

$$T = \frac{k_0 - \frac{k_1}{\sqrt{n'}} + (k_1 - k_0) \sqrt{\frac{u}{u + n' - 1}}}{1 - \frac{1}{\sqrt{n'}}} \quad \text{Equation 60}$$

The basis value is  $\bar{x} - TS$ .

The ANOVA method can produce extremely conservative basis values when a small number of batches are available. Therefore, when less than five (5) batches are available and the ANOVA method is used, the basis values produced will be listed as estimates.

### 2.3 Single Batch and Two Batch Estimates using Modified CV

This method has not been approved for use by the CMH-17 organization. Values computed in this manner are estimates only. It is used only when fewer than three batches are available and no valid B-basis value could be computed using any other method. The estimate is made using the mean of the data and setting the coefficient of variation to 8 percent if it was less than that. A modified standard deviation ( $S_{adj}$ ) was computed by multiplying the mean by 0.08 and computing the A and B-basis values using this inflated value for the standard deviation.

$$\text{Estimated B-Basis} = \bar{X} - k_b S_{adj} = \bar{X} - k_b \cdot 0.08 \cdot \bar{X} \quad \text{Equation 61}$$

### 2.4 Lamina Variability Method (LVM)

This method has not been approved for use by the CMH-17 organization. Values computed in this manner are estimates only. It is used only when the sample size is less than 16 and no valid B-basis value could be computed using any other method. The prime assumption for applying the LVM is that the intrinsic strength variability of the laminate (small) dataset is no greater than the strength variability of the lamina (large) dataset. This assumption was tested and found to be reasonable for composite materials as documented by Tomblin and Seneviratne [12].

To compute the estimate, the coefficients of variation (CVs) of laminate data are paired with lamina CV's for the same loading condition and environmental condition. For example, the 0° compression lamina CV CTD condition is used with open hole compression CTD condition. Bearing and in-plane shear laminate CV's are paired with 0° compression lamina CV's. However, if the laminate CV is larger than the corresponding lamina CV, the larger laminate CV value is used.

The LVM B-basis value is then computed as:

$$\text{LVM Estimated B-Basis} = \bar{X}_1 - K_{(N_1, N_2)} \cdot \bar{X}_1 \cdot \max(CV_1, CV_2) \quad \text{Equation 62}$$

When used in conjunction with the modified CV approach, a minimum value of 8% is used for the CV.

$$\text{Mod CV LVM Estimated B-Basis} = \bar{X}_1 - K_{(N_1, N_2)} \cdot \bar{X}_1 \cdot \text{Max}(8\%, CV_1, CV_2) \quad \text{Equation 63}$$

With:

- $\bar{X}_1$  the mean of the laminate (small dataset)
- $N_1$  the sample size of the laminate (small dataset)
- $N_2$  the sample size of the lamina (large dataset)
- $CV_1$  is the coefficient of variation of the laminate (small dataset)
- $CV_2$  is the coefficient of variation of the lamina (large dataset)
- $K_{(N_1, N_2)}$  is given in Table 2-5

		N1														
		2	3	4	5	6	7	8	9	10	11	12	13	14	15	
N1+N2-2	2	0	0	0	0	0	0	0	0	0	0	0	0	0	0	
	3	4.508	0	0	0	0	0	0	0	0	0	0	0	0	0	
	4	3.827	3.607	0	0	0	0	0	0	0	0	0	0	0	0	
	5	3.481	3.263	3.141	0	0	0	0	0	0	0	0	0	0	0	
	6	3.273	3.056	2.934	2.854	0	0	0	0	0	0	0	0	0	0	
	7	3.134	2.918	2.796	2.715	2.658	0	0	0	0	0	0	0	0	0	
	8	3.035	2.820	2.697	2.616	2.558	2.515	0	0	0	0	0	0	0	0	
	9	2.960	2.746	2.623	2.541	2.483	2.440	2.405	0	0	0	0	0	0	0	
	10	2.903	2.688	2.565	2.484	2.425	2.381	2.346	2.318	0	0	0	0	0	0	
	11	2.856	2.643	2.519	2.437	2.378	2.334	2.299	2.270	2.247	0	0	0	0	0	
	12	2.819	2.605	2.481	2.399	2.340	2.295	2.260	2.231	2.207	2.187	0	0	0	0	
	13	2.787	2.574	2.450	2.367	2.308	2.263	2.227	2.198	2.174	2.154	2.137	0	0	0	
	14	2.761	2.547	2.423	2.341	2.281	2.236	2.200	2.171	2.147	2.126	2.109	2.093	0	0	
	15	2.738	2.525	2.401	2.318	2.258	2.212	2.176	2.147	2.123	2.102	2.084	2.069	2.056	0	
	16	2.719	2.505	2.381	2.298	2.238	2.192	2.156	2.126	2.102	2.081	2.063	2.048	2.034	2.022	
	17	2.701	2.488	2.364	2.280	2.220	2.174	2.138	2.108	2.083	2.062	2.045	2.029	2.015	2.003	
	18	2.686	2.473	2.348	2.265	2.204	2.158	2.122	2.092	2.067	2.046	2.028	2.012	1.999	1.986	
	19	2.673	2.459	2.335	2.251	2.191	2.144	2.108	2.078	2.053	2.032	2.013	1.998	1.984	1.971	
	20	2.661	2.447	2.323	2.239	2.178	2.132	2.095	2.065	2.040	2.019	2.000	1.984	1.970	1.958	
	21	2.650	2.437	2.312	2.228	2.167	2.121	2.084	2.053	2.028	2.007	1.988	1.972	1.958	1.946	
22	2.640	2.427	2.302	2.218	2.157	2.110	2.073	2.043	2.018	1.996	1.978	1.962	1.947	1.935		
23	2.631	2.418	2.293	2.209	2.148	2.101	2.064	2.033	2.008	1.987	1.968	1.952	1.938	1.925		
24	2.623	2.410	2.285	2.201	2.139	2.092	2.055	2.025	1.999	1.978	1.959	1.943	1.928	1.916		
25	2.616	2.402	2.277	2.193	2.132	2.085	2.047	2.017	1.991	1.969	1.951	1.934	1.920	1.907		
26	2.609	2.396	2.270	2.186	2.125	2.078	2.040	2.009	1.984	1.962	1.943	1.927	1.912	1.900		
27	2.602	2.389	2.264	2.180	2.118	2.071	2.033	2.003	1.977	1.955	1.936	1.920	1.905	1.892		
28	2.597	2.383	2.258	2.174	2.112	2.065	2.027	1.996	1.971	1.949	1.930	1.913	1.899	1.886		
29	2.591	2.378	2.252	2.168	2.106	2.059	2.021	1.990	1.965	1.943	1.924	1.907	1.893	1.880		
30	2.586	2.373	2.247	2.163	2.101	2.054	2.016	1.985	1.959	1.937	1.918	1.901	1.887	1.874		
40	2.550	2.337	2.211	2.126	2.063	2.015	1.977	1.946	1.919	1.897	1.877	1.860	1.845	1.832		
50	2.528	2.315	2.189	2.104	2.041	1.993	1.954	1.922	1.896	1.873	1.853	1.836	1.820	1.807		
60	2.514	2.301	2.175	2.089	2.026	1.978	1.939	1.907	1.880	1.857	1.837	1.819	1.804	1.790		
70	2.504	2.291	2.164	2.079	2.016	1.967	1.928	1.896	1.869	1.846	1.825	1.808	1.792	1.778		
80	2.496	2.283	2.157	2.071	2.008	1.959	1.920	1.887	1.860	1.837	1.817	1.799	1.783	1.769		
90	2.491	2.277	2.151	2.065	2.002	1.953	1.913	1.881	1.854	1.830	1.810	1.792	1.776	1.762		
100	2.486	2.273	2.146	2.060	1.997	1.948	1.908	1.876	1.849	1.825	1.805	1.787	1.771	1.757		
125	2.478	2.264	2.138	2.051	1.988	1.939	1.899	1.867	1.839	1.816	1.795	1.777	1.761	1.747		
150	2.472	2.259	2.132	2.046	1.982	1.933	1.893	1.861	1.833	1.809	1.789	1.770	1.754	1.740		
175	2.468	2.255	2.128	2.042	1.978	1.929	1.889	1.856	1.828	1.805	1.784	1.766	1.750	1.735		
200	2.465	2.252	2.125	2.039	1.975	1.925	1.886	1.853	1.825	1.801	1.781	1.762	1.746	1.732		

Table 2-5: B-Basis factors for small datasets using variability of corresponding large dataset

### 3. Summary of Results

The basis values for all tests are summarized in the following tables. The NCAMP recommended B-basis values meet all requirements of CMH-17 Rev G. However, not all test data meets those requirements. The summary tables provide a complete listing of all computed basis values and estimates of basis values. Data that does not meet the requirements of CMH-17 Rev G are shown in shaded boxes and labeled as estimates. Basis values computed with the modified coefficient of variation (CV) are presented whenever possible. Basis values and estimates computed without that modification are presented for all tests.

#### 3.1 NCAMP Recommended B-basis Values

The following rules are used in determining what B-basis value, if any, is included in tables Table 3-1 and Table 3-2 of recommended values.

1. Recommended values are NEVER estimates. Only B-basis values that meet all requirements of CMH-17 Rev G are recommended.
2. Modified CV basis values are preferred. Recommended values will be the modified CV basis value when available. The CV provided with the recommended basis value will be the one used in the computation of the basis value.
3. Only normalized basis values are given for properties that are normalized.
4. ANOVA B-basis values are not recommended since only three batches of material are available and CMH-17 Rev G recommends that no less than five batches be used when computing basis values with the ANOVA method.
5. Basis values of 90% or more of the mean value imply that the CV is unusually low and may not be conservative. Caution is recommended with B-Basis values calculated from STAT17 when the B-basis value is 90% or more of the average value. Such values will be indicated.
6. If the data appear questionable (e.g. when the CTD-RTD-ETW trend of the basis values are not consistent with the CTD-RTD-ETW trend of the average values), then the B-basis values will not be recommended.



**NCAMP Recommended B-basis Values for  
Cytac Cycom 5250-5 T650 6K-135-5HS Fabric**

All B-basis values in this table meet the standards for publication in CMH-17G Handbook  
Values are for normalized data unless otherwise noted

**Lamina Strength Tests**

Environment	Statistic	WT	WC	FT	FC	SBS*	IPS*		
							0.2% Offset	5% Strain	Peak before 5% Strain
CTD (-65° F)	B-basis	109.61	101.14	105.14	99.32	9.49	9.83		13.23
	Mean	123.56	112.92	118.51	112.18	10.99	10.87		14.91
	CV	6.51	7.12	6.53	7.50	7.14	6.00		6.00
RTD (70° F)	B-basis	114.66	97.17	113.10	93.65	10.18	7.34		
	Mean	128.78	109.07	126.47	106.50	11.53	8.37		
	CV	6.86	6.00	6.27	6.72	6.17	6.00		
ETD (350° F)	B-basis		74.61		69.35	6.14			
	Mean		86.11		81.98	6.93			
	CV		7.21		7.97	6.00			
ETW (350° F)	B-basis	NA (1)	NA (1)	NA (1)	NA:A	NA (1)	NA (1)	NA:I	
	Mean	125.53	56.03	116.98	52.63	4.07	2.01	4.23	
	CV	3.92	11.94	4.40	10.25	2.69	4.65	3.71	

Notes: The modified CV B-basis value is recommended when available.

The CV provided corresponds with the B-basis value given.

NA implies that tests were run but data did not meet NCAMP recommended requirements.


"NA: A" indicates ANOVA with 3 batches, "NA: I" indicates insufficient data,

NA (1): Users of ETW condition data are cautioned of the fact that ETW test temperature of 350°F is not 50°F (28°C) or more below the wet glass transition temperature as is recommended. They are advised to refer to CMH-17 Rev G section 22.8 and DOT/FAA/AR-01/40 for more information about establishing MOL.

Shaded empty boxes indicate that no test data is available for that property and condition.

\* Data is as measured rather than normalized

\*\* indicates the Stat17 B-basis value is greater than 90% of the mean value.

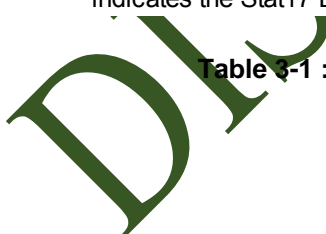

**Table 3-1 : NCAMP Recommended B-basis values for Lamina Test Data**

**NCAMP Recommended B-basis Values for  
Cytex Cycom 5250-5 T650 6K-135-5HS Fabric**

All B-basis values in this table meet the standards for publication in CMH-17G Handbook  
Values are for normalized data unless otherwise noted

**Laminate Strength Tests**

Lay-up	ENV	Statistic	OHT	OHC	FHT	FHC	UNT	UNC	SSB 2% Offset	SSB Ult.	LSBS*	
25/50/25	CTD (-65° F)	B-basis	43.00		48.09		74.97					
		Mean	48.43		53.78		83.91					
		CV	6.00		6.00		6.00					
	RTD (70° F)	B-basis	45.30	41.22	49.47	67.02	77.00	75.53	94.01		9.11	
		Mean	50.74	46.54	55.15	77.20	85.99	88.16	108.01		10.49	
		CV	6.10	6.00	6.15	6.76	6.00	7.35	7.20		6.83	
	ETW (350° F)	B-basis	NA (1)	NA:A	NA (1)	NA (1)	NA (1)	NA (1)	NA (1)	NA (1)	NA (1)	NA:A
		Mean	54.53	27.59	52.03	41.92	77.98	40.27	77.67	92.83	5.08	
		CV	2.71	6.15	3.07	14.35	5.28	7.74	10.01	8.24	8.65	
10/80/10	CTD (-65° F)	B-basis	35.43		41.51		50.21					
		Mean	40.13		45.79		55.60					
		CV	6.00		6.00		6.00					
	RTD (70° F)	B-basis	34.97	34.00	40.55	49.91	49.09	52.35	96.45			
		Mean	39.60	37.37	44.82	56.52	54.43	58.07	109.41			
		CV	6.00	6.00	6.00	6.00	6.00	6.55	6.00			
	ETW (350° F)	B-basis	NA (1)	NA (1)	NA (1)	NA:A	NA (1)	NA (1)	NA (1)	NA (1)	NA (1)	
		Mean	28.23	22.77	28.92	29.02	38.39	25.95	75.47	94.71		
		CV	6.30	4.26	3.35	10.48	5.24	9.17	9.40	6.66		
40/20/40	CTD (-65° F)	B-basis	51.86		53.61		89.74					
		Mean	58.84		60.18		101.26					
		CV	6.43		6.02		6.15					
	RTD (70° F)	B-basis	54.95	44.79	55.31		95.97	75.53	92.25			
		Mean	61.89	49.58	61.87		107.44	85.91	104.05			
		CV	6.36	6.31	6.31		6.00	6.20	7.63			
	ETW (350° F)	B-basis	NA (1)	NA (1)	NA (1)	NA (1)	NA (1)	NA:A	NA (1)	NA (1)		
		Mean	70.16	32.09	61.44	46.95	100.59	47.29	66.67	81.48		
		CV	3.37	4.89	2.96	5.42	5.94	7.58	7.08	5.18		

Notes: The modified CV B-basis value is recommended when available.

The CV provided corresponds with the B-basis value given.

NA implies that tests were run but data did not meet NCAMP recommended requirements.

"NA: A" indicates ANOVA with 3 batches, "NA: I" indicates insufficient data,

NA (1): Users of ETW condition data are cautioned of the fact that ETW test temperature of 350°F is not 50°F (28°C) or more below the wet glass transition temperature as is recommended. They are advised to refer to CMH-17 Rev G section 22.8 and DOT/FAA/AR-01/40 for more information about establishing MOL.

Shaded empty boxes indicate that no test data is available for that property and condition.

\* Data is as measured rather than normalized

\*\* indicates the Stat17 B-basis value is greater than 90% of the mean value.

Table 3-2 : NCAMP Recommended B-basis values for Laminate Test Data

3.2 Lamina and Laminate Summary Tables

<b>Prepreg Material:</b>	Cytec Cycom® 5250-5 T650 6K-135-5HS fabric NMS 226/2 Material Specification			Cytec Cycom® 5250-5 T650 6K-135-5HS Lamina Properties Summary
<b>Fabric:</b>	T650 6K-135-5HS weave	<b>Resin:</b>	Cytec Cycom® 5250-5	
	<b>Tg(dry):</b> 466.88 °F	<b>Tg(bone dry):</b> 522.83 °F	<b>Tg(wet):</b> 378.38 °F	<b>Tg METHOD:</b> DMA (SRM 18-94)
<b>PROCESSING:</b>	NPS 81226 Process Specification "C" Cure Cycle			

<b>Date of fiber manufacture</b>	8/16/2006	<b>Date of testing</b>	10/9/2008-8/11/2010
<b>Date of resin manufacture</b>	7/9/2007-7/11/2007	<b>Date of data submittal</b>	November 2010
<b>Date of prepreg manufacture</b>	7/9/2007-7/11/2007	<b>Date of analysis</b>	6/1/2011-5/30/2012
<b>Date of composite manufacture</b>	3/31/2008		

LAMINA MECHANICAL PROPERTY B-BASIS SUMMARY												
Data reported: As measured followed by normalized values in parentheses, normalizing tply: 0.0152 in												
Values shown in shaded boxes do not meet CMH-17G requirements and are estimates only												
These values may not be used for certification unless specifically allowed by the certifying agency												
	CTD			RTD			ETD			ETW <sup>(1)</sup>		
	B-Basis	Modified CV B-basis	Mean	B-Basis	Modified CV B-basis	Mean	B-Basis	Modified CV B-basis	Mean	B-Basis	Modified CV B-basis	Mean
<b>F<sub>1</sub><sup>tu</sup> (ksi)</b>	110.62 (112.89)	107.33 (109.61)	122.35 (123.56)	94.28 (117.98)	111.03 (114.66)	128.61 (128.78)				115.96 (114.78)	110.66 (111.47)	124.94 (125.53)
<b>E<sub>1</sub><sup>t</sup> (Msi)</b>			9.75 (9.86)			9.81 (9.82)						9.18 (9.22)
<b>V<sub>12</sub><sup>t</sup></b>			0.024			0.037						NA
<b>F<sub>2</sub><sup>tu</sup> (ksi)</b>	107.40 (108.66)	104.26 (105.14)	117.88 (118.51)	115.44 (116.62)	112.29 (113.10)	125.92 (126.47)				105.92 (107.23)	102.81 (103.74)	116.30 (116.98)
<b>E<sub>2</sub><sup>t</sup> (Msi)</b>			9.55 (9.60)			9.57 (9.62)						9.13 (9.18)
<b>F<sub>1</sub><sup>cu</sup> (ksi)</b>	102.00 (102.63)	100.73 (101.14)	112.76 (112.92)	98.15 (98.68)	96.87 (97.17)	109.03 (109.07)	75.27 (76.07)	74.03 (74.61)	85.77 (86.11)	44.81 (45.74)	43.54 (44.25)	55.57 (56.03)
<b>E<sub>1</sub><sup>c</sup> (Msi)</b>			9.15 (9.18)			8.87 (8.88)			8.85 (8.87)			8.79 (8.83)
<b>F<sub>2</sub><sup>cu</sup> (ksi)</b>	100.94 (100.37)	99.25 (99.32)	113.39 (112.18)	95.00 (94.70)	93.31 (93.65)	107.44 (106.50)	69.93 (70.38)	NA (69.35)	82.85 (81.98)	43.07 (26.05)	NA	52.96 (52.63)
<b>E<sub>2</sub><sup>c</sup> (Msi)</b>			8.78 (8.69)			8.85 (8.77)			8.68 (8.56)			8.30 (8.29)
<b>F<sub>12</sub><sup>s0.2%</sup> (ksi)</b>	10.36	9.83	10.87	7.49	7.34	8.37				1.60	1.77	2.01
<b>F<sub>12</sub><sup>s5%</sup> (ksi)</b>										3.91	3.71	4.23
<b>F<sub>12</sub><sup>s max</sup> (ksi)</b>	11.86	13.23	14.91									
<b>G<sub>12</sub><sup>s</sup> (Msi)</b>			0.80			0.71						0.20
<b>SBS (ksi)</b>	9.67	9.49	10.99	9.55	10.18	11.53	6.08	6.14	6.93	3.86	3.60	4.07

Note (1): Users of ETW condition data are cautioned of the fact that ETW test temperature of 350°F is not 50°F (28°C) or more below the wet glass transition temperature as is recommended. They are advised to refer to CMH-17 Rev G section 2.2.8 and DOT/FAA/AR-01/40 for more information about establishing MOL.

Table 3-3: Summary of Test Results for Lamina Data

<b>Prepreg Material:</b>	Cytec Cycom® 5250-5 T650 6K-135-5HS fabric NMS 226/2 Material Specification	<b>Cytec Cycom® 5250-5 T650 6K-135-5HS Laminate Properties Summary</b>
<b>Fabric:</b>	T650 6K-135-5HS weave <b>Resin:</b> Cytec Cycom® 5250-5	
<b>Tg(dry):</b> 466.88 °F <b>Tg(bone dry):</b> 522.83 °F <b>Tg(wet):</b> 378.38 °F		<b>Tg METHOD:</b> DMA (SRM 18-94)
<b>PROCESSING:</b>	NPS 81226 Process Specification "C" Cure Cycle	

<b>Date of fiber manufacture</b>	8/16/2006	<b>Date of testing</b>	10/9/2008-8/11/2010
<b>Date of resin manufacture</b>	7/9/2007-7/11/2007	<b>Date of data submittal</b>	November 2010
<b>Date of prepreg manufacture</b>	7/9/2007-7/11/2007	<b>Date of analysis</b>	6/1/2011-5/30/2012
<b>Date of composite manufacture</b>	3/31/2008		

<b>LAMINATE MECHANICAL PROPERTY B-BASIS SUMMARY</b>													
Data reported as normalized used a normalizing t <sub>ply</sub> of 0.0152 in													
Values shown in shaded boxes do not meet CMH17 Rev G requirements and are estimates only													
These values may not be used for certification unless specifically allowed by the certifying agency													
Test	Property	Layup:			Quasi Isotropic 25/50/25			"Soft" 10/80/10			"Hard" 40/20/40		
		Test Condition	Unit	B-value	Mod. CV B-value	Mean	B-value	Mod. CV B-value	Mean	B-value	Mod. CV B-value	Mean	
OHT (normalized)	Strength	CTD	ksi	45.46	43.00	48.43	35.60	35.43	40.13	53.64	51.86	58.84	
		RTD	ksi	47.77	45.30	50.74	38.07	34.97	39.60	56.71	54.95	61.89	
		ETW <sup>(1)</sup>	ksi	51.59	49.15	54.53	18.91	22.19	28.23	57.63	63.19	70.16	
OHC (normalized)	Strength	RTD	ksi	44.79	41.22	46.54	35.08	34.00	37.37	46.03	44.79	49.58	
		ETW <sup>(1)</sup>	ksi	18.33	23.87	27.58	18.44	19.40	22.77	28.54	27.30	32.09	
UNT (normalized)	Strength	CTD	ksi	67.60	74.97	83.91	52.41	50.21	55.60	92.86	89.74	101.26	
			Msi	---	---	6.95	---	---	4.70	---	---	8.68	
	Modulus	RTD	ksi	80.64	77.00	85.99	51.27	49.09	54.43	99.08	95.97	107.44	
			Msi	---	---	6.95	---	---	4.75	---	---	8.72	
Strength	ETW <sup>(1)</sup>	ksi	69.96	69.00	77.98	26.02	33.00	38.39	92.23	89.12	100.59		
		Msi	---	---	6.20	---	---	3.35	---	---	8.28		
UNC (normalized)	Strength	RTD	ksi	76.65	75.53	88.16	53.23	52.35	58.07	64.37	75.53	85.91	
			Msi	---	---	6.32	---	---	4.23	---	---	7.86	
	Modulus	ETW <sup>(1)</sup>	ksi	34.34	34.23	40.27	21.10	20.23	25.95	28.35	40.46	47.29	
			Msi	---	---	5.67	---	---	3.32	---	---	7.61	
SBS1 (as measured)	Strength	RTD	ksi	9.35	9.11	10.49	---	---	---	---	---	---	
		ETW <sup>(1)</sup>	ksi	2.09	4.24	5.08	---	---	---	---	---	---	
FHT (normalized)	Strength	CTD	ksi	50.36	48.09	53.78	44.14	41.51	45.79	55.44	53.61	60.18	
		RTD	ksi	51.74	49.47	55.15	43.18	40.55	44.82	48.17	55.31	61.87	
		ETW <sup>(1)</sup>	ksi	48.65	46.40	52.03	27.28	24.65	28.92	57.90	54.88	61.44	
FHC (normalized)	Strength	RTD	ksi	68.88	67.02	77.20	52.84	49.91	56.52	---	---	---	
		ETW <sup>(1)</sup>	ksi	30.78	NA	41.92	11.25	22.27	29.02	34.85	40.73	46.95	
Single Shear Bearing (normalized)	2% Offset Strength	RTD	ksi	76.04	94.01	108.01	101.82	96.45	109.41	92.86	92.25	104.05	
		ETW <sup>(1)</sup>	ksi	62.69	63.74	77.67	61.95	61.95	75.47	55.58	54.97	66.67	
	Ultimate Strength	ETW <sup>(1)</sup>	ksi	78.09	NA	92.83	82.70	81.49	94.71	73.44	71.25	81.48	
CAI (normalized)	Strength	RTD	ksi	---	---	30.83	---	---	---	---	---		
ILT (as measured)	Strength	CTD	ksi	---	---	7.85	---	---	---	---	---	---	
		RTD	ksi	---	---	8.35	---	---	---	---	---	---	
		ETW	ksi	---	---	2.55	---	---	---	---	---	---	
CBS (as measured)	Strength	CTD	lb	---	---	263.73	---	---	---	---	---	---	
		RTD	lb	---	---	287.43	---	---	---	---	---	---	
		ETW	lb	---	---	84.52	---	---	---	---	---	---	

Note (1): Users of ETW condition data are cautioned of the fact that ETW test temperature of 350°F is not 50°F (28°C) or more below the wet glass transition temperature as is recommended. They are advised to refer to CMH-17 Rev G section 2.2.8 and DOT/FAA/AR-01/40 for more information about establishing MOL.

Table 3-4: Summary of Test Results for Laminate Data

Note: There were no usable values from the FHC3 RTD tests due bad failure modes occurring for all specimens.

#### 4. Individual Test Summaries, Statistics, Basis Values and Graphs

Test data for fiber dominated properties was normalized according to nominal cured ply thickness. Both normalized and as-measured statistics were included in the tables, but only the normalized data values were graphed. Test failures, outliers and explanations regarding computational choices were noted in the accompanying text for each test.

For organic matrix composites, the typical rule of thumb is to maintain a 50 degree margin between the materials maximum operating limit (MOL) and the wet glass transition temperature. Users of ETW condition data are cautioned of the fact that ETW test temperature of 350°F is not 50°F (28°C) or more below the wet glass transition temperature as is recommended. They are advised to refer to CMH-17 Rev G section 2.2.8 and DOT/FAA/AR-01/40 for more information about establishing MOL.

All individual specimen results are graphed for each test by batch and environmental condition with a line indicating the recommended basis values for each environmental condition. The data is jittered (moved slightly to the left or right) in order for all specimen values to be clearly visible. The strength values are always graphed on the vertical axis with the scale adjusted to include all data values and their corresponding basis values. The vertical axis may not include zero. The horizontal axis values will vary depending on the data and how much overlapping of there was of the data within and between batches. When there was little variation, the batches were graphed from left to right and the environmental conditions were identified by the shape and color of the symbol used to plot the data. Otherwise, the environmental conditions were graphed from left to right and the batches were identified by the shape and color of the symbol.

When a dataset fails the Anderson-Darling k sample (ADK) test for batch-to-batch variation an ANOVA analysis is required. In order for B-basis values computed using the ANOVA method, data from five batches is required. Since this qualification dataset has only three batches, the basis values computed using ANOVA are considered estimates only. However, the basis values resulting from the ANOVA method using only three batches may be overly conservative. The ADK test is performed again after a transformation of the data according to the assumptions of the modified CV method (see section 2.1.4 for details). If the dataset still passes the ADK test at this point, modified CV basis values are provided. If the dataset does not pass the ADK test after the transformation, estimates may be computed using the modified CV method per the guidelines of CMH17 Rev G section 8.3.10.

### 4.1 Warp (0°) Tension Properties (WT)

The Warp Tension data was normalized so both normalized and as-measured statistics are provided. There were no test failures in the normalized data so pooling across environments was acceptable and basis values computed by pooling were provided.

The as-measured RTD data failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate.

When the RTD data was transformed according to the assumptions of the modified CV method, it did pass the ADK test and so the modified CV B-basis value is provided. The pooled dataset did not pass Levene’s test for equality of variation, so pooling across environments remained unacceptable for the as-measured data.

There was one outlier. It was an outlier in both the normalized and the as-measured datasets. The outlier was from batch 3. It was the lowest value in the CTD dataset. It was an outlier for the CTD condition, but not for batch 3. It was retained for this analysis.

Statistics, estimates and basis values are given for strength data in Table 4-1 and for the modulus data in Table 4-2. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-1.

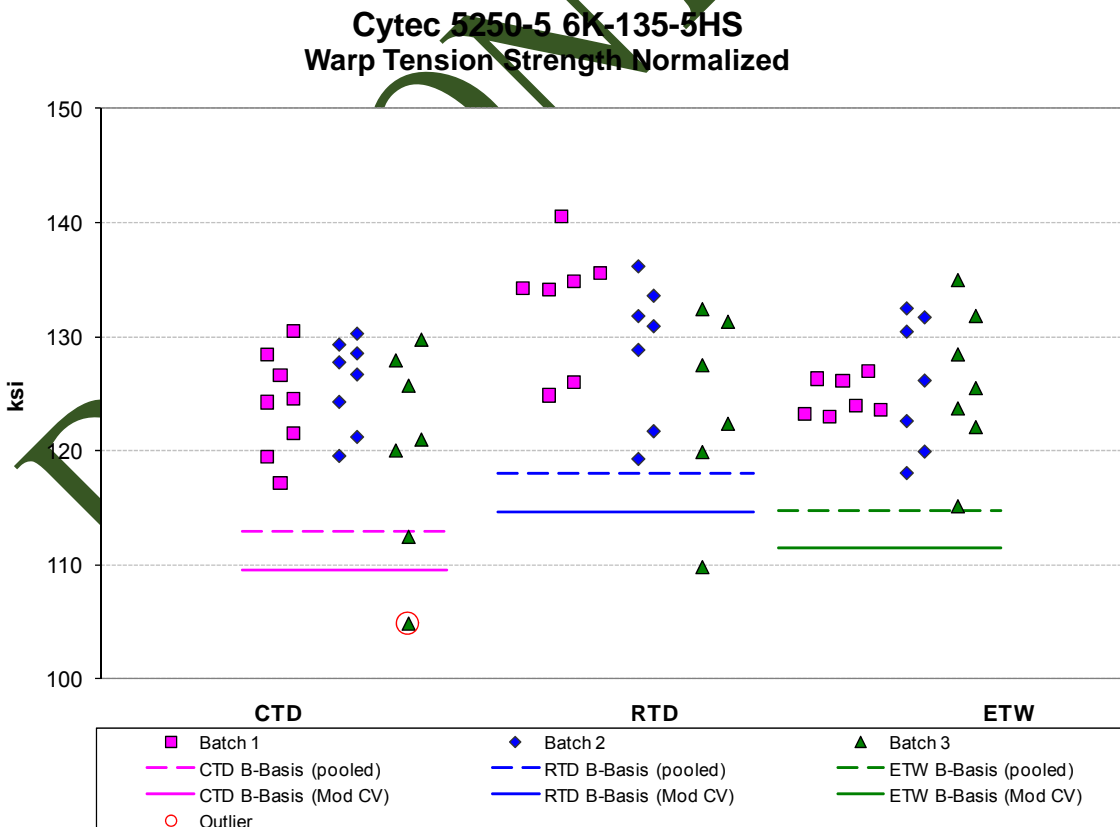


Figure 4-1 Batch plot for WT normalized strength

Warp Tension Strength Basis Values and Statistics						
Env	Normalized			As Measured		
	CTD	RTD	ETW	CTD	RTD	ETW
Mean	123.56	128.78	125.53	122.35	128.61	124.94
Stdev	6.20	7.37	4.92	6.28	7.97	4.72
CV	5.02	5.73	3.92	5.13	6.19	3.77
Mod CV	6.51	6.86	6.00	6.57	7.10	6.00
Min	104.89	109.83	115.15	103.78	108.81	113.33
Max	130.47	140.59	134.92	130.88	142.52	133.51
No. Batches	3	3	3	3	3	3
No. Spec.	23	20	21	23	20	21
Basis Values and/or Estimates						
B-basis Value	112.89	117.98	114.78	110.62	115.96	115.96
B-Estimate					94.28	
A-Estimate	105.61	110.73	107.52	102.22	69.78	109.55
Method	pooled	pooled	pooled	Normal	ANOVA	Normal
Modified CV Basis Values and/or Estimates						
B-basis Value	109.61	114.66	111.47	107.33	111.03	110.66
A-Estimate	100.10	105.17	101.98	96.59	98.53	100.48
Method	pooled	pooled	pooled	Normal	Normal	Normal

Table 4-1: Statistics and Basis values for WT Strength Data

Warp Tension Modulus Statistics						
Env	Normalized			As Measured		
	CTD	RTD	ETW	CTD	RTD	ETW
Mean	9.86	9.82	9.22	9.75	9.81	9.18
Stdev	0.30	0.07	0.55	0.29	0.14	0.63
CV	3.09	0.70	6.01	3.02	1.45	6.83
Mod CV	6.00	6.00	7.00	6.00	6.00	7.42
Min	9.61	9.70	8.19	9.49	9.56	7.97
Max	10.90	9.92	10.45	10.77	10.10	10.55
No. Batches	3	3	3	3	3	3
No. Spec.	22	20	21	22	20	21

Table 4-2: Statistics from WT Modulus Data

### 4.2 Fill (90°) Tension Properties (FT)

The Fill Tension data was normalized so both normalized and as-measured statistics are provided. There were no test failures in the normalized data so pooling across environments was acceptable and basis values computed by pooling were provided. There were no outliers.

Statistics, estimates and basis values are given for the FT strength data in Table 4-3 and for the FT modulus data in Table 4-4. The normalized data, B-estimates and the B-basis values are shown graphically in Figure 4-2.

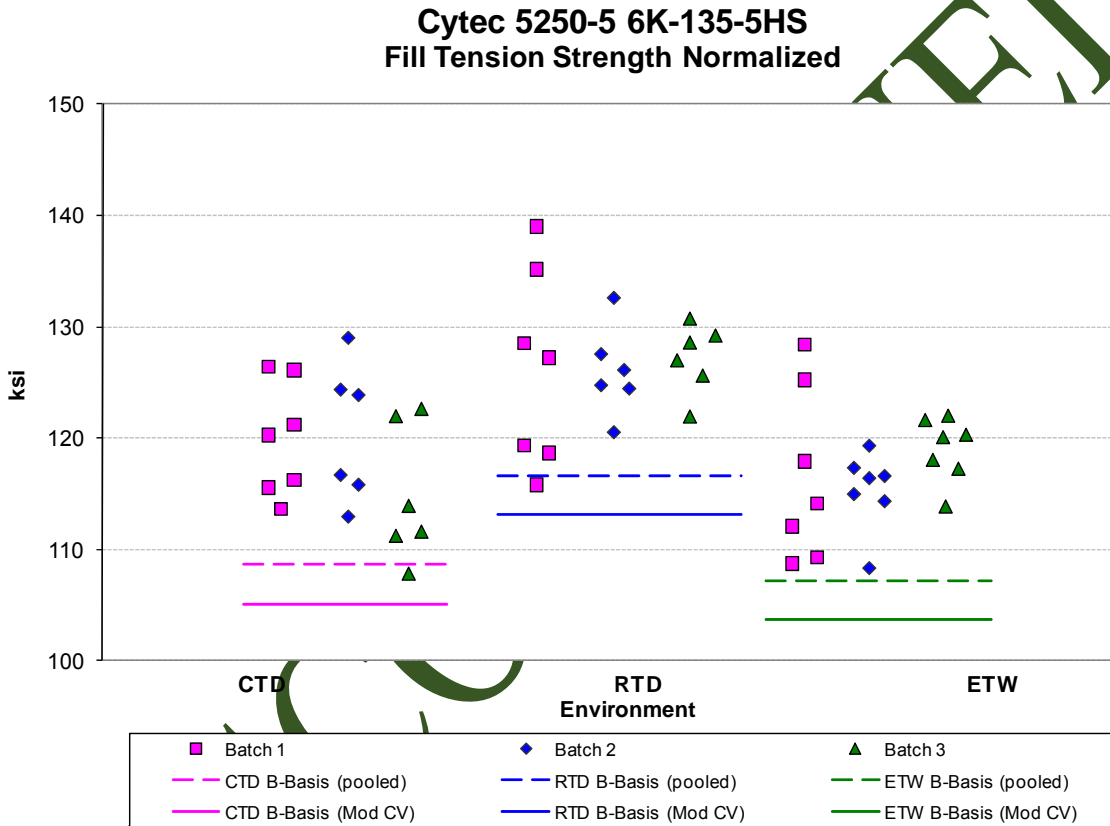


Figure 4-2: Batch Plot for FT normalized strength



Fill Tension Strength Basis Values and Statistics						
Env	Normalized			As Measured		
	CTD	RTD	ETW	CTD	RTD	ETW
Mean	118.51	126.47	116.98	117.88	125.92	116.30
Stdev	5.99	5.75	5.14	6.82	5.96	5.14
CV	5.05	4.55	4.40	5.78	4.73	4.42
Mod CV	6.53	6.27	6.20	6.89	6.37	6.21
Min	107.90	115.82	108.32	106.21	116.01	107.69
Max	129.01	139.02	128.38	130.23	139.54	128.93
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	21	19	19	21
Basis Values and Estimates						
B-basis Value	108.66	116.62	107.23	107.40	115.44	105.92
A-Estimate	102.07	110.03	100.62	100.39	108.42	98.69
Method	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and/or Estimates						
B-basis Value	105.14	113.10	103.74	104.26	112.29	102.81
A-Estimate	96.19	104.15	94.77	95.14	103.17	93.66
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-3: Statistics and Basis Values for FT Strength Data

Fill Tension Modulus Statistics						
Env	Normalized			As Measured		
	CTD	RTD	ETW	CTD	RTD	ETW
Mean	9.60	9.62	9.18	9.55	9.57	9.13
Stdev	0.20	0.09	0.32	0.18	0.12	0.33
CV	2.07	0.89	3.51	1.90	1.30	3.58
Mod CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	9.31	9.44	8.55	9.35	9.32	8.55
Max	10.01	9.74	9.87	10.00	9.76	9.93
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	21	19	19	21


Table 4-4: Statistics from FT Modulus Data

### 4.3 Warp (0°) Compression Properties (WC)

The Warp Compression data is normalized so both normalized and as-measured statistics are provided. There were no test failures in either the normalized or as-measured data so pooling across environments was acceptable and pooled B-basis values are provided.

There was one outlier. It was an outlier in both the normalized and the as-measured datasets. The outlier was the highest value in batch one for the ETW condition. It was an outlier for batch one, but not for the ETW condition. It was retained for this analysis.

Statistics, basis values and estimates are given for strength data in Table 4-5 and for the modulus data in Table 4-6. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-3.

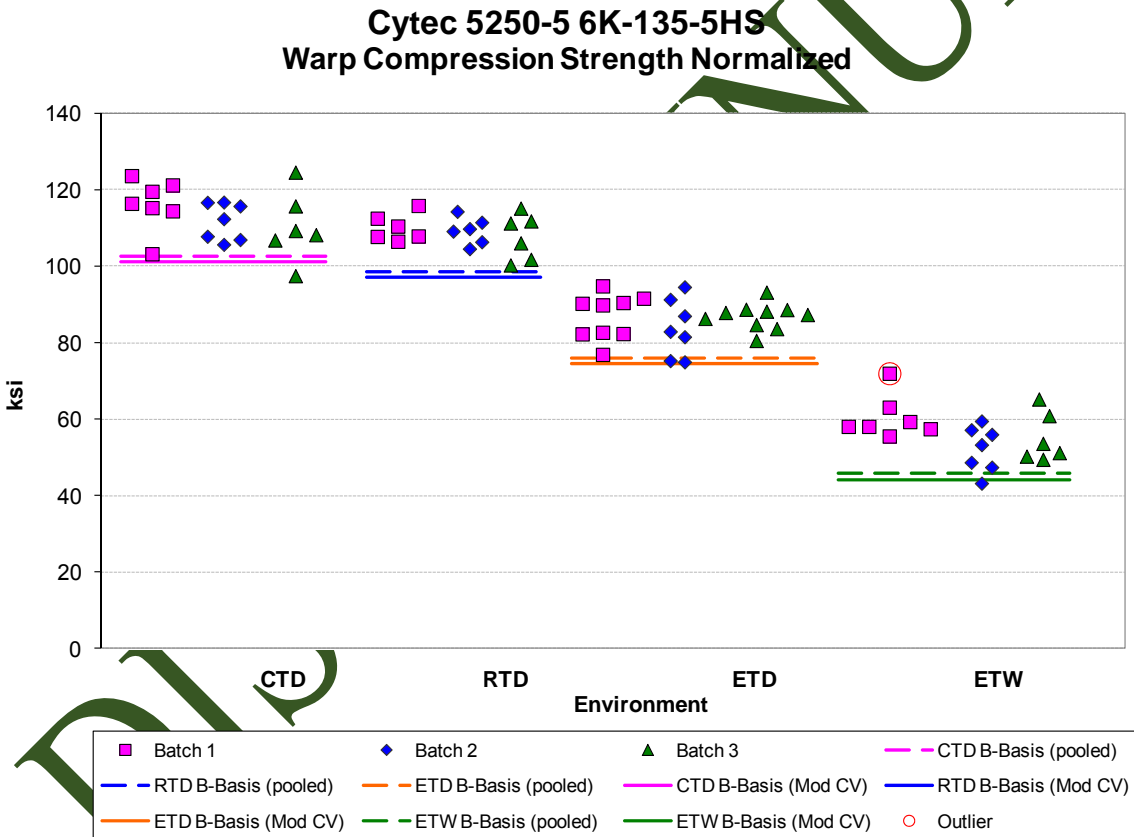

Warp Compression Strength Basis Values and Statistics								
Normalized					As Measured			
Env	CTD	RTD	ETD	ETW	CTD	RTD	ETD	ETW
Mean	112.92	109.07	86.11	56.03	112.76	109.03	85.77	55.57
Stdev	7.06	4.33	5.53	6.69	7.46	4.96	5.66	6.78
CV	6.25	3.97	6.42	11.94	6.62	4.55	6.60	12.19
Mod CV	7.12	6.00	7.21	11.94	7.31	6.27	7.30	12.19
Min	97.53	100.31	74.99	43.28	94.68	96.89	75.48	42.99
Max	124.58	115.87	94.84	72.01	122.58	116.25	94.85	71.56
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	20	18	26	20	20	18	26	20
Basis Values and/or Estimates								
B-basis Value	102.63	98.68	76.07	45.74	102.00	98.15	75.27	44.81
A-Estimate	95.80	91.86	69.19	38.90	94.85	91.02	68.08	37.67
Method	pooled	pooled	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and/or Estimates								
B-basis Value	101.14	97.17	74.61	44.25	100.73	96.87	74.03	43.54
A-Estimate	93.32	89.37	66.75	36.43	92.73	88.89	65.99	35.55
Method	pooled	pooled	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-5: Statistics and Basis Values for WC Strength Data

Warp Compression Modulus Statistics								
Normalized					As Measured			
Env	CTD	RTD	ETD	ETW	CTD	RTD	ETD	ETW
Mean	9.18	8.88	8.87	8.83	9.15	8.87	8.85	8.79
Stdev	0.28	0.21	0.22	0.45	0.31	0.26	0.25	0.49
CV	3.04	2.39	2.51	5.15	3.37	2.94	2.82	5.58
Mod CV	6.00	6.00	6.00	6.57	6.00	6.00	6.00	6.79
Min	8.67	8.48	8.34	8.14	8.54	8.47	8.20	7.88
Max	9.86	9.29	9.22	9.56	9.88	9.32	9.25	9.65
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	21	19	19	18	21	19	19	18

Table 4-6: Statistics from WC Modulus Data

DISCO

### 4.4 Fill (90°) Compression Properties (FC)

The Fill Compression data was normalized so both normalized and as-measured statistics are provided. The normalized ETW data failed both the normality test and the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. The ETW dataset failed the normality test and the ADK test even after transforming the data for the modified. Since the ETW data had a CV greater than 8%, the modified CV method could not be used. An override of the ADK result for the ETW datasets is recommended and is permissible in this case according to the guidelines given in section 8.3.10.1 of CMH-17 Rev G with situation 1 being applicable to this dataset. Estimates of the basis values are provided for the normalized ETW dataset using the Weibull distribution.

The as-measured ETW dataset failed the normality test but not the ADK test, so a B-basis value based on the Weibull distribution was computed. The pooled dataset failed the normality test so pooling across all environments was not acceptable. However, the CTD and RTD conditions could be pooled together and the basis values for those two environments were computed by pooling. The as-measured ETD and ETW datasets had a CV greater than 8%, so no modified CV basis values are provided as that method would not alter the results which are presented.

There were no outliers in either the normalized or the as-measured datasets. Statistics, basis values and estimates are given for strength data in Table 4-7 and for the modulus data in Table 4-8. The normalized data and B-basis values are shown graphically in Figure 4-4.

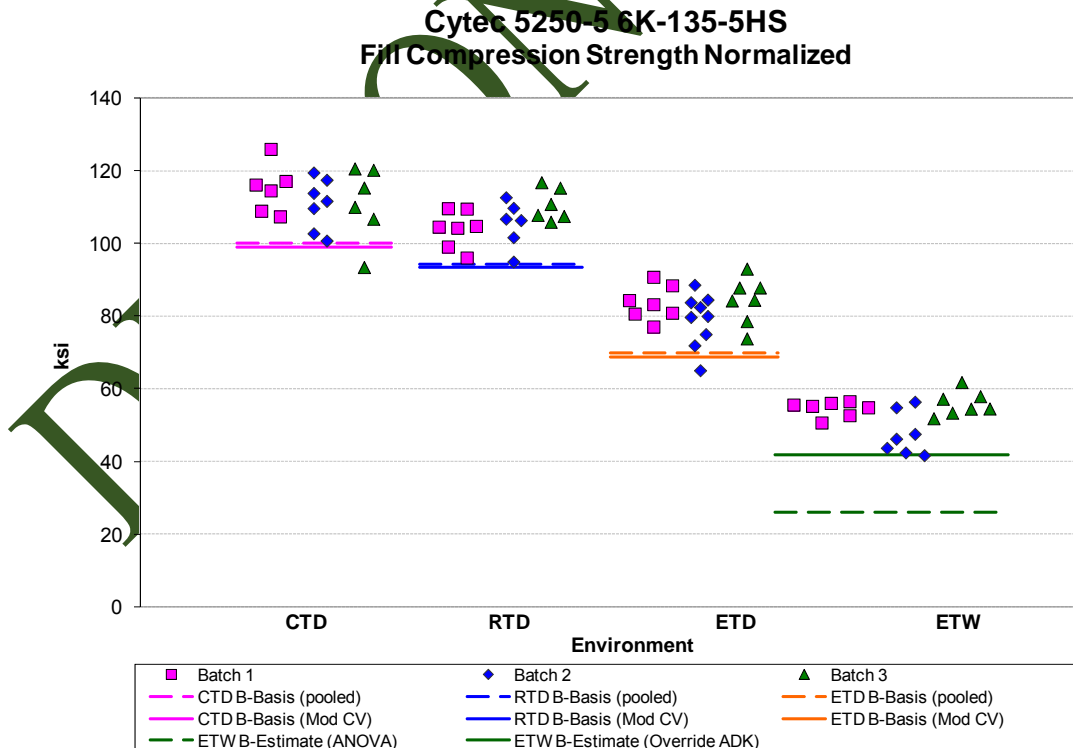


Figure 4-4: Batch Plot for FC normalized strength

Fill Compression Strength Basis Values and Statistics								
Normalized					As Measured			
Env	CTD	RTD	ETD	ETW	CTD	RTD	ETD	ETW
Mean	112.18	106.50	81.98	52.63	113.39	107.44	82.85	52.96
Stdev	7.85	5.79	6.51	5.40	8.19	5.30	6.92	4.97
CV	7.00	5.44	7.94	10.25	7.23	4.93	8.35	9.38
Mod CV	7.50	6.72	7.97	10.25	7.61	6.47	8.35	9.38
Min	93.43	94.92	65.03	41.66	93.15	96.28	65.21	42.76
Max	125.92	116.76	92.99	61.78	128.74	114.38	92.67	61.05
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	19	19	23	21	19	19	23	21
Basis Values and/or Estimates								
B-basis Value	100.37	94.70	70.38		100.94	95.00	69.93	43.07
B-Estimate				26.05				
A-Estimate	92.48	86.81	62.45	7.08	92.43	86.49	60.68	33.95
Method	pooled	pooled	pooled	ANOVA	pooled	pooled	Normal	Weibull
Modified CV Basis Values and/or Estimates								
B-basis Value	99.32	93.65	69.35		99.25	93.31		
A-Estimate	90.73	85.06	60.71		89.60	83.65		
Method	pooled	pooled	pooled		pooled	pooled		
Basis Values and Estimates with override of ADK test result								
B-Estimate				41.93				
A-Estimate				32.31				
Method				Weibull				

Table 4-7: Statistics and Basis Values for FC Strength Data

Fill Compression Modulus Statistics								
Normalized					As Measured			
Env	CTD	RTD	ETD	ETW	CTD	RTD	ETD	ETW
Mean	8.69	8.77	8.56	8.29	8.78	8.85	8.68	8.30
Stdev	0.33	0.23	0.19	0.29	0.36	0.31	0.22	0.28
CV	3.79	2.66	2.20	3.52	4.08	3.50	2.53	3.39
Mod CV	6.00	6.00	6.00	6.00	6.04	6.00	6.00	6.00
Min	7.97	8.31	8.24	7.70	8.03	8.25	8.35	7.73
Max	9.27	9.04	8.85	8.88	9.33	9.37	9.13	8.95
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	21	19	19	21	21	19	19	21

Table 4-8: Statistics from FC Modulus Data

### 4.5 Short Beam Strength (SBS) Data

The Short Beam Strength data is not normalized. The RTD and ETD datasets both failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, these values are considered estimates. Both datasets passed the ADK test after applying the transformation to meet the assumptions of the modified CV method. Pooling across environments was not acceptable due to the failure of Levene’s test.

There was one outlier. It was the highest value in batch three of the CTD dataset. It was an outlier only for batch three and not for the CTD condition. It was retained for this analysis.

Statistics, basis values and estimates are given for SBS strength data in Table 4-9. The data, B-estimates and B-basis values are shown graphically in Figure 4-5.

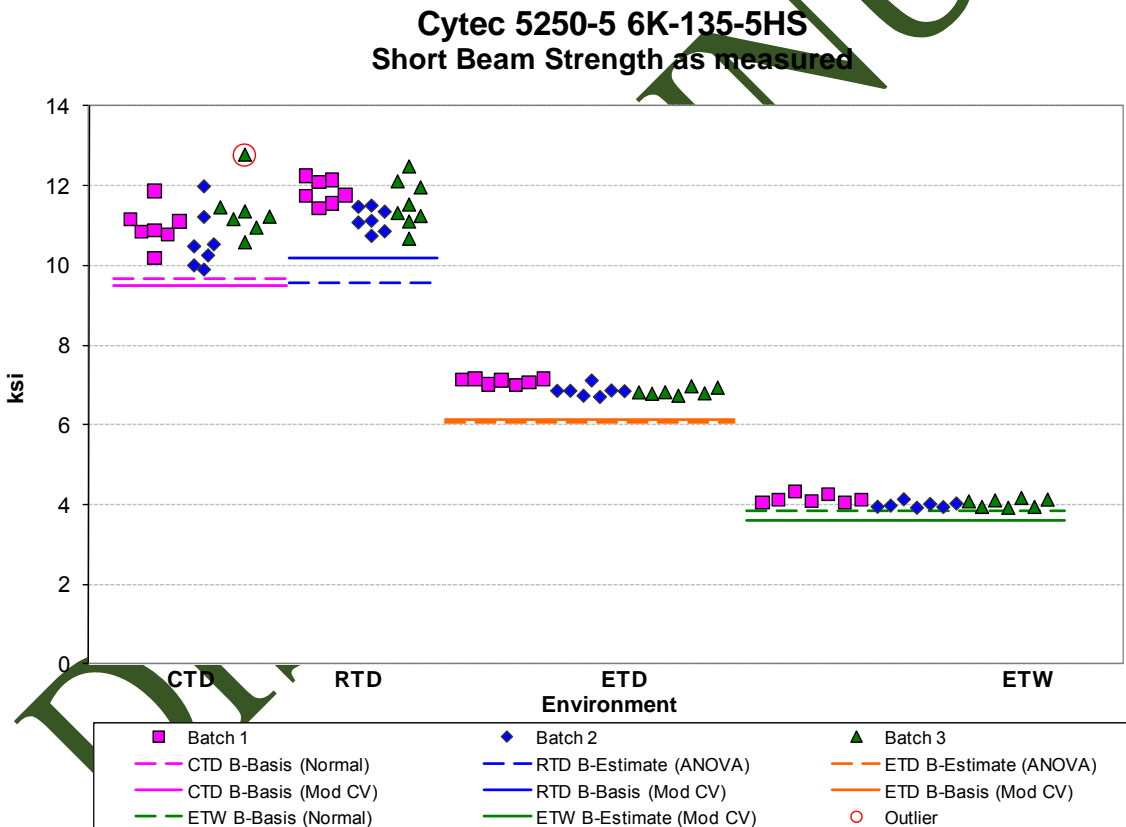


Figure 4-5: Batch plot for SBS strength as-measured

<b>Short Beam Strength (SBS) as measured</b>				
Env	CTD	RTD	ETD	ETW
Mean	10.99	11.53	6.93	4.07
Stdev	0.69	0.50	0.15	0.11
CV	6.28	4.34	2.18	2.69
Mod CV	7.14	6.17	6.00	6.00
Min	9.90	10.67	6.71	3.93
Max	12.77	12.48	7.16	4.32
No. Batches	3	3	3	3
No. Spec.	21	22	21	21
<b>Basis Values and Estimates</b>				
B-basis Value	9.67			3.86
B-Estimate		9.55	6.08	
A-Estimate	8.73	8.15	5.47	3.71
Method	Normal	ANOVA	ANOVA	Normal
<b>Modified CV Basis Values and Estimates</b>				
B-basis Value	9.49	10.18	6.14	3.60
A-Estimate	8.43	9.23	5.58	3.27
Method	Normal	Normal	Normal	Normal

Table 4-9: Statistics and Basis Values for SBS Strength Data

DISCONTINUED

## 4.6 In-Plane Shear Properties (IPS)

The In-Plane Shear data is not normalized. The strength at 5% strain data was available only for the ETW condition and had insufficient data to generate a B-basis value meeting CMH17 Ref G requirements. The peak strength before 5% strain data was available only for the CTD condition. Maximum shear strength data was not available.


The CTD peak strength before 5% strain and the RTD and ETW datasets for the 0.2% offset strength failed the Anderson Darling k-sample test (ADK test) for batch to batch variability, which means that pooling across environments was not acceptable and CMH 17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, these values are considered estimates. All three of these datasets passed the ADK test after applying the transformation to meet the assumptions of the modified CV method, so modified CV B-basis values are provided. Pooling was not acceptable for all three conditions of the 0.2% offset strength data due to the failure of Levene's test but the CTD and RTD conditions could be pooled when computing the modified CV basis values.

There were two outliers in the 0.2% offset strength data. The lowest value in batch one of the CTD dataset and the highest value in batch one of the RTD dataset were both flagged as outliers for their respective batches and not for their respective conditions. There was one outlier in the peak strength before 5% strain dataset. It was the lowest value in batch two of the CTD condition. It was an outlier for batch two but not for the CTD condition. All three outliers were retained for this analysis.

Statistics, basis values and estimates are given for the strength data in Table 4-10. Modulus statistics are shown in Table 4-11. The data, B-basis values and B-estimates are shown graphically for Figure 4-6.



**Cytec 5250-5 6K-135-5HS  
In-Plane Shear Strength as measured**

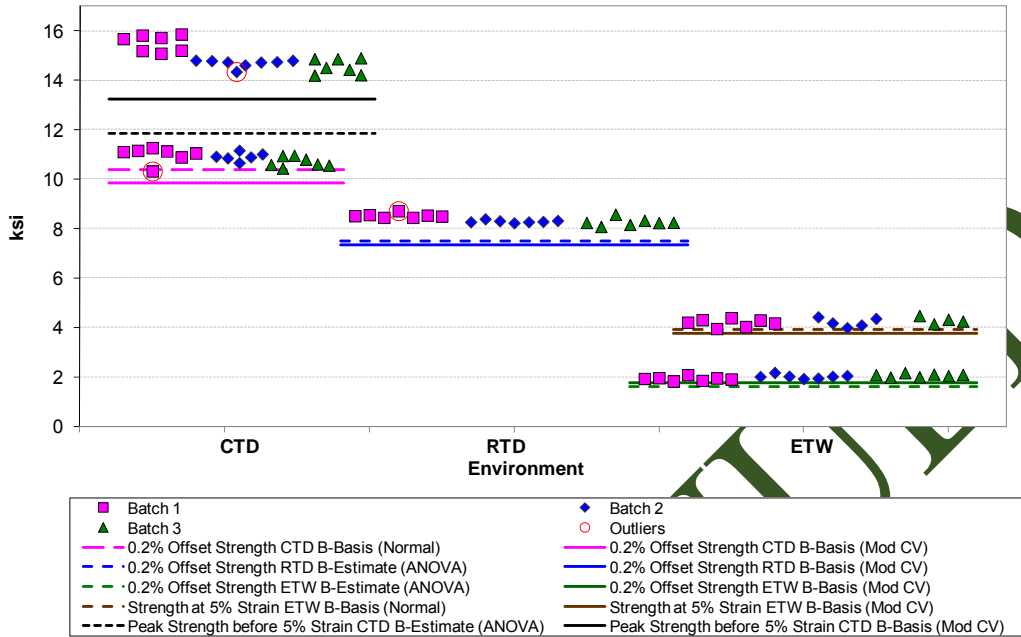

**Figure 4-6: Batch plot for IPS strength as-measured**

In-Plane Shear Strength Basis Values and Statistics					
Env	0.2% Offset			5% Strain	Peak before 5% Strain
	CTD	RTD	ETW	ETW	CTD
Mean	10.87	8.37	2.01	4.23	14.91
Stdev	0.26	0.16	0.09	0.16	0.49
CV	2.40	1.90	4.65	3.71	3.29
Mod CV	6.00	6.00	6.32	6.00	6.00
Min	10.32	8.08	1.83	3.95	14.20
Max	11.27	8.72	2.18	4.48	15.86
No. Batches	3	3	3	3	3
No. Spec	20	21	21	16	22
Basis Values and Estimates					
B-basis Value	10.36				
B-Estimate		7.49	1.60	3.91	11.86
A-Estimate	10.01	6.87	1.30	3.68	9.69
Method	Normal	ANOVA	ANOVA	Normal	ANOVA
Modified CV Basis Values and Estimates					
B-basis Value	9.83	7.34	1.77		13.23
B-Estimate				3.71	
A-Estimate	9.12	6.63	1.60	3.35	12.02
Method	pooled	pooled	Normal	Normal	Normal

**Table 4-10: Statistics and Basis Values for IPS Strength Data**

<b>In-Plane Shear Modulus Statistics</b>			
<b>Env</b>	<b>CTD</b>	<b>RTD</b>	<b>ETW</b>
<b>Mean</b>	<b>0.80</b>	<b>0.71</b>	<b>0.20</b>
<b>Stdev</b>	<b>0.02</b>	<b>0.01</b>	<b>0.01</b>
<b>CV</b>	<b>2.85</b>	<b>2.01</b>	<b>4.94</b>
<b>Modified CV</b>	<b>6.00</b>	<b>6.00</b>	<b>6.47</b>
<b>Min</b>	<b>0.76</b>	<b>0.69</b>	<b>0.18</b>
<b>Max</b>	<b>0.87</b>	<b>0.73</b>	<b>0.22</b>
<b>No. Batches</b>	<b>3</b>	<b>3</b>	<b>3</b>
<b>No. Spec.</b>	<b>20</b>	<b>21</b>	<b>21</b>

Table 4-11: Statistics and Basis Values for IPS Modulus Data

DISCONTINUED

### 4.7 Quasi Isotropic Unnotched Tension Properties (UNT1)

The UNT1 data was normalized so both normalized and as-measured statistics are provided. The as-measured CTD and RTD datasets both fail the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. The RTD dataset passed the ADK test after applying the transformation to meet the assumptions of the modified CV method and modified CV basis values are provided. A B-estimate computed was for the CTD dataset using the modified CV method, but it is considered an estimate since the CTD dataset failed the the ADK test even after transforming the data for the modified CV method. Pooling of the RTD and ETW datasets for the modified CV basis value computations was not acceptable due to the non-normality of the pooled dataset.

The normalized CTD data failed the ADK test but passed after mod CV transform. A B-estimate was computed using the ANOVA method and a B-basis value was computed using the modified CV method. The normalized RTD and ETW datasets could not be pooled due to a failure of Levene's test, but pooling was acceptable after transforming all three normalized datasets to meet the assumptions of the modified CV method.

There were no outliers. Statistics, basis values and estimates are given for UNT1 strength data in Table 4-12 and for the modulus data in Table 4-13. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-7.

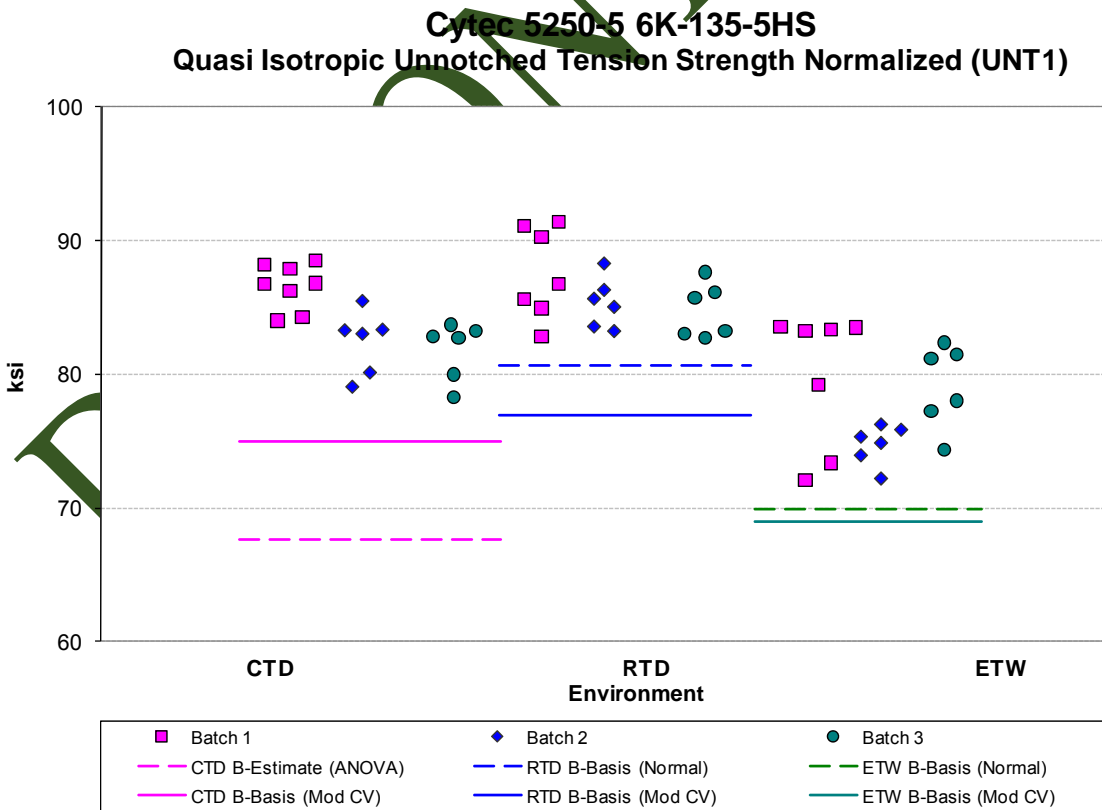


Figure 4-7: Batch Plot for UNT1 normalized strength

Unnotched Tension (UNT1) Strength Basis Values and Statistics						
	Normalized			As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	83.91	85.99	77.98	83.85	85.68	78.09
Stdev	2.99	2.74	4.12	3.71	3.22	3.97
CV	3.56	3.19	5.28	4.43	3.76	5.08
Modified CV	6.00	6.00	6.64	6.21	6.00	6.54
Min	78.31	82.75	72.09	76.91	80.65	71.72
Max	88.53	91.44	83.58	89.83	90.55	85.13
No. Batches	3	3	3	3	3	3
No. Spec.	20	19	19	20	19	19
Basis Values and Estimates						
B-basis Value		80.64	69.96			70.35
B-Estimate	67.60			60.43	70.89	
A-Estimate	55.96	76.85	64.27	43.71	60.34	64.86
Method	ANOVA	Normal	Normal	ANOVA	ANOVA	Normal
Modified CV Basis Values and Estimates						
B-basis Value	74.97	77.00	69.00		75.66	68.13
B-Estimate				73.81		
A-Estimate	68.95	70.99	62.99	66.68	68.56	61.07
Method	pooled	pooled	pooled	Normal	Normal	Normal

Table 4-12: Statistics and Basis Values for UNT1 Strength Data

Unnotched Tension (UNT1) Modulus Statistics						
	Normalized			As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	6.95	6.95	6.20	6.94	6.93	6.21
Stdev	0.20	0.12	0.09	0.25	0.18	0.14
CV	2.86	1.79	1.41	3.53	2.62	2.17
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	6.70	6.77	6.02	6.60	6.64	5.98
Max	7.65	7.17	6.36	7.68	7.29	6.53
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	19	19	19	19

Table 4-13: Statistics from UNT1 Modulus Data

### 4.8 "Soft" Unnotched Tension Properties (UNT2)

The UNT2 data was normalized so both normalized and as-measured statistics are provided. The as-measured data from each of the three conditions tested, CTD, RTD and ETW, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. The CTD and RTD datasets passed the ADK test after applying the transformation to meet the assumptions of the modified CV method and modified CV basis values are provided. A B-estimate computed was for the ETW dataset using the modified CV method, but it is considered an estimate since the ETW dataset failed the ADK test even after transforming the data for the modified CV method. Pooling of the CTD and RTD datasets for the modified CV basis value computations was acceptable and the modified CV basis values provided were computed after pooling the data from those two environments.

For the normalized data, only the data from the ETW environment failed the ADK test and required the ANOVA analysis. The ETW dataset passed the ADK test after applying the transformation to meet the assumptions of the modified CV method and modified CV basis values are provided. Pooling was acceptable for the normalized CTD and RTD datasets. For the modified CV basis values, all three environments were pooled together.

There were no outliers. Statistics, basis values and estimates are given for UNT2 strength data in Table 4-14 and for the modulus data in Table 4-15. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-8.

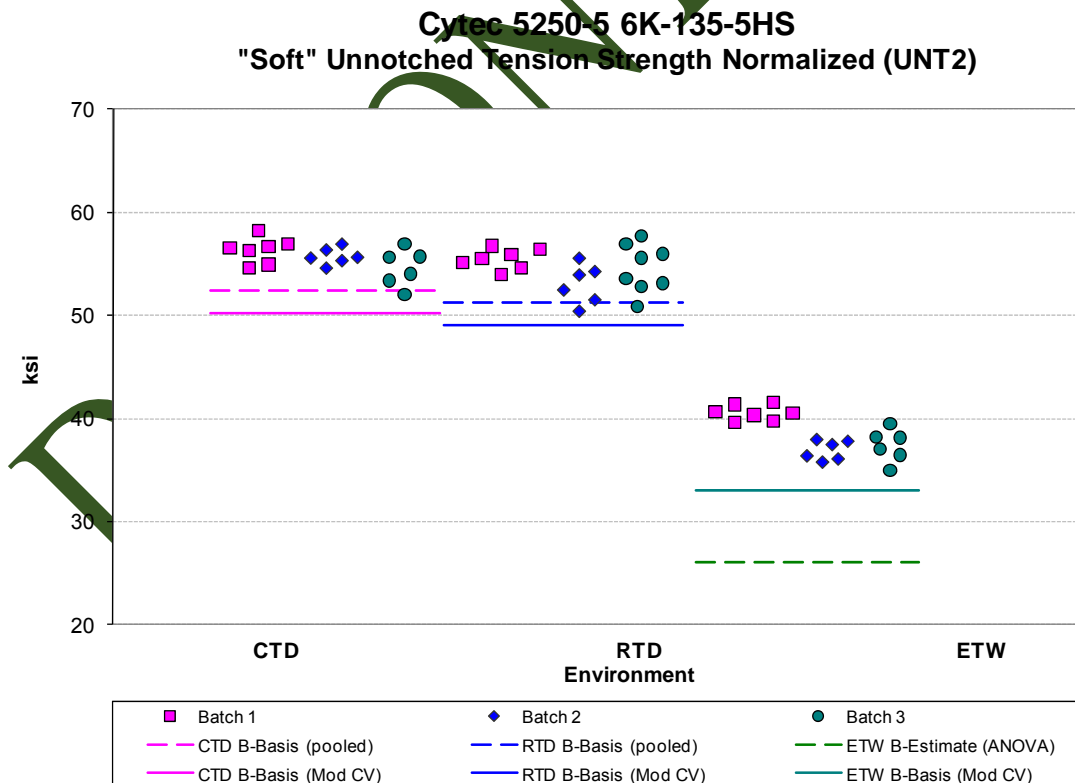


Figure 4-8: Batch Plot for UNT2 normalized strength

Unnotched Tension (UNT2) Strength Basis Values and Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	55.60	54.43	38.39	55.77	54.70	38.57
Stdev	1.45	2.02	2.01	1.76	1.86	2.06
CV	2.60	3.72	5.24	3.16	3.40	5.35
Modified CV	6.00	6.00	6.62	6.00	6.00	6.68
Min	52.05	50.39	34.98	52.44	50.99	35.13
Max	58.23	57.70	41.54	59.04	57.35	41.64
No. Batches	3	3	3	3	3	3
No. Spec.	19	21	19	19	21	19
Basis Values and Estimates						
B-basis Value	52.41	51.27	26.02			25.54
B-Estimate				46.70	46.60	
A-Estimate	50.24	49.10	17.19	40.23	40.82	16.23
Method	pooled	pooled	ANOVA	ANOVA	ANOVA	ANOVA
Modified CV Basis Values and Estimates						
B-basis Value	50.21	49.09	33.00	49.82	48.81	
						33.55
A-Estimate	46.60	45.48	29.39	45.76	44.74	29.99
Method	pooled	pooled	pooled	pooled	pooled	Normal

Table 4-14: Statistics and Basis Values for UNT2 Strength Data

Unnotched Tension (UNT2) Modulus Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	4.70	4.75	3.35	4.71	4.78	3.37
Stdev	0.07	0.27	0.09	0.12	0.27	0.10
CV	1.54	5.59	2.73	2.50	5.61	2.95
Modified CV	6.00	6.80	6.00	6.00	6.80	6.00
Min	4.58	4.42	3.19	4.52	4.47	3.21
Max	4.86	5.66	3.50	5.05	5.70	3.57
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	19	19	19	19

Table 4-15: Statistics from UNT2 Modulus Data

### 4.9 “Hard” Unnotched Tension Properties (UNT3)

The UNT3 data was normalized so both normalized and as-measured statistics are provided. The as-measured data from each of the three conditions tested, CTD, RTD and ETW, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. The CTD and RTD datasets passed the ADK test after applying the transformation to meet the assumptions of the modified CV method and modified CV basis values are provided. A B-estimate computed was for the ETW dataset using the modified CV method, but it is considered an estimate since the ETW dataset failed the ADK test even after transforming the data for the modified CV method. Pooling of the CTD and RTD datasets for the modified CV basis value computations was acceptable and the modified CV basis values provided were computed after pooling the data from those two environments.

The normalized data had no test failures and pooling was acceptable across all three environmental conditions. There was one outlier. It was in the normalized (not as-measured) RTD dataset. In was on the low side of batch one and was an outlier only for batch one and not for the RTD condition.

Statistics, basis values and estimates are given for UNT3 strength data in Table 4-16 and for the modulus data in Table 4-17. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-9.

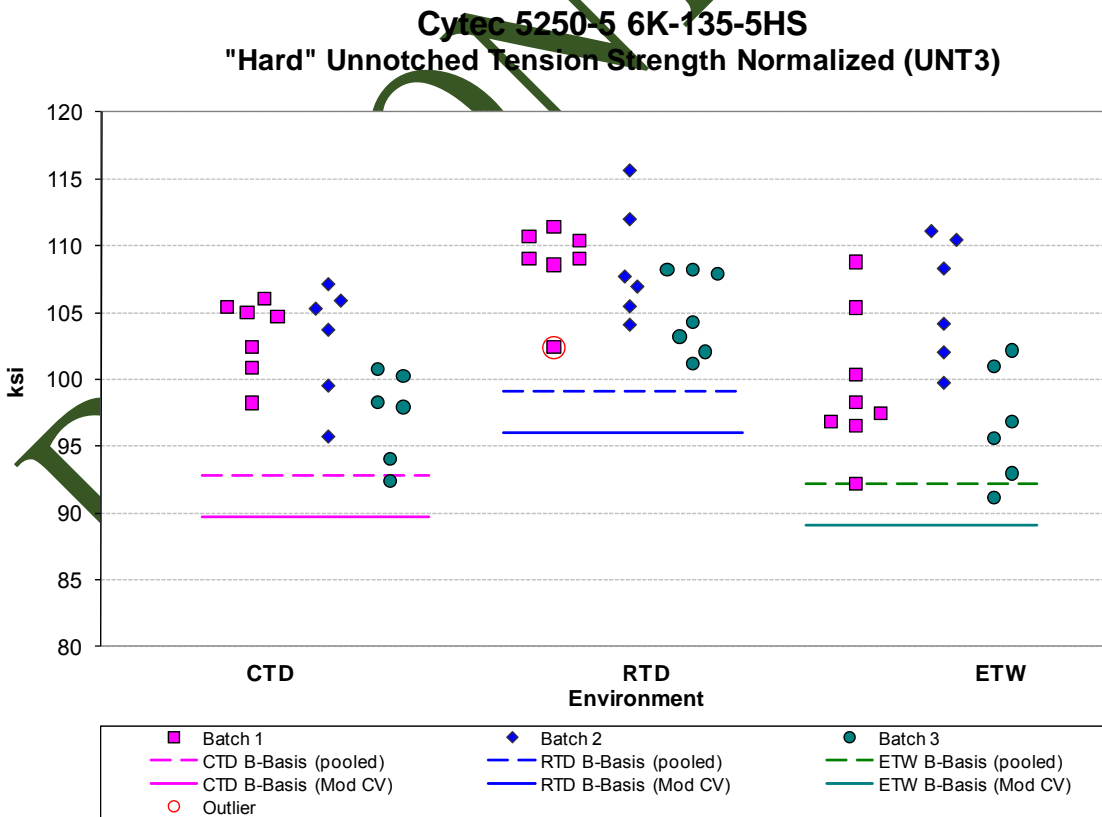


Figure 4-9: Batch Plot for UNT3 normalized strength

Unnotched Tension (UNT3) Strength Basis Values and Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	101.26	107.44	100.59	101.35	108.05	100.77
Stdev	4.35	3.76	5.98	4.66	4.43	6.47
CV	4.30	3.50	5.94	4.59	4.10	6.42
Modified CV	6.15	6.00	6.97	6.30	6.05	7.21
Min	92.42	101.22	91.17	91.80	100.59	90.02
Max	107.16	115.68	111.14	108.26	117.81	112.44
No. Batches	3	3	3	3	3	3
No. Spec.	19	20	20	19	20	20
Basis Values and Estimates						
B-basis Value	92.86	99.08	92.23			
B-Estimate				78.13	87.07	67.69
A-Estimate	87.24	93.45	86.60	61.56	72.09	44.08
Method	pooled	pooled	pooled	ANOVA	ANOVA	ANOVA
Modified CV Basis Values and Estimates						
B-basis Value	89.74	95.97	89.12	89.72	96.48	
B-Estimate						86.77
A-Estimate	82.03	88.25	81.40	81.79	88.53	76.82
Method	pooled	pooled	pooled	pooled	pooled	Normal

Table 4-16: Statistics and Basis Values for UNT3 Strength Data

Unnotched Tension (UNT3) Modulus Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	8.68	8.72	8.28	8.68	8.77	8.30
Stdev	0.10	0.21	0.19	0.13	0.22	0.17
CV	1.13	2.42	2.28	1.50	2.54	2.06
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	8.47	8.54	7.87	8.51	8.53	7.93
Max	8.88	9.53	8.57	8.97	9.47	8.57
No. Batches	3	3	3	3	3	3
No. Spec.	19	20	21	19	20	21

Table 4-17: Statistics from UNT3 Modulus Data



### 4.10 Quasi Isotropic Unnotched Compression (UNC1)

The UNC1 data was normalized so both normalized and as-measured statistics are provided. Pooling was unacceptable for both the normalized and the as-measured datasets due to a failure of Levene’s test. The as-measured RTD dataset failed the normality test. The Weibull distribution provided the best fit to that dataset. There were no outliers.

Statistics, basis values and estimates are given for UNC1 strength data in Table 4-18 and for the modulus data in Table 4-19. The normalized data and B-basis values are shown graphically in Figure 4-10.

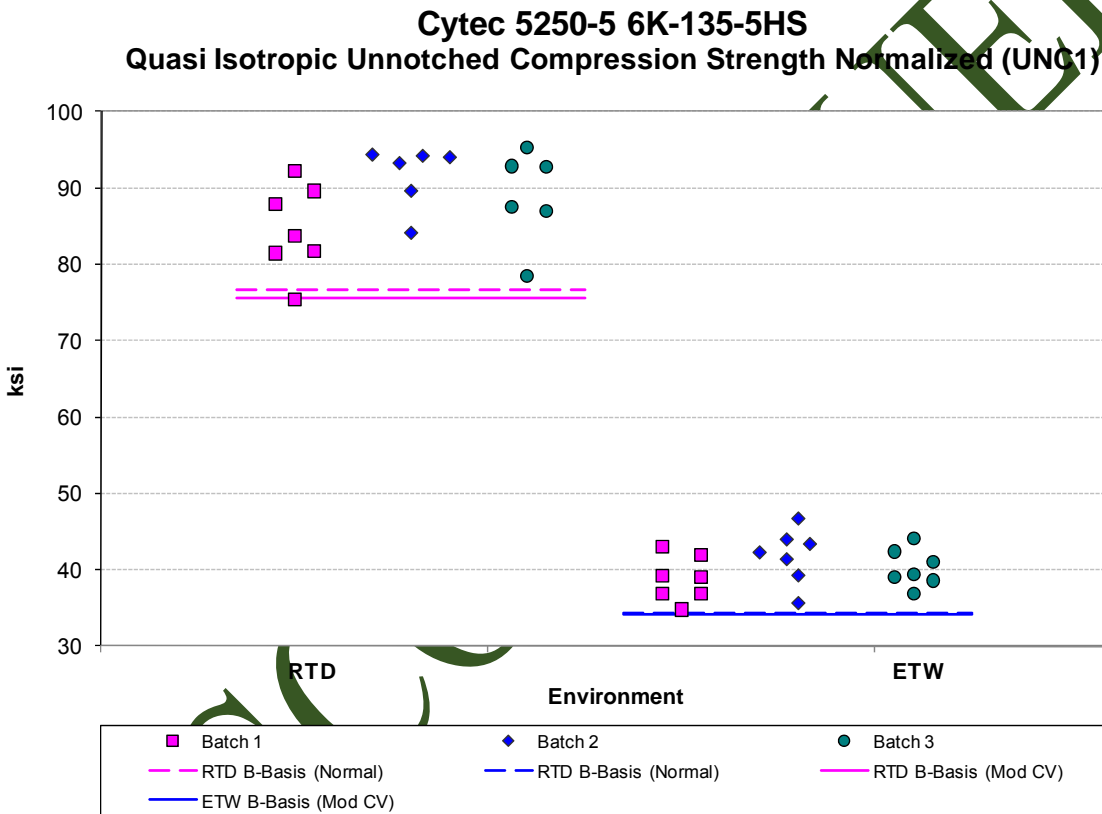


Figure 4-10: Batch plot for UNC1 normalized strength

Unnotched Compression (UNC1) Strength Basis Values and Statistics				
	Normalized		As Measured	
Env	RTD	ETW	RTD	ETW
Mean	88.16	40.27	89.35	40.12
Stdev	5.90	3.12	6.29	3.11
CV	6.70	7.74	7.04	7.75
Modified CV	7.35	7.87	7.52	7.88
Min	75.37	34.80	75.63	35.14
Max	95.27	46.72	96.33	46.42
No. Batches	3	3	3	3
No. Spec.	19	21	19	21
Basis Values and Estimates				
B-basis Value	76.65	34.34	76.92	34.20
A-Estimate	68.48	30.10	64.68	29.97
Method	Normal	Normal	Weibull	Normal
Modified CV Basis Values and Estimates				
B-basis Value	75.53	34.23	NA	34.10
A-Estimate	66.58	29.93	NA	29.81
Method	Normal	Normal	NA	Normal

Table 4-18: Statistics and Basis Values for UNC1 Strength Data

Unnotched Compression (UNC) Modulus Statistics				
	Normalized		As Measured	
Env	RTD	ETW	RTD	ETW
Mean	6.32	5.67	6.41	5.66
Stdev	0.17	0.28	0.19	0.30
CV	2.72	4.99	2.89	5.27
Modified CV	6.00	6.49	6.00	6.63
Min	5.77	5.24	6.02	5.22
Max	6.52	6.20	6.65	6.18
No. Batches	3	3	3	3
No. Spec.	19	19	19	19

Table 4-19: Statistics from UNC1 Modulus Data

### 4.11 “Soft” Unnotched Compression (UNC2)


The UNC2 data was normalized so both normalized and as-measured statistics are provided. Both the normalized and the as-measured ETW datasets failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. Since the ETW data had a CV greater than 8%, the modified CV method could not be used. Estimates of basis values computed with an override of the ADK result for the ETW as-measured dataset are also provided.

There was one outlier. It was from batch one and was the highest value for the ETW condition. It was an outlier for both the normalized and the as-measured data and for both batch one and for the ETW condition. It was removed for this analysis.

This outlier contributed heavily to the large variation of the dataset. When this outlier was removed from the normalized ETW dataset, that dataset passed the ADK test and a B-basis value could be provided. While no identifiable cause was found, since it was on the high end and deleting it reduced the mean and variation of ETW strength, it was removed from this analysis for both the normalized and the as-measured datasets.

The normalized RTD and ETW datasets could be pooled after removal of the outlier. The as-measured ETW dataset still failed the ADK test. Since the as-measured ETW dataset has a CV of over 8%, the modified CV method could not be used with that dataset.

Statistics, basis values and estimates are given for UNC2 strength data after removal of the outlier in Table 4-20. Statistics for the modulus data are given in Table 4-21. The normalized data and B-basis values are shown graphically in Figure 4-11. This graph includes the outlier that was removed prior to analysis.

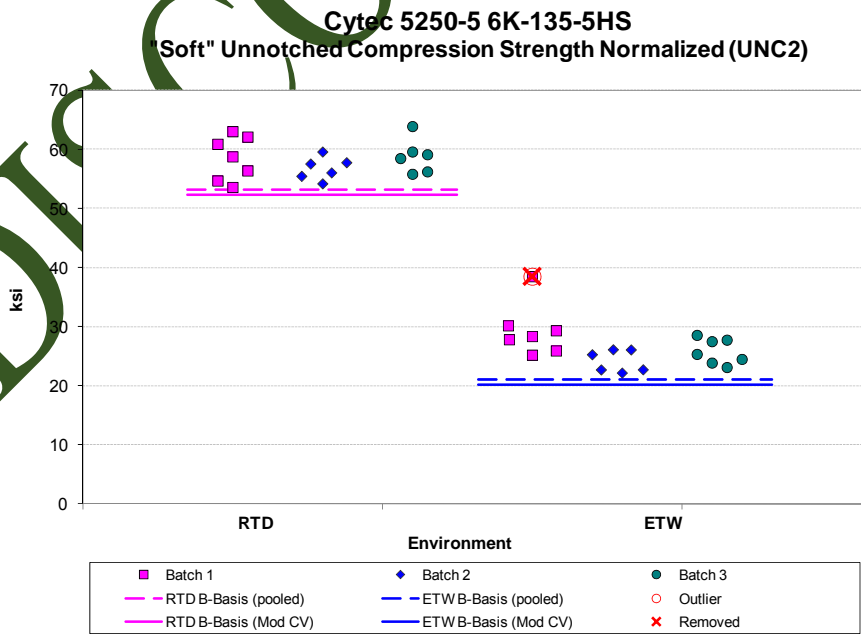

**Figure 4-11: Batch plot for UNC2 normalized strength**

Unnotched Compression (UNC2) Strength Basis Values and Statistics				
Env	Normalized		As Measured	
	RTD	ETW	RTD	ETW
Mean	58.07	25.95	58.98	25.90
Stdev	2.96	2.38	3.09	2.47
CV	5.10	9.17	5.23	9.53
Modified CV	6.55	9.17	6.62	9.53
Min	53.60	22.21	55.23	22.22
Max	63.90	30.19	65.32	30.78
No. Batches	3	3	3	3
No. Spec.	19	19	19	19
Basis Values and Estimates				
B-basis Value	53.23	21.10	52.96	15.00
B-Estimate				15.00
A-Estimate	49.92	17.79	48.69	7.23
Method	pooled	pooled	Normal	ANOVA
Modified CV Basis Values and Estimates				
B-basis Value	52.35	20.23	51.37	NA
A-Estimate	48.44	16.32	45.98	NA
Method	pooled	pooled	Normal	NA
Basis Value Estimates with override of ADK test result				
B-Estimate				21.09
A-Estimate				17.68
Method				Normal

Table 4-20: Statistics and Basis Values for UNC2 Strength Data

Unnotched Compression (UNC2) Modulus Statistics				
Env	Normalized		As Measured	
	RTD	ETW	RTD	ETW
Mean	4.23	3.32	4.30	3.32
Stdev	0.09	0.14	0.12	0.14
CV	2.12	4.27	2.86	4.32
Modified CV	6.00	6.14	6.00	6.16
Min	4.06	3.07	4.13	3.06
Max	4.38	3.56	4.55	3.58
No. Batches	3	3	3	3
No. Spec.	19	19	19	19

Table 4-21: Statistics from UNC2 Modulus Data

### 4.12 “Hard” Unnotched Compression (UNC3)

The UNC3 data was normalized so both normalized and as-measured statistics are provided. The RTD and ETW datasets, both normalized and as-measured, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. The RTD datasets passed the ADK test after applying the transformation to meet the assumptions of the modified CV method and modified CV basis values are provided. B-estimates were computed for the ETW datasets using the modified CV method, but it is considered an estimate since the ETW dataset failed the ADK test even after transforming the data for the modified CV method.

There were no outliers. Statistics, basis values and estimates are given for UNC3 strength data in Table 4-22 and for the modulus data in Table 4-23. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-12.

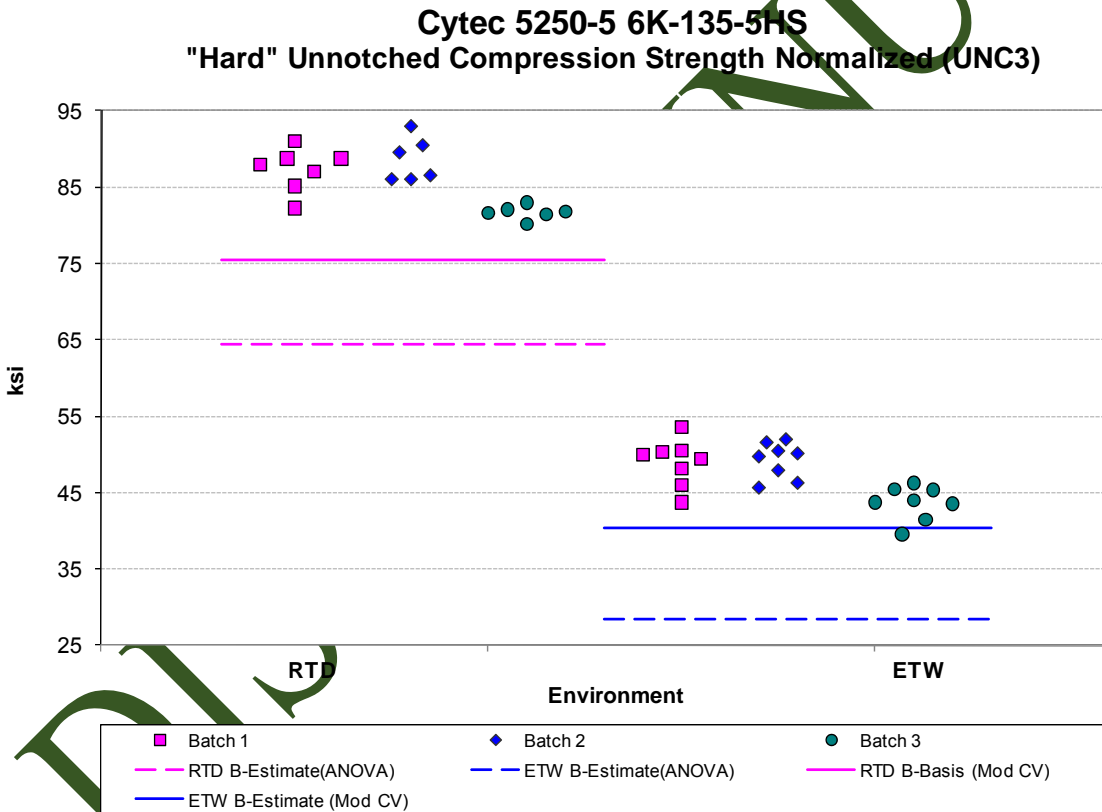


Figure 4-12: Batch plot for UNC3 normalized strength

Unnotched Compression (UNC3) Strength Basis Values and Statistics				
Env	Normalized		As Measured	
	RTD	ETW	RTD	ETW
Mean	85.91	47.29	86.19	47.02
Stdev	3.77	3.58	4.35	3.71
CV	4.39	7.58	5.05	7.89
Modified CV	6.20	7.79	6.52	7.95
Min	80.18	39.58	79.94	39.15
Max	92.90	53.61	93.73	53.22
No. Batches	3	3	3	3
No. Spec.	19	24	19	24
Basis Values and Estimates				
B-Estimate	64.37	28.35	59.65	26.43
A-Estimate	48.99	14.82	40.71	11.73
Method	ANOVA	ANOVA	ANOVA	ANOVA
Modified CV Basis Values and Estimates				
B-basis Value	75.53		75.23	
B-Estimate		40.46		40.16
A-Estimate	68.18	35.57	67.46	35.14
Method	Normal	Normal	Normal	Normal

Table 4-22: Statistics and Basis values for UNC3 Strength Data

Unnotched Compression (UNC3) Modulus Statistics				
Env	Normalized		As Measured	
	RTD	ETW	RTD	ETW
Mean	7.86	7.61	7.88	7.55
Stdev	0.20	0.28	0.20	0.29
CV	2.52	3.64	2.59	3.80
Modified CV	6.00	6.00	6.00	6.00
Min	7.57	7.15	7.46	7.02
Max	8.28	8.14	8.26	8.03
No. Batches	3	3	3	3
No. Spec.	19	19	19	19

Table 4-23: Statistics from UNC3 Modulus Data

### 4.13 Laminate Short Beam Strength (SBS1) Data

The SBS1 data was not normalized. The ETW dataset failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. A B-estimate was computed for the ETW dataset using the modified CV method, but it is considered an estimate since the ETW dataset failed the ADK test even after transforming the data for the modified CV method.

There were no outliers. The Laminate Short Beam Strength data is not normalized. Statistics, basis values and estimates are given for LSBS strength data in Table 4-24. The data, B-estimates and B-basis values are shown graphically in Figure 4-13.

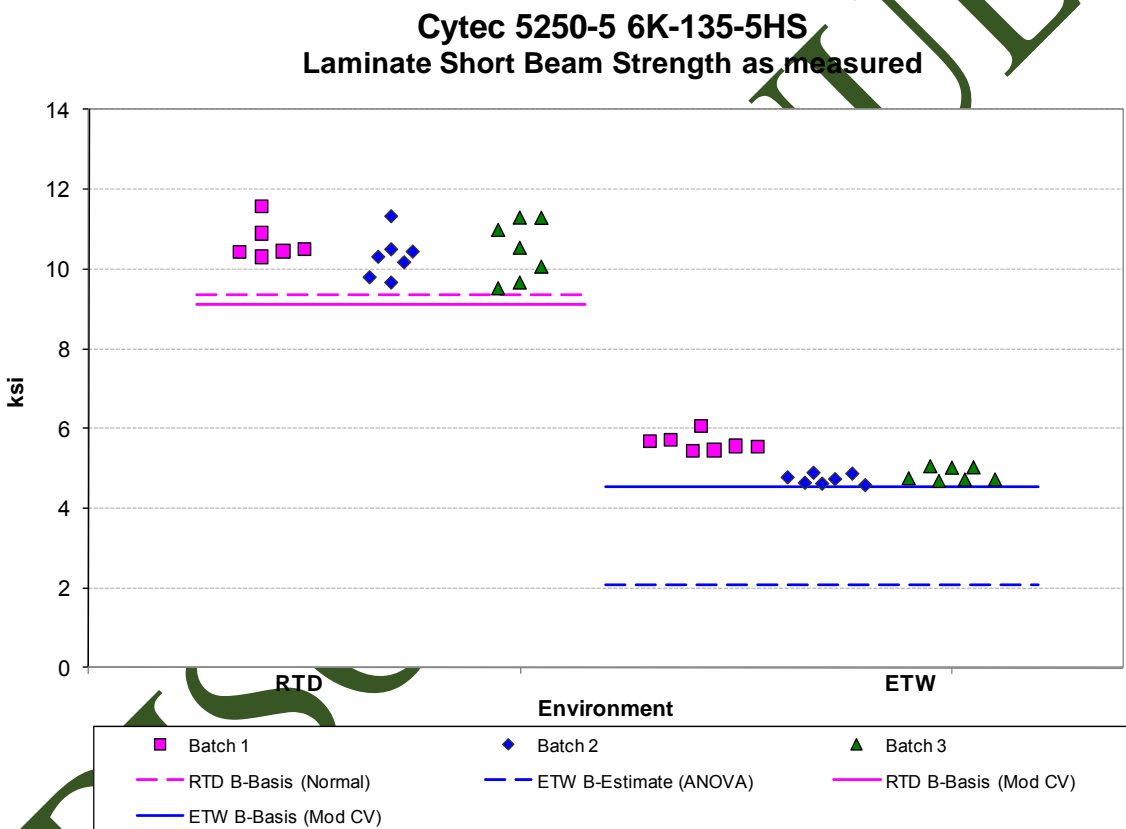


Figure 4-13: Batch plot for SBS1 strength as-measured

<b>Laminate Short Beam Strength (SBS1)</b>		
Env	RTD	ETW
Mean	10.49	5.08
Stdev	0.59	0.44
CV	5.65	8.65
Modified CV	6.83	8.65
Min	9.53	4.60
Max	11.56	6.07
No. Batches	3	3
No. Spec.	20	21
<b>Basis Value Estimates</b>		
B-basis Value	9.35	
B-Estimate		2.09
A-Estimate	8.54	NA
Method	Normal	ANOVA
<b>Modified CV Basis Values and Estimates</b>		
B-basis Value	9.11	
B-Estimate		4.24
A-Estimate	8.13	3.65
Method	Normal	Normal

Table 4-24: Statistics and Basis Values for SBS1 Strength Data

DISCONTINUED



### 4.14 Quasi Isotropic Open Hole Tension Properties (OHT1)

The OHT1 data was normalized so both normalized and as-measured statistics are provided. The as-measured pooled dataset failed Levene’s test so pooling was unacceptable. There were no other test failures. Pooling was acceptable for the normalized datasets.

There were no outliers. Statistics, basis values and estimates are given for OHT1 strength data in Table 4-25. The normalized data, B-basis values and B-estimates are shown graphically in Figure 4-14.

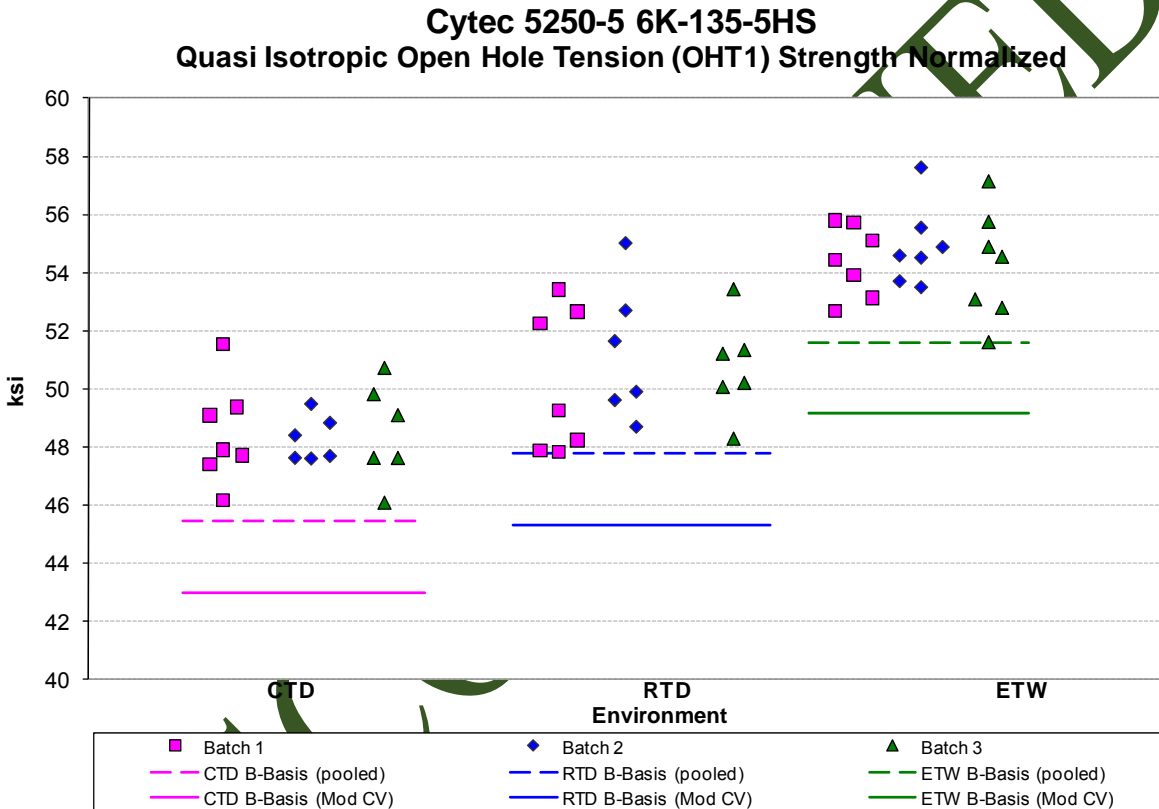


Figure 4-14: Batch Plot for OHT1 normalized strength

Open Hole Tension (OHT1) Strength Basis Values and Statistics						
	Normalized			As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	48.43	50.74	54.53	48.39	51.08	54.33
Stdev	1.40	2.13	1.48	1.27	2.27	1.62
CV	2.90	4.20	2.71	2.63	4.45	2.98
Modified CV	6.00	6.10	6.00	6.00	6.22	6.00
Min	46.11	47.85	51.62	46.17	47.82	51.11
Max	51.54	55.04	57.63	51.20	55.41	57.94
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	21	19	19	21
Basis Values and Estimates						
B-basis Value	45.46	47.77	51.59	45.91	46.66	51.25
A-Estimate	43.47	45.78	49.60	44.15	43.51	49.05
Method	pooled	pooled	pooled	Normal	Normal	Normal
Modified CV Basis Values and/or Estimates						
B-basis Value	43.00	45.30	49.15	42.73	44.89	48.12
A-Estimate	39.36	41.67	45.51	38.72	40.49	43.70
Method	pooled	pooled	pooled	Normal	Normal	Normal

Table 4-25: Statistics and Basis Values for OHT1 Strength Data

DISCONTINUED

### 4.15 “Soft” Open Hole Tension Properties (OHT2)

The OHT2 data was normalized so both normalized and as-measured statistics are provided. The CTD and ETW datasets, both normalized and as-measured, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. The CTD datasets passed the ADK test after applying the transformation to meet the assumptions of the modified CV method and modified CV basis values are provided. The ETW datasets failed the normality test and the ADK test even after transforming the data for the modified. An override of the ADK result for the ETW datasets is recommended and is permissible in this case according to the guidelines given in section 8.3.10.1 of CMH-17 Rev G with situation 1 being applicable to this dataset.

There were no outliers. Statistics, basis values and estimates are given for OHT2 strength data in Table 4-26. The normalized data and B-basis values are shown graphically in Figure 4-15.

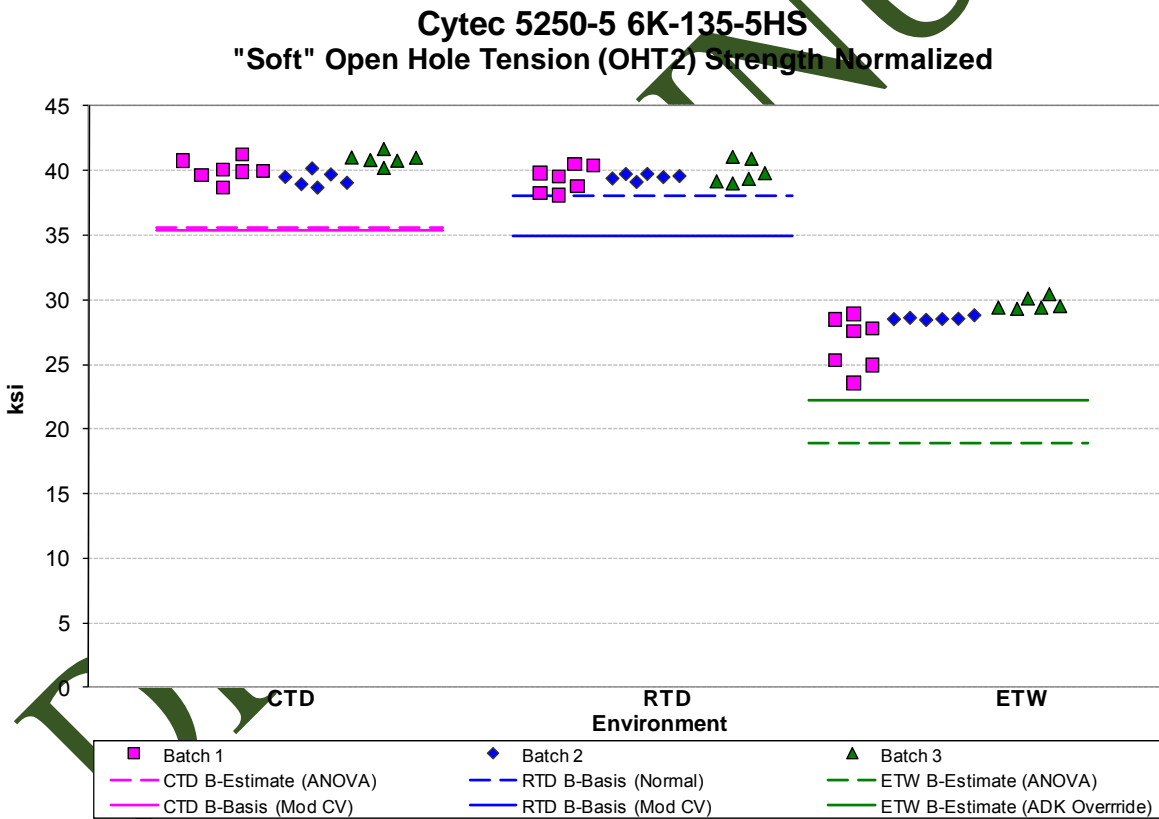


Figure 4-15: Batch Plot for OHT2 normalized strength

Open Hole Tension (OHT2) Strength Basis Values and Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	40.13	39.60	28.23	40.01	39.66	28.19
Stdev	0.88	0.79	1.78	1.00	0.74	1.70
CV	2.20	1.98	6.30	2.51	1.85	6.02
Modified CV	6.00	6.00	7.15	6.00	6.00	7.01
Min	38.69	38.09	23.56	38.27	38.64	23.78
Max	41.71	41.10	30.45	42.15	40.97	30.40
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	19	19	19	19
Basis Values and Estimates						
B-basis Value		38.07			38.23	
B-Estimate	35.60		18.91	35.04		18.97
A-Estimate	32.38	36.98	12.25	31.49	37.21	12.39
Method	ANOVA	Normal	ANOVA	ANOVA	Normal	ANOVA
Modified CV Basis Values and Estimates						
B-basis Value	35.43	34.97		35.70	35.35	
A-Estimate	32.11	31.68		32.76	32.41	
Method	Normal	Normal		pooled	pooled	
Basis Values and Estimates with override of ADK test result						
B-basis Value			22.19			24.98
A-Estimate			16.33			21.72
Method			Non-Parametric			Weibull

Table 4-26: Statistics and Basis Values for OHT2 Strength Data

DISCOM

### 4.16 "Hard" Open Hole Tension Properties (OHT3)

The OHT3 data was normalized so both normalized and as-measured statistics are provided. The ETW datasets, both normalized and as-measured, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. These datasets passed the ADK test after applying the transformation to meet the assumptions of the modified CV method so modified CV basis values are provided. There were no other test failures.

There were no outliers. Statistics, basis values and estimates are given for OHT3 strength data in Table 4-27. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-16.

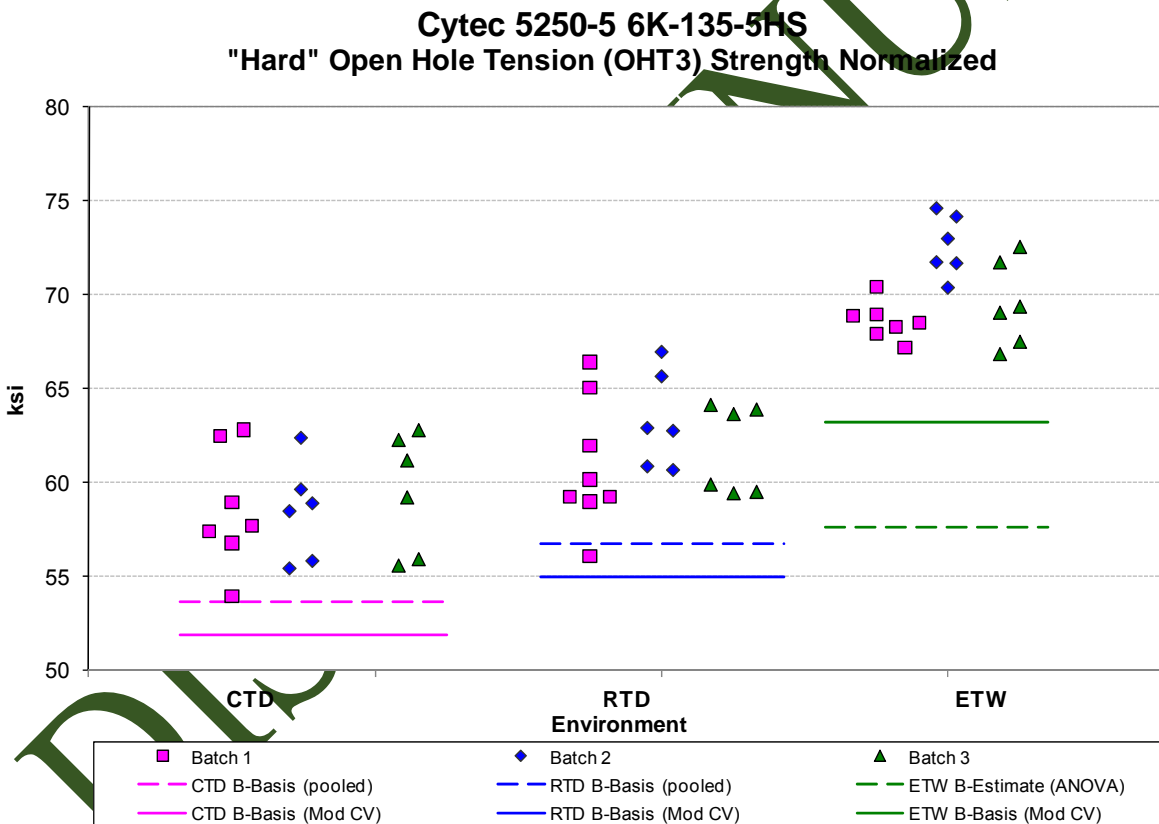


Figure 4-16: Batch Plot for OHT3 normalized strength

Open Hole Tension (OHT3) Strength (ksi) Basis Values and Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	58.84	61.89	70.16	58.44	61.87	69.92
Stdev	2.86	2.92	2.36	2.95	2.91	2.44
CV	4.86	4.72	3.37	5.05	4.71	3.49
Modified CV	6.43	6.36	6.00	6.52	6.35	6.00
Min	53.94	56.10	66.86	53.75	55.95	66.41
Max	62.82	66.98	74.64	63.30	66.83	74.31
No. Batches	3	3	3	3	3	3
No. Spec.	19	20	19	19	20	19
Basis Value Estimates						
B-basis Value	53.64	56.71		53.17	56.62	
B-Estimate			57.63			58.02
A-Estimate	50.09	53.16	48.68	49.57	53.02	49.54
Method	pooled	pooled	ANOVA	pooled	pooled	ANOVA
Modified CV Basis Values and Estimates						
B-basis Value	51.86	54.95	63.19	51.46	54.92	62.94
A-Estimate	47.19	50.27	58.51	46.78	50.24	58.26
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-27: Statistics and Basis Values for OHT3 Strength Data

DISCONTINUED

### 4.17 Quasi Isotropic Filled Hole Tension (FHT1)

The FHT1 data was normalized so both normalized and as-measured statistics are provided. Pooling was unacceptable for the as-measured datasets due to a failure of Levene’s test, but the normalized data could be pooled across the environments. There were no other test failures.

There were two outliers. One outlier was from batch one and was the highest value in the CTD condition. It was an outlier only for the normalized data and only for the CTD condition, not batch one. The second outlier was the lowest value in batch one of the ETW condition. It was an outlier in both the normalized and the as-measured datasets, but it was an outlier only for batch one, not for the ETW condition. Both outliers were retained for this analysis.

Statistics, basis values and estimates are given for FHT1 strength data in Table 4-28. The normalized data and B-basis values are shown graphically in Figure 4-17.

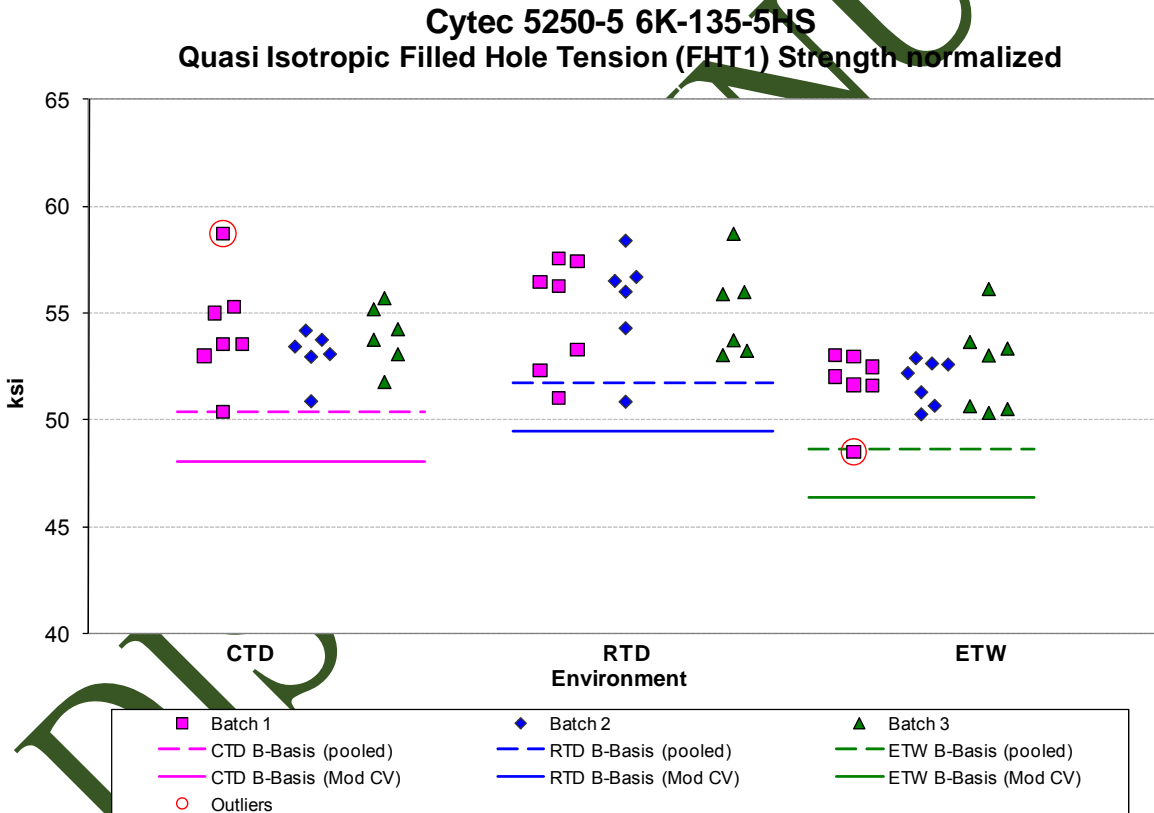


Figure 4-17: Batch plot for FHT1 normalized strength

Filled Hole Tension (FHT1) Strength Basis Values and Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	53.78	55.15	52.03	53.85	55.06	51.84
Stdev	1.84	2.37	1.60	1.86	2.64	1.51
CV	3.42	4.30	3.07	3.46	4.80	2.92
Modified CV	6.00	6.15	6.00	6.00	6.40	6.00
Min	50.38	50.87	48.51	50.69	50.35	48.77
Max	58.74	58.73	56.14	58.72	59.19	55.44
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	21	19	19	21
Basis Values and Estimates						
B-basis Value	50.36	51.74	48.65	50.22	49.91	48.96
A-Estimate	48.07	49.45	46.35	47.64	46.25	46.91
Method	pooled	pooled	pooled	Normal	Normal	Normal
Modified CV Basis Values and Estimates						
B-basis Value	48.09	49.47	46.40	47.55	48.15	45.92
A-Estimate	44.29	45.67	42.59	43.09	43.32	41.69
Method	pooled	pooled	pooled	Normal	Normal	Normal

Table 4-28: Statistics and Basis Values for FHT1 Strength Data

DISCONTINUED



### 4.18 "Soft" Filled Hole Tension (FHT2)

The FHT2 data was normalized so both normalized and as-measured statistics are provided. The as-measured CTD dataset and the as-measured pooled dataset failed the normality test. This was due to an outlier in the CTD condition. If the outlier is removed, both the CTD dataset and the pooled dataset pass the normality test. An override of the normality test result is recommended for this reason and pooled basis values are provided. The normalized data had no test failures.

There was one outlier. The outlier was from batch one and was the highest value in the CTD condition. It was an outlier only for the as-measured data, nor the normalized data. It was an outlier for both batch one and for the CTD condition. The outlier was retained for this analysis.

Statistics, basis values and estimates are given for FHT2 strength data in Table 4-29. The normalized data and the B-basis values are shown graphically in Figure 4-18.

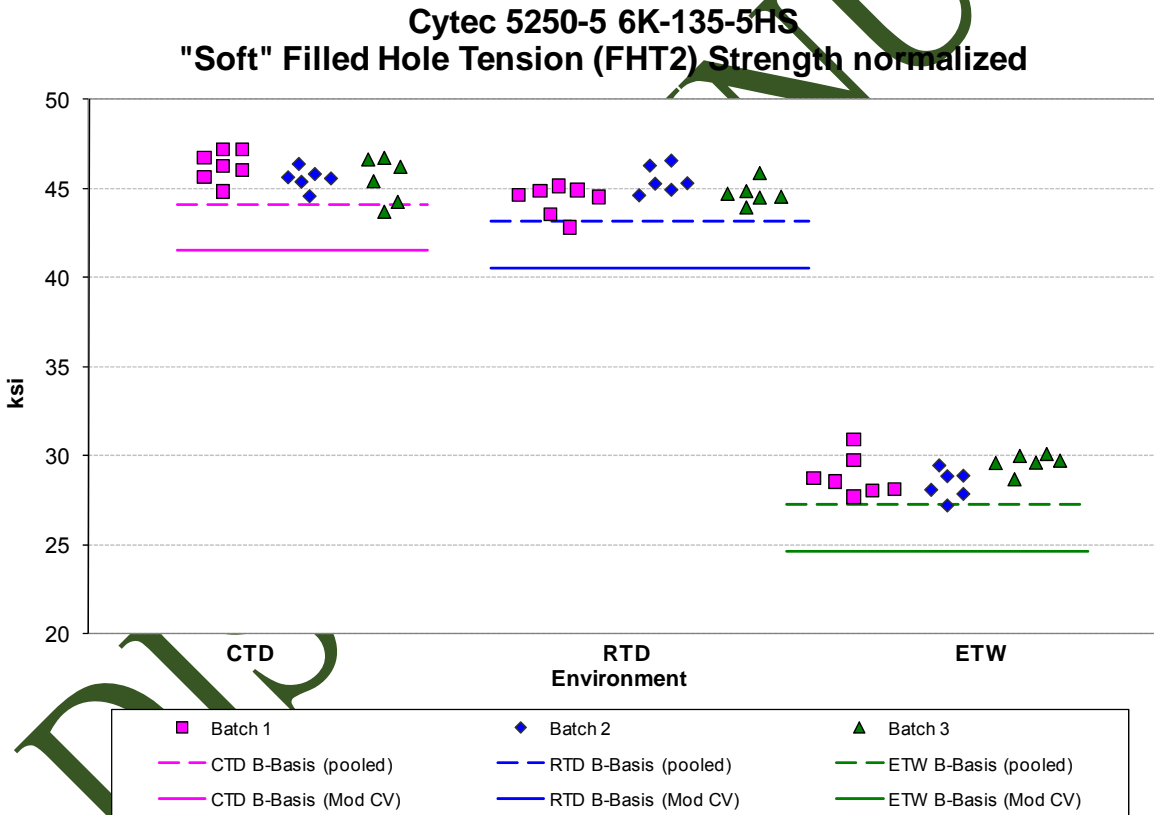


Figure 4-18: Batch plot for FHT2 normalized strength

Filled Hole Tension (FHT2) Strength Basis Values and Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	45.79	44.82	28.92	45.89	44.95	28.90
Stdev	0.97	0.87	0.97	0.85	0.93	0.95
CV	2.12	1.93	3.35	1.86	2.08	3.30
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	43.66	42.84	27.17	44.36	43.47	27.03
Max	47.19	46.56	30.93	48.55	47.10	30.70
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	19	19	19	19
Basis Values and Estimates						
B-basis Value	44.14	43.18	27.28	44.28	43.35	27.30
A-Estimate	43.04	42.08	26.17	43.20	42.27	26.22
Method	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and Estimates						
B-basis Value	41.51	40.55	24.65	41.61	40.67	24.62
A-Estimate	38.65	37.68	21.78	38.73	37.80	21.75
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-29: Statistics and Basis Values for FHT2 Strength Data

DISCONTINUED

### 4.19 "Hard" Filled Hole Tension (FHT3)

The FHT3 data was normalized so both normalized and as-measured statistics are provided. The RTD datasets, both normalized and as-measured, and the as-measured ETW dataset failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. All three of those datasets passed the ADK test after applying the transformation to meet the assumptions of the modified CV method and modified CV basis values are provided. When the data from all three conditions was transformed, the pooled dataset passed Levene's test, so pooling was used to compute the modified CV basis values.

There were no outliers. Statistics, basis values and estimates are given for FHT3 strength data in Table 4-30. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-19.

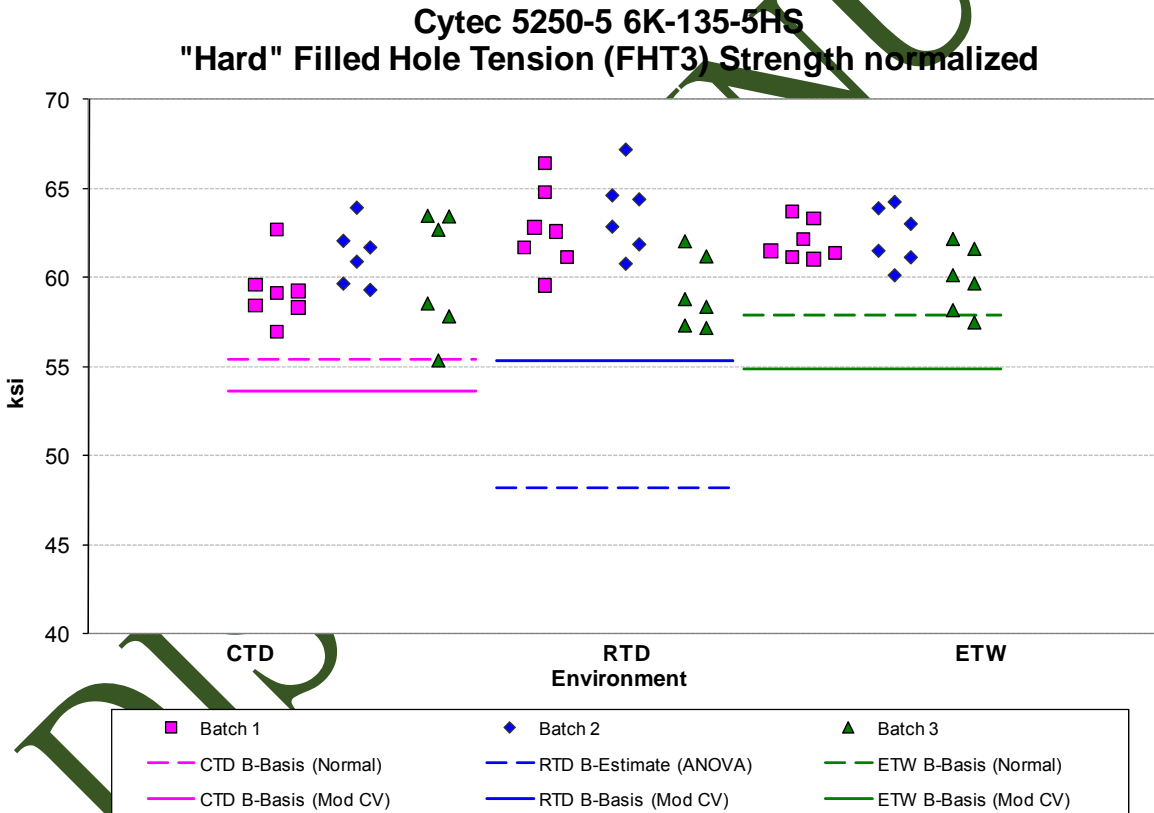


Figure 4-19: Batch plot for FHT3 normalized strength

Filled Hole Tension (FHT3) Strength Basis Values and Statistics						
Normalized				As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	60.18	61.87	61.44	60.39	61.49	61.39
Stdev	2.43	2.85	1.82	2.59	3.03	2.01
CV	4.04	4.61	2.96	4.28	4.93	3.27
Modified CV	6.02	6.31	6.00	6.14	6.46	6.00
Min	55.33	57.15	57.46	54.86	56.32	56.91
Max	63.92	67.16	64.25	65.06	67.24	64.47
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	19	19	19	19
Basis Values and Estimates						
B-basis Value	55.44		57.90	55.35		
B-Estimate		48.17			46.15	50.33
A-Estimate	52.08	38.39	55.38	51.77	35.21	42.78
Method	Normal	ANOVA	Normal	Normal	ANOVA	ANOVA
Modified CV Basis Values and Estimates						
B-basis Value	53.61	55.31	54.88	53.74	54.83	54.74
A-Estimate	49.21	50.91	50.48	49.28	50.37	50.28
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-30: Statistics and Basis Values for FHT3 Strength Data

DISCONTINUED

### 4.20 Quasi Isotropic Open Hole Compression (OHC1)

The OHC1 data was normalized so both normalized and as-measured statistics are provided. The ETW datasets, both normalized and as-measured, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. B-estimates were computed for the ETW datasets using the modified CV method, but these are considered estimates since the ETW datasets failed the ADK test even after transforming the data for the modified CV method.

There was one outlier. It was the lowest value in batch two of the RTD dataset. It was an outlier for both the normalized and the as-measured data. It was an outlier only for batch two, not for the RTD condition. This outlier was retained for this analysis.

Statistics, B-basis values and estimates are given for OHC1 strength data in Table 4-31. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-20.

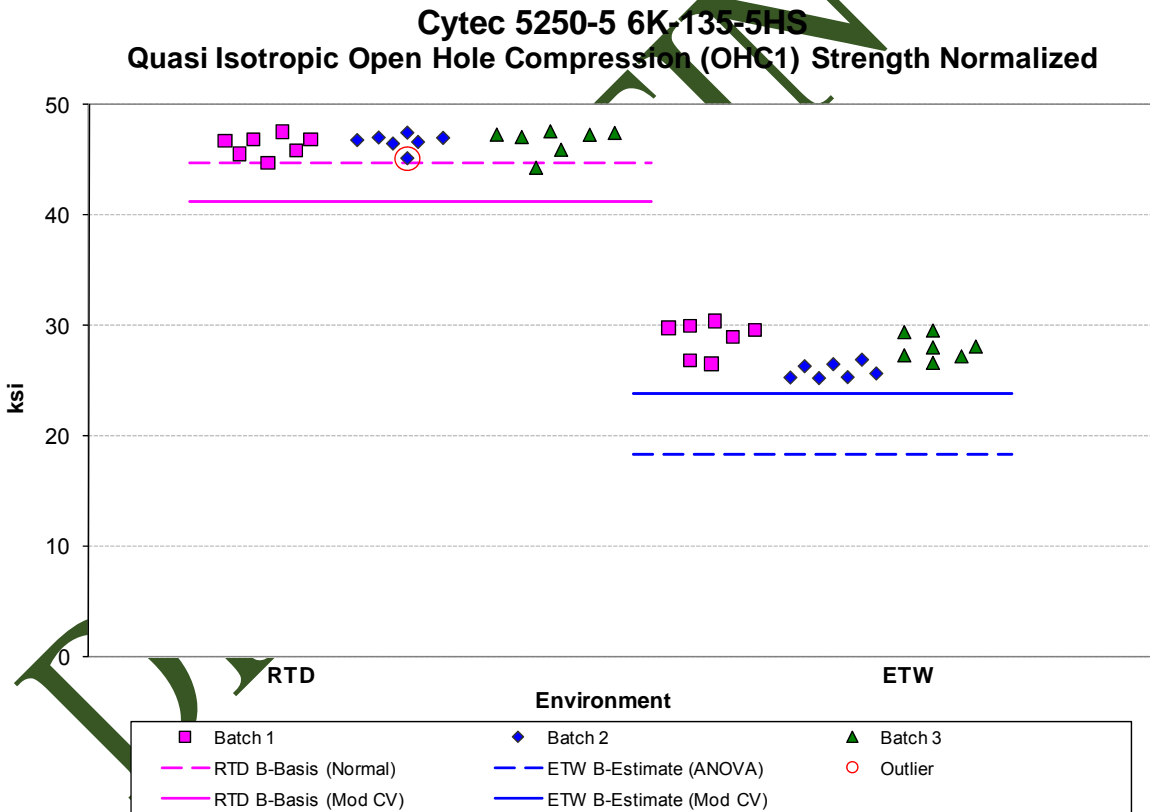


Figure 4-20: Batch plot for OHC1 normalized strength

Open Hole Compression (OHC1) Strength Basis Values and Statistics				
Env	Normalized		As Measured	
	RTD	ETW	RTD	ETW
Mean	46.54	27.59	46.65	27.68
Stdev	0.95	1.70	0.89	1.66
CV	2.03	6.15	1.90	6.01
Modified CV	6.00	7.07	6.00	7.00
Min	44.25	25.23	44.98	25.18
Max	47.56	30.40	47.81	30.53
No. Batches	3	3	3	3
No. Spec.	21	21	21	21
Basis Values and Estimates				
B-basis Value	44.79		44.83	
B-Estimate		18.33		18.85
A-Estimate	42.80	11.71	42.78	12.54
Method	Weibull	ANOVA	Weibull	ANOVA
Modified CV Basis Values and Estimates				
B-basis Value	41.22		41.32	
B-Estimate		23.87		23.99
A-Estimate	37.43	21.22	37.52	21.36
Method	Normal	Normal	Normal	Normal

Table 4-31: Statistics and Basis Values for OHC1 Strength Data

DISCONTINUED

### 4.21 "Soft" Open Hole Compression (OHC2)

The OHC2 data was normalized so both normalized and as-measured statistics are provided. The ETW datasets, both normalized and as-measured failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. Both of those datasets passed the ADK test after applying the transformation to meet the assumptions of the modified CV method and modified CV basis values are provided.

There were no outliers. Statistics, basis values and estimates are given for OHC2 strength data in Table 4-32. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-21.

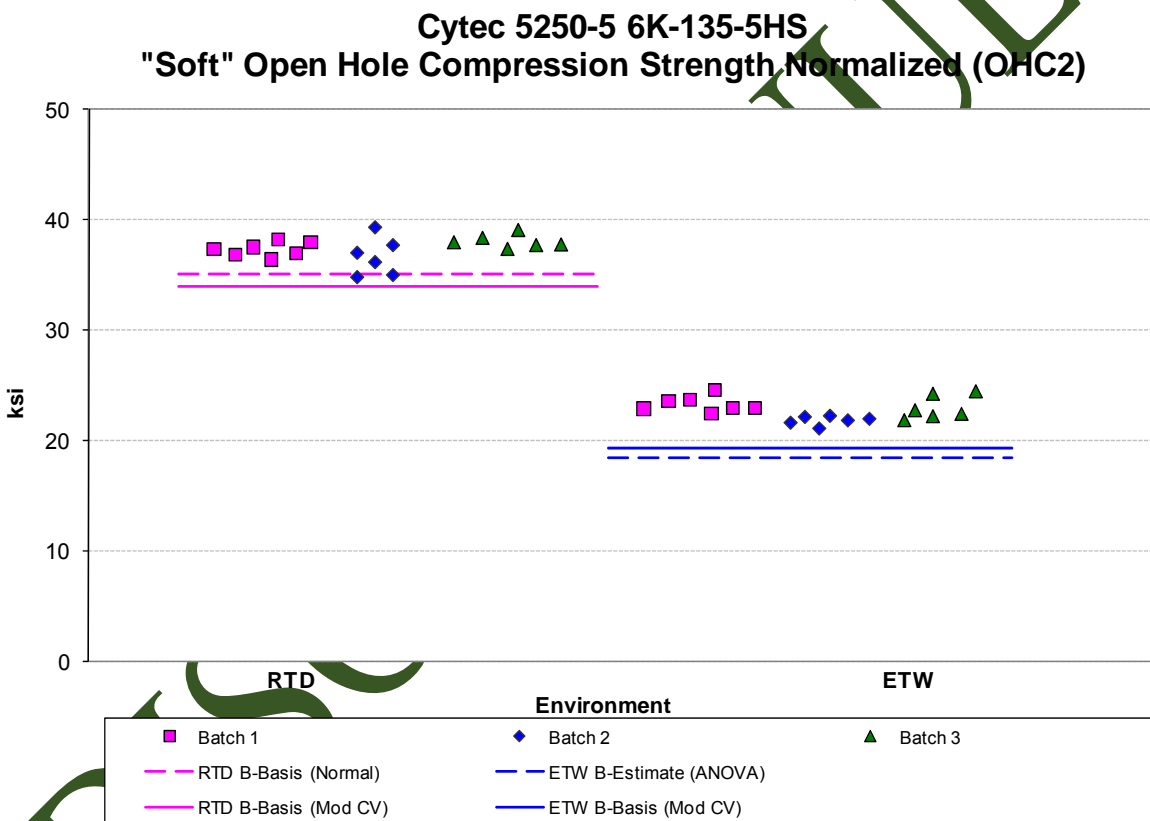


Figure 4-21: Batch plot for OHC2 normalized strength

Open Hole Compression (OHC2) Strength Basis Values and Statistics				
	Normalized		As Measured	
Env	RTD	ETW	RTD	ETW
Mean	37.37	22.77	37.26	22.78
Stdev	1.18	0.97	1.21	0.93
CV	3.15	4.26	3.26	4.08
Modified CV	6.00	6.13	6.00	6.04
Min	34.83	21.18	34.42	21.49
Max	39.33	24.62	38.93	24.86
No. Batches	3	3	3	3
No. Spec.	19	19	19	19
Basis Values and Estimates				
B-basis Value	35.08		34.90	
B-Estimate		18.44		17.96
A-Estimate	33.45	15.35	33.22	14.51
Method	Normal	ANOVA	Normal	ANOVA
Modified CV Basis Values and Estimates				
B-basis Value	34.00	19.40	33.92	19.44
A-Estimate	31.70	17.10	31.68	17.15
Method	pooled	pooled	pooled	pooled

Table 4-32: Statistics and Basis Values for OHC2 Strength Data

DISCONTINUED



### 4.22 "Hard" Open Hole Compression (OHC3)

The OHC3 data was normalized so both normalized and as-measured statistics are provided. There were no tests failures. Pooling across the environments was acceptable.

There were no outliers. Statistics, basis values and estimates are given for OHC3 strength data in Table 4-33. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-22.

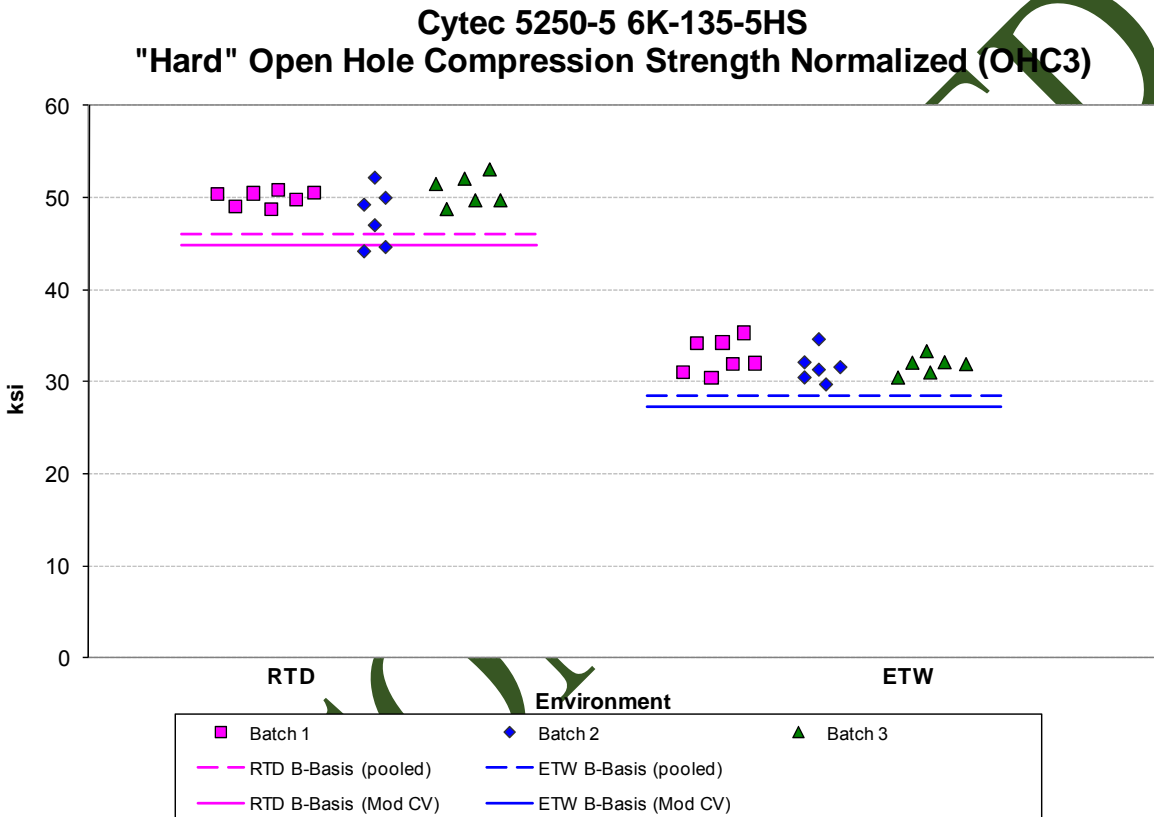


Figure 4-22: Batch plot for OHC3 normalized strength

DISC

Open Hole Compression (OHC3) Strength Basis Values and Statistics				
	Normalized		As Measured	
Env	RTD	ETW	RTD	ETW
Mean	49.58	32.09	49.43	32.10
Stdev	2.30	1.57	2.40	1.61
CV	4.63	4.89	4.85	5.01
Modified CV	6.31	6.45	6.42	6.50
Min	44.19	29.72	43.62	29.77
Max	53.06	35.31	53.39	35.12
No. Batches	3	3	3	3
No. Spec.	19	19	19	19
Basis Values and Estimates				
B-basis Value	46.03	28.54	45.75	28.42
A-Estimate	43.61	26.12	43.23	25.91
Method	pooled	pooled	pooled	pooled
Modified CV Basis Values and Estimates				
B-basis Value	44.79	27.30	44.58	27.25
A-Estimate	41.52	24.03	41.27	23.94
Method	pooled	pooled	pooled	pooled

Table 4-33: Statistics and Basis Values for OHC3 Strength Data

DISCONTINUED

### 4.23 Quasi Isotropic Filled Hole Compression (FHC1)

The FHC1 data was normalized so both normalized and as-measured statistics are provided. The pooled normalized data failed the test for normality, so pooling was unacceptable. However, the as-measured data could be pooled across the environments. There were no other test failures. The ETW dataset had a CV greater than 8%, so no modified CV basis values are provided as that method would not alter the results which are presented.

There was one outlier. It was the highest value in batch three of the RTD data. It was an outlier for both the normalized and the as-measured datasets, but only for batch three, not for the RTD condition.

Statistics, basis values and estimates are given for FHC1 strength data in Table 4-34. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-23.

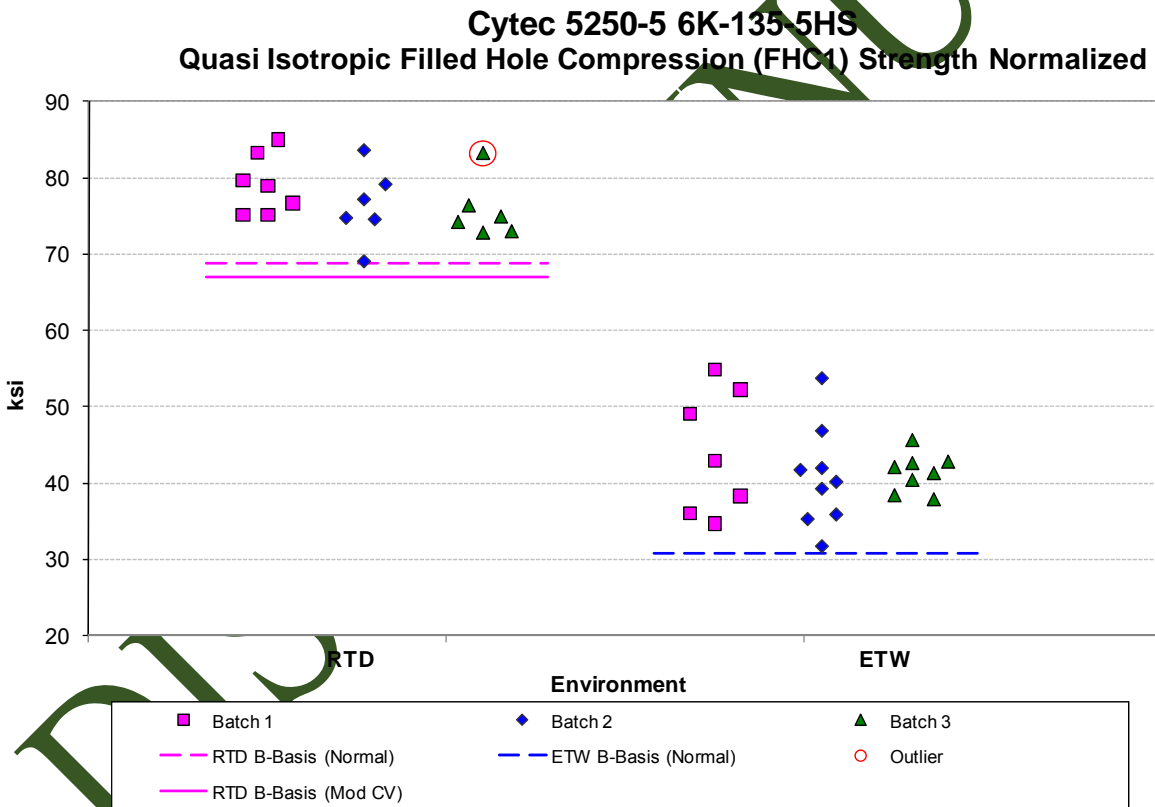


Figure 4-23: Batch plot for FHC1 normalized strength

Filled Hole Compression (FHC1) Strength Basis Values and Statistics				
	Normalized		As Measured	
Env	RTD	ETW	RTD	ETW
Mean	77.20	41.92	77.25	42.00
Stdev	4.27	6.02	4.15	6.09
CV	5.53	14.35	5.38	14.50
Modified CV	6.76	14.35	6.69	14.50
Min	69.09	31.73	69.28	31.83
Max	84.99	54.94	84.56	54.73
No. Batches	3	3	3	3
No. Spec.	19	24	19	24
Basis Values and Estimates				
B-basis Value	68.88	30.78	67.73	32.68
A-Estimate	62.97	22.79	61.27	26.17
Method	Normal	Normal	pooled	pooled
Modified CV Basis Values and Estimates				
B-basis Value	67.02	NA	67.06	32.02
A-Estimate	59.80		60.14	25.06
Method	Normal		pooled	pooled

Table 4-34: Statistics and Basis Values for FHC1 Strength Data

DISCONTINUED

### 4.24 "Soft" Filled Hole Compression (FHC2)

The FHC2 data was normalized so both normalized and as-measured statistics are provided. The ETW datasets, both normalized and as-measured, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate.

The ETW datasets failed the normality test and the ADK test even after transforming the data for the modified. Examination of the data reveals that the failure of the ADK test is due to the batch one data having higher strength values than nearly all values from batches two and three. An override of the ADK test result is not recommended as the ETW data does not meet any of the guideline situations covered in CMH-17 Rev G section 8.3.10.1. Addition B-estimates were computed for the ETW datasets using the modified CV method for two batches described in section 2.3 and applied to batches two and three.

There was one outlier. It was on the high side of batch three in the ETW environment. It was an outlier only for the as-measured dataset, not the normalized dataset and it was an outlier only for batch three, not for the ETW condition.

Statistics, basis values and estimates are given for FHC2 strength data in Table 4-35. The normalized data and the B-basis values are shown graphically in Figure 4-24.

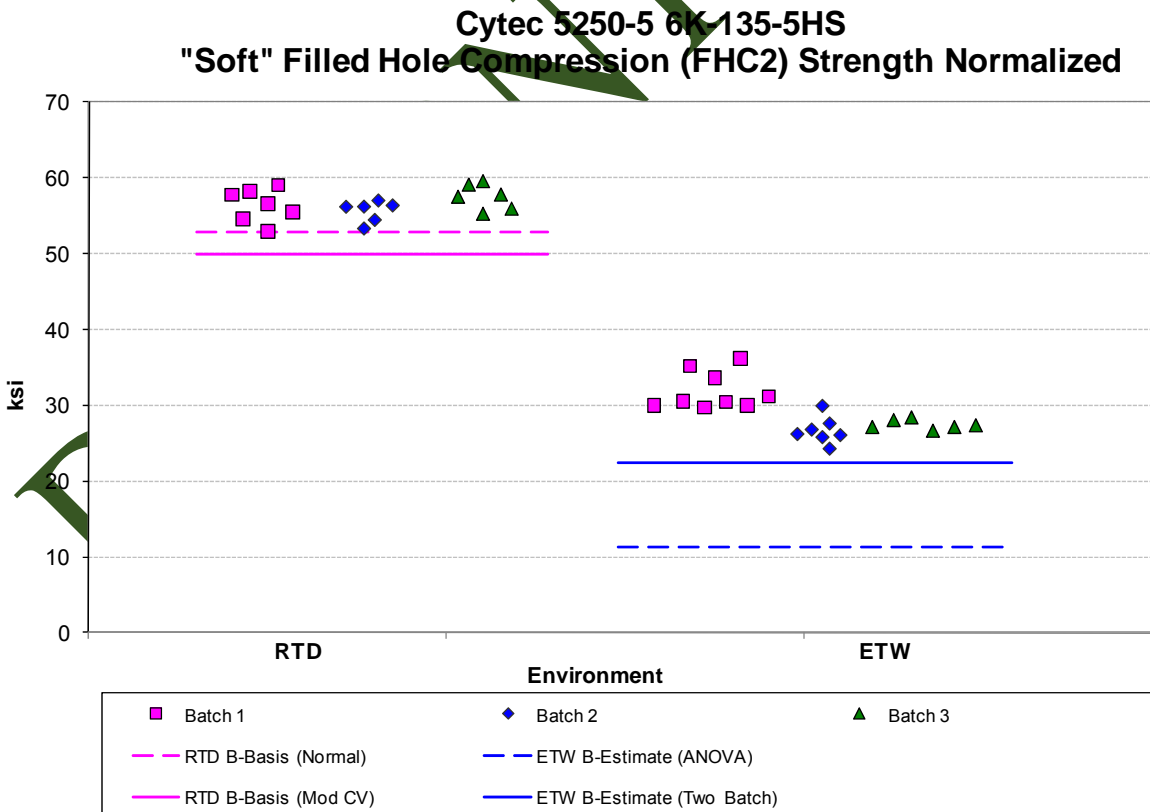


Figure 4-24: Batch plot for FHC2 normalized strength

Filled Hole Compression (FHC2) Strength Basis Values and Statistics				
Normalized			As Measured	
Env	RTD	ETW	RTD	ETW
Mean	56.52	29.02	56.45	29.03
Stdev	1.89	3.04	1.72	3.07
CV	3.34	10.48	3.05	10.59
Modified CV	6.00	10.48	6.00	10.59
Min	52.98	24.31	52.75	24.60
Max	59.58	36.19	58.99	36.26
No. Batches	3	3	3	3
No. Spec.	19	22	19	22
Basis Values and Estimates				
B-basis Value	52.84		53.09	
B-Estimate		11.25		10.78
A-Estimate	50.23	NA	50.71	NA
Method	Normal	ANOVA	Normal	ANOVA
Modified CV Basis Values and Estimates				
B-basis Value	49.91		49.85	
B-Estimate		22.39		23.23
A-Estimate	45.22	19.13	45.17	19.09
Method	Normal	Two Batch	Normal	Two Batch

Table 4-35: Statistics and Basis Values for FHC2 Strength Data

DISCONTINUED

### 4.25 "Hard" Filled Hole Compression (FHC3)

The FHC3 data was normalized so both normalized and as-measured statistics are provided. There were no usable values from the RTD tests due bad failure modes occurring for all specimens.

The ETW datasets, both normalized and as-measured, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. Both of those datasets passed the ADK test after applying the transformation to meet the assumptions of the modified CV method and modified CV basis values are provided.

There were no outliers. Statistics, basis values and estimates are given for FHC3 strength data in Table 4-36. The normalized data, B-estimates and the B-basis values are shown graphically in Figure 4-25.

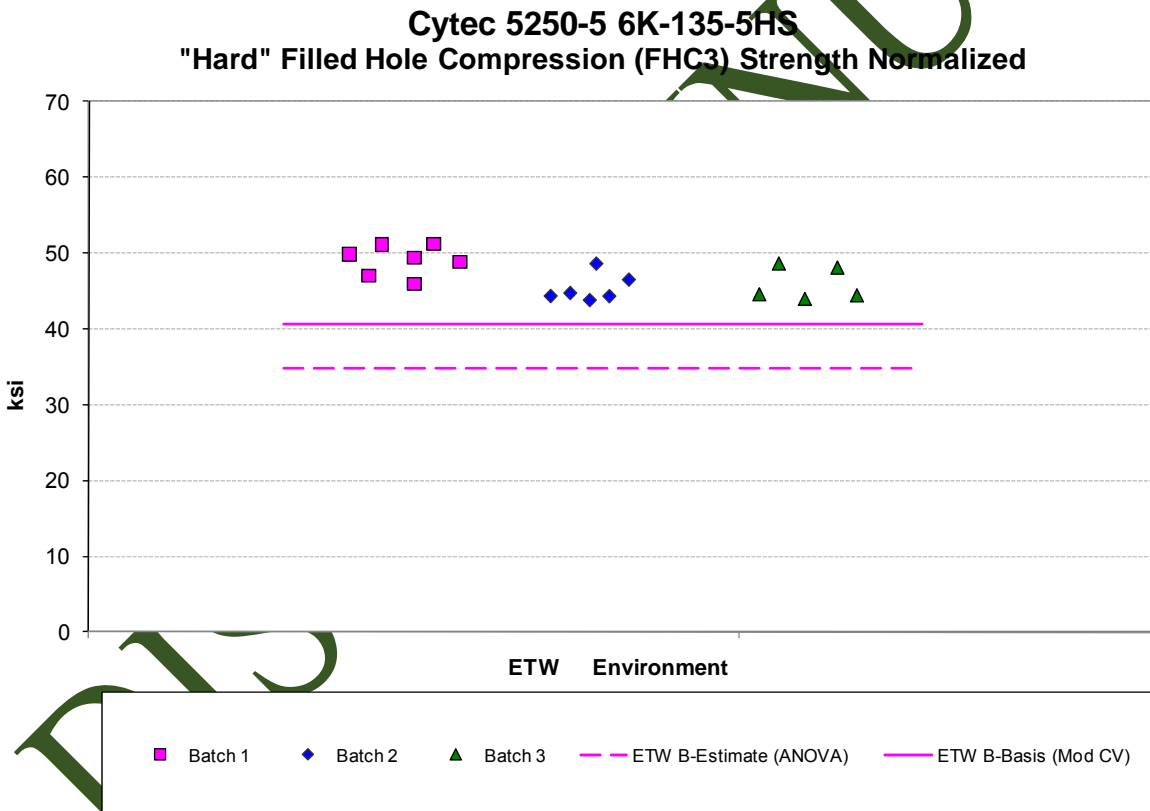


Figure 4-25: Batch plot for FHC3 normalized strength

<b>Filled Hole Compression (FHC3) Strength Basis Values and Statistics</b>		
<b>ETW</b>	<b>Norm</b>	<b>As Meas</b>
Mean	46.95	46.86
Stdev	2.54	2.69
CV	5.42	5.73
Modified CV	6.71	6.87
Min	43.86	43.65
Max	51.20	51.49
No. Batches	3	3
No. Spec.	18	18
<b>Basis Values and Estimates</b>		
B-Estimate	34.85	33.49
A-Estimate	26.22	23.95
Method	ANOVA	ANOVA
<b>Modified CV Basis Values and Estimates</b>		
B-basis Value	40.73	40.51
A-Estimate	36.33	36.02
Method	Normal	Normal

Table 4-36: Statistics and Basis Values for FHC3 Strength Data

DISCONTINUED



### 4.26 Quasi Isotropic Single Shear Bearing (SSB1)

The SSB1 data was normalized so both normalized and as-measured statistics are provided. There were no values reported for ultimate strength from the RTD tests due to testing being stopped after reaching 2%.

The RTD 2% strength datasets, both normalized and as-measured, failed the ADK test, which means that pooling across environments was not acceptable and CMH-17 Rev G guidelines required using the ANOVA analysis. With fewer than 5 batches, this is considered an estimate. Both of those datasets passed the ADK test after applying the transformation to meet the assumptions of the modified CV method and modified CV basis values are provided.

The ETW ultimate strength datasets had CV's greater than 8%, so no modified CV basis values are provided as that method would not alter the results which are presented.

There were no outliers. Statistics, basis values and estimates are given for the SSB1 strength data in Table 4-37. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-26.

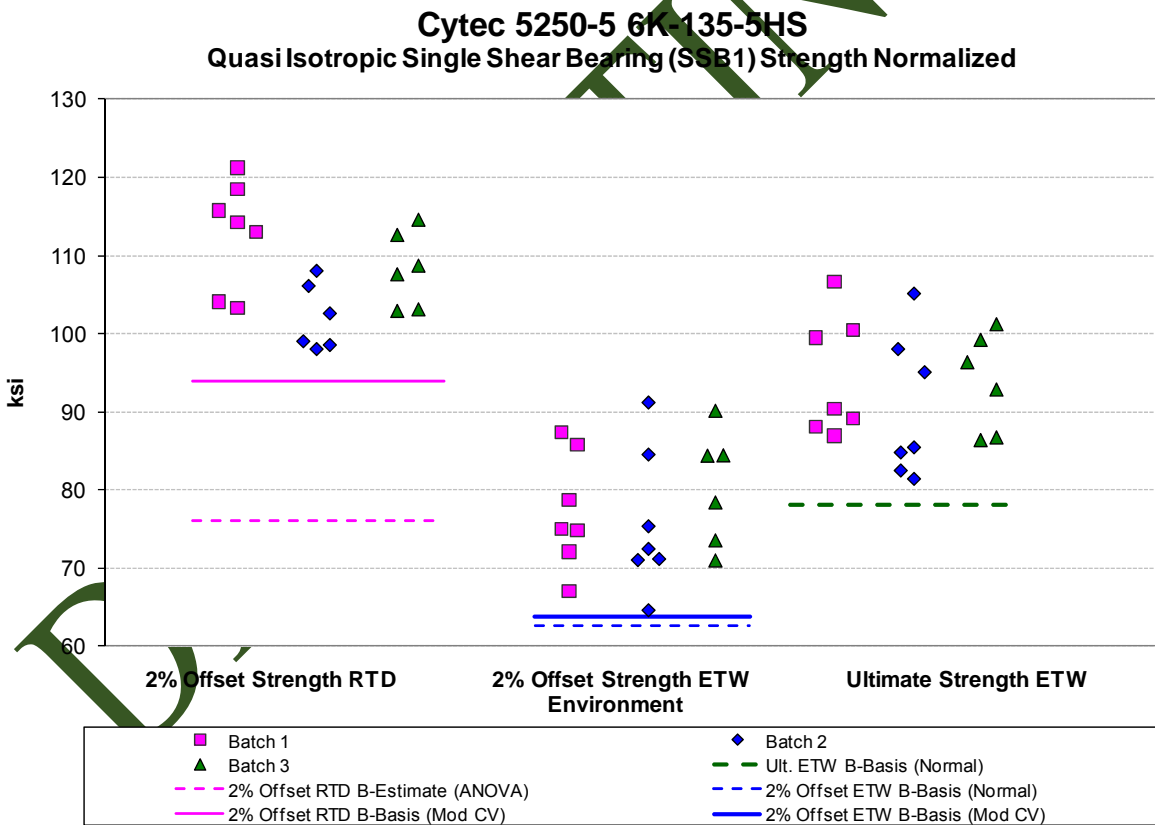


Figure 4-26: Batch plot for SSB1 normalized strength

Single Shear Bearing (SSB1) Strength Basis Values and Statistics						
Property	Normalized			As measured		
	2% Offset Strength		Ultimate Strength	2% Offset Strength		Ultimate Strength
Env	RTD	ETW	ETW	RTD	ETW	ETW
Mean	108.01	77.67	92.83	108.88	78.05	93.32
Stdev	6.91	7.78	7.65	6.89	7.90	8.27
CV	6.40	10.01	8.24	6.33	10.12	8.86
Modified CV	7.20	10.01	8.24	7.16	10.12	8.86
Min	98.07	64.60	81.43	100.76	64.39	82.25
Max	121.23	91.22	106.69	122.52	91.14	113.38
No. Batches	3	3	3	3	3	3
No. Spec.	19	20	20	19	20	20
Basis Values and Estimates						
B-basis Value		62.69	78.09		62.84	77.39
B-Estimate	76.04			77.87		
A-Estimate	53.23	52.03	67.61	55.75	52.01	66.06
Method	ANOVA	Normal	Normal	ANOVA	Normal	Normal
Modified CV Basis Values and Estimates						
B-basis Value	94.01	63.74	NA	93.68	NA	NA
A-Estimate	84.46	54.17		82.90		
Method	pooled	pooled		Normal		

Table 4-37: Statistics and Basis Values for SSB1 Strength Data

DISCONTINUED

### 4.27 "Soft" Single Shear Bearing (SSB2)

The SSB2 data was normalized so both normalized and as-measured statistics are provided. There were no values reported for ultimate strength from the RTD tests due to testing being stopped after reaching 2%.

There were two outliers. Both outliers were outliers for the 2% offset strength, but not ultimate strength and they were outliers in both the normalized and the as-measured datasets. One outlier was on the low side of batch three in the RTD 2% offset strength dataset. It was an outlier for both batch three and for the RTD condition. The second outlier was on the high side of batch one in the ETW 2% offset strength dataset. It was an outlier only for batch one, not for the ETW condition. The RTD outlier was removed from the dataset after investigation. The ETW outlier was retained for this analysis.

Pooling was not accepted for either the normalized or the as-measured 2% offset datasets due to failing Levene's test for equality of variance. There were no other test failures. Modified CV basis values are not provided for the 2% offset ETW condition datasets due to the coefficient of variation being over 8%.

Statistics, basis values and estimates are given for the SSB2 strength data in Table 4-38. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-27.

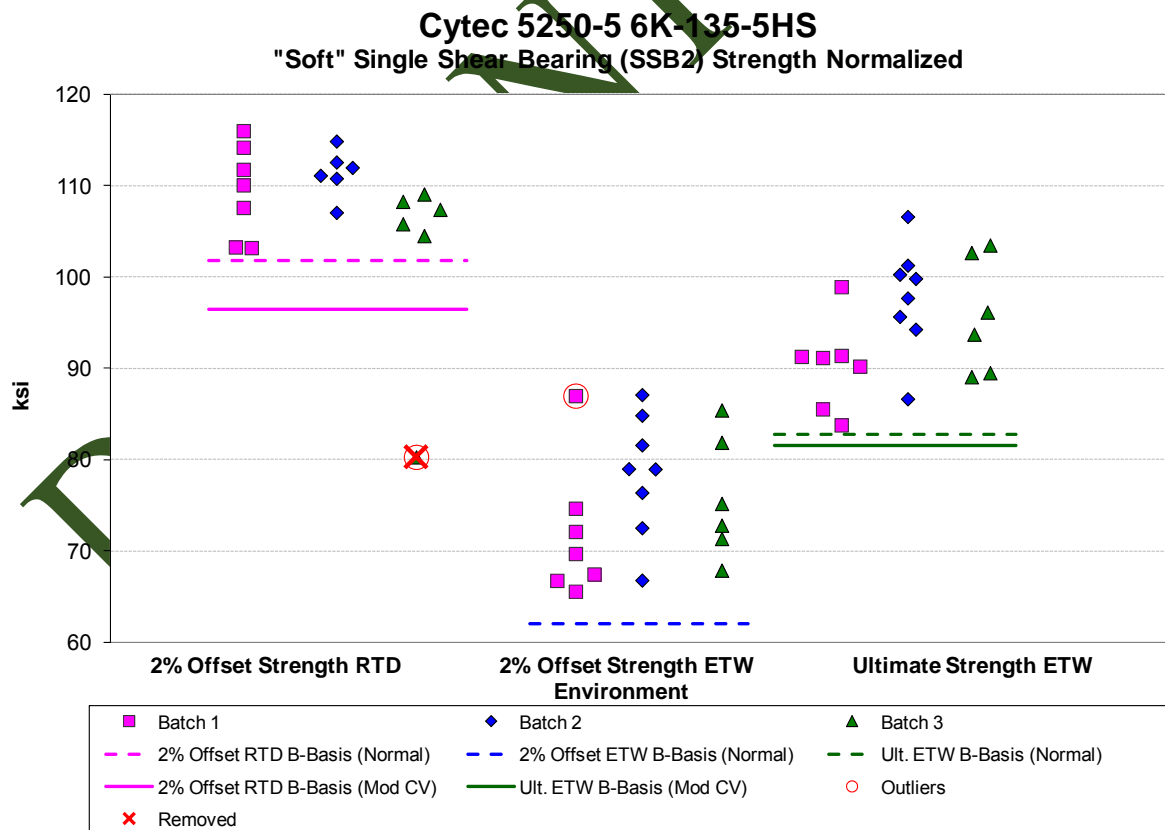


Figure 4-27: Batch plot for SSB2 normalized strength

Single Shear Bearing (SSB2) Strength Basis Values and Statistics						
Property	Normalized			As measured		
	2% Offset Strength		Ultimate Strength	2% Offset Strength		Ultimate Strength
Env	RTD	ETW	ETW	RTD	ETW	ETW
Mean	109.41	75.47	94.71	110.07	75.20	94.39
Stdev	3.84	7.10	6.31	4.10	6.95	6.25
CV	3.51	9.40	6.66	3.72	9.24	6.62
Modified CV	6.00	9.40	7.33	6.00	9.24	7.31
Min	103.19	65.57	83.79	104.35	66.15	83.82
Max	116.00	87.10	106.60	117.31	88.63	106.95
No. Batches	3	3	3	3	3	3
No. Spec.	18	21	21	18	21	21
Basis Values and Estimates						
B-basis Value	101.82	61.95	82.70	101.98	61.96	82.48
A-Estimate	96.45	52.31	74.14	96.25	52.52	73.99
Method	Normal	Normal	Normal	Normal	Normal	Normal
Modified CV Basis Values and Estimates						
B-basis Value	96.45	NA	81.49	97.03	NA	81.24
A-Estimate	87.28	NA	72.06	87.81	NA	71.87
Method	Normal	NA	Normal	Normal	NA	Normal

Table 4-38: Statistics and Basis Values for SSB2 Strength Data

DISCONTINUED

### 4.28 “Hard” Single Shear Bearing (SSB3)

The SSB3 data was normalized so both normalized and as-measured statistics are provided. There were no values reported for ultimate strength from the RTD tests due to testing being stopped after reaching 2%.

The as-measured 2% offset strength dataset failed the normality test and the as-measured 2% offset strength pooled dataset also failed the normality test. This means that pooling across the two environments is not acceptable. There were no other test failures.

There was one outlier. It was the lowest value in batch three of the as-measured RTD 2% offset strength dataset. It was an outlier for the RTD condition but not for batch three. It was retained for this analysis.

Statistics, basis values and estimates are given for the SSB3 strength data in Table 4-39. The normalized data, B-estimates and B-basis values are shown graphically in Figure 4-28.

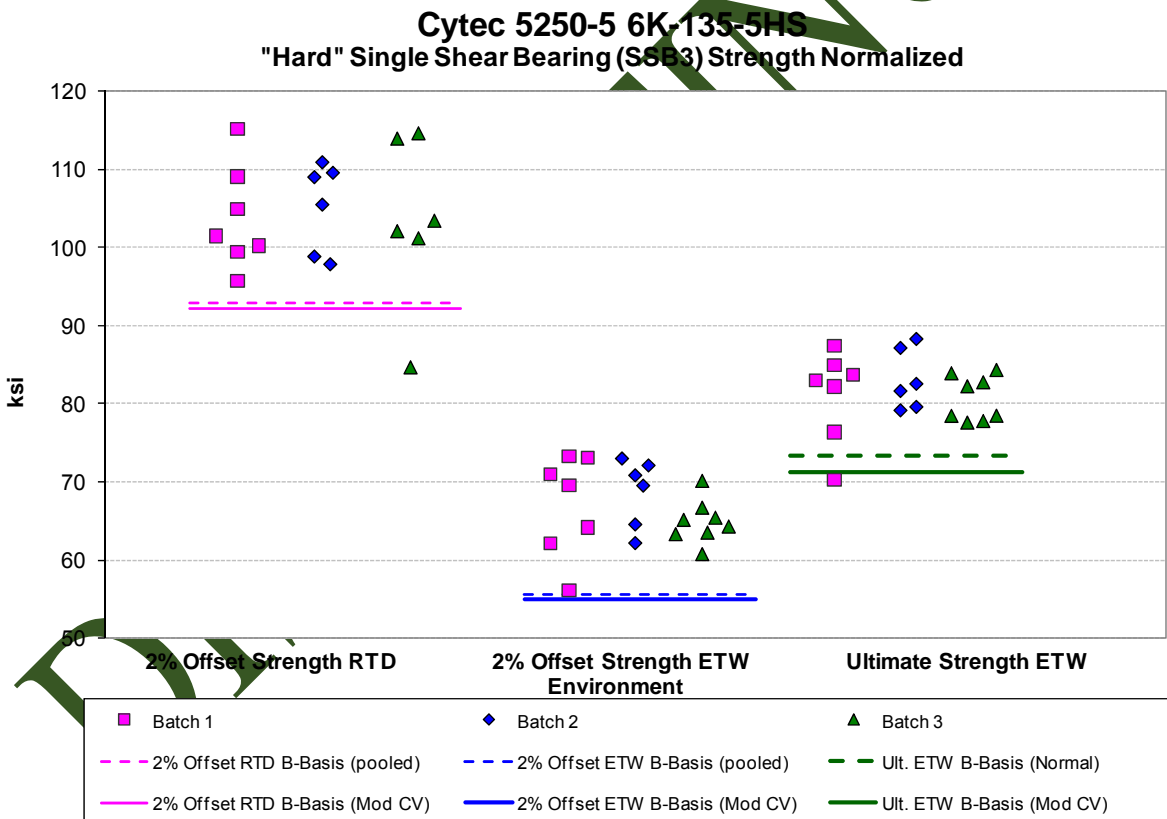


Figure 4-28: Batch plot for SSB3 normalized strength

Single Shear Bearing (SSB3) Strength Basis Values and Statistics						
Property	Normalized			As measured		
	2% Offset Strength		Ultimate Strength	2% Offset Strength		Ultimate Strength
Env	RTD	ETW	ETW	RTD	ETW	ETW
Mean	104.05	66.67	81.48	104.70	66.48	81.23
Stdev	7.56	4.72	4.22	7.62	5.10	4.26
CV	7.27	7.08	5.18	7.28	7.67	5.24
Modified CV	7.63	7.54	6.59	7.64	7.83	6.62
Min	84.64	56.14	70.31	82.94	56.85	71.20
Max	115.19	73.26	88.22	114.56	75.37	87.01
No. Batches	3	3	3	3	3	3
No. Spec.	19	21	21	19	21	21
Basis Values and Estimates						
B-basis Value	92.86	55.58	73.44	88.96	56.78	73.17
A-Estimate	85.24	47.93	67.71	73.81	49.85	67.35
Method	pooled	pooled	Normal	Weibull	Normal	Normal
Modified CV Basis Values and Estimates						
B-basis Value	92.25	54.97	71.25	89.11	56.56	70.98
A-Estimate	84.21	46.90	63.96	78.05	49.49	63.69
Method	pooled	pooled	Normal	Normal	Normal	Normal

Table 4-39: Statistics and Basis Values for SSB3 Strength Data

DISCONTINUED

### 4.29 Compression After Impact (CAI)

Basis values are not computed for this property. Testing is done only for the RTD condition and only one batch of material was tested. There were no outliers. Summary statistics are presented in Table 4-40 and the data are displayed graphically in Figure 4-29.

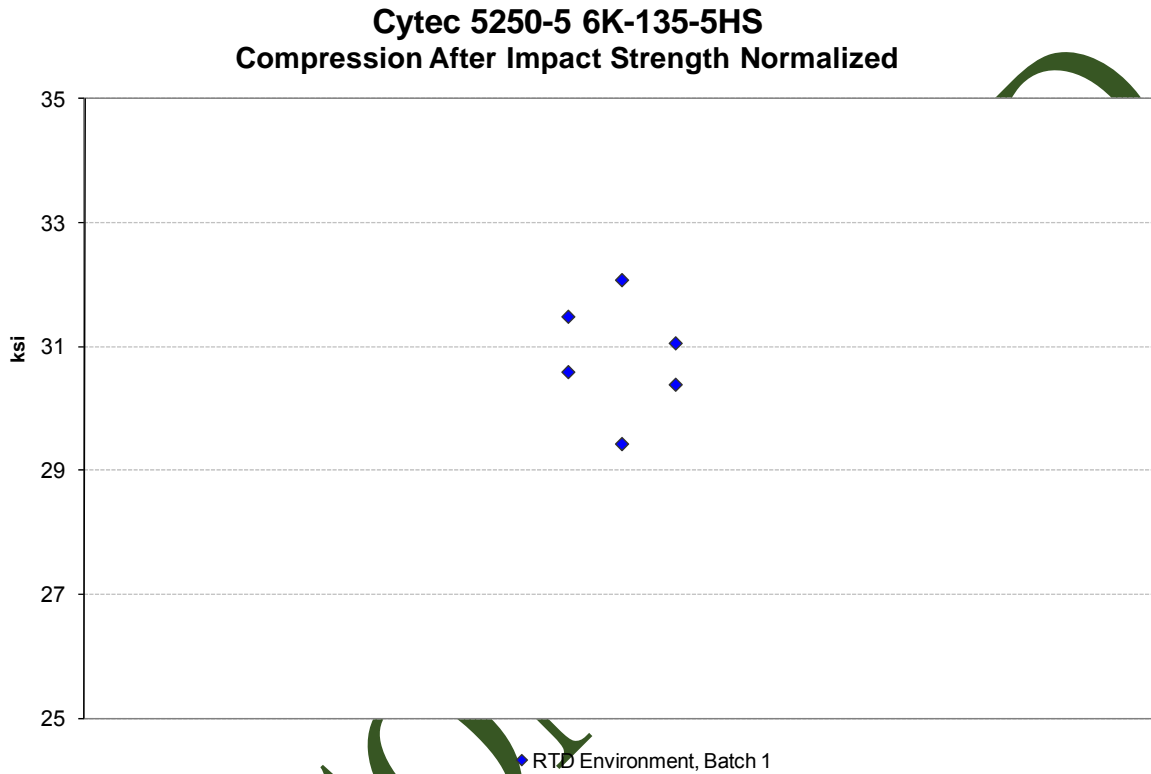


Figure 4-29: Plot for Compression After Impact normalized strength

Compression After Impact Strength (ksi)		
	Normalized	As Measured
Env	RTD	RTD
Mean	30.83	31.60
Stdev	0.92	0.84
CV	2.97	2.65
Modified CV	6.00	6.00
Min	29.43	30.48
Max	32.06	32.77
No. Batches	1	1
No. Spec.	6	6

Table 4-40: Statistics for Compression After Impact Strength Data

### 4.30 Interlaminar Tension Strength (ILT) and Curved Beam Strength (CBS)

The ILT and CBS data is not normalized. Only one batch of material was tested. Basis values are not computed for these properties. Two outliers were identified. The lowest value in the RTD environment for the ILT data and the highest value in the ETW environment for the CBS data. The summary statistics are presented in Table 4-41 and the data are displayed graphically in Figure 4-30.

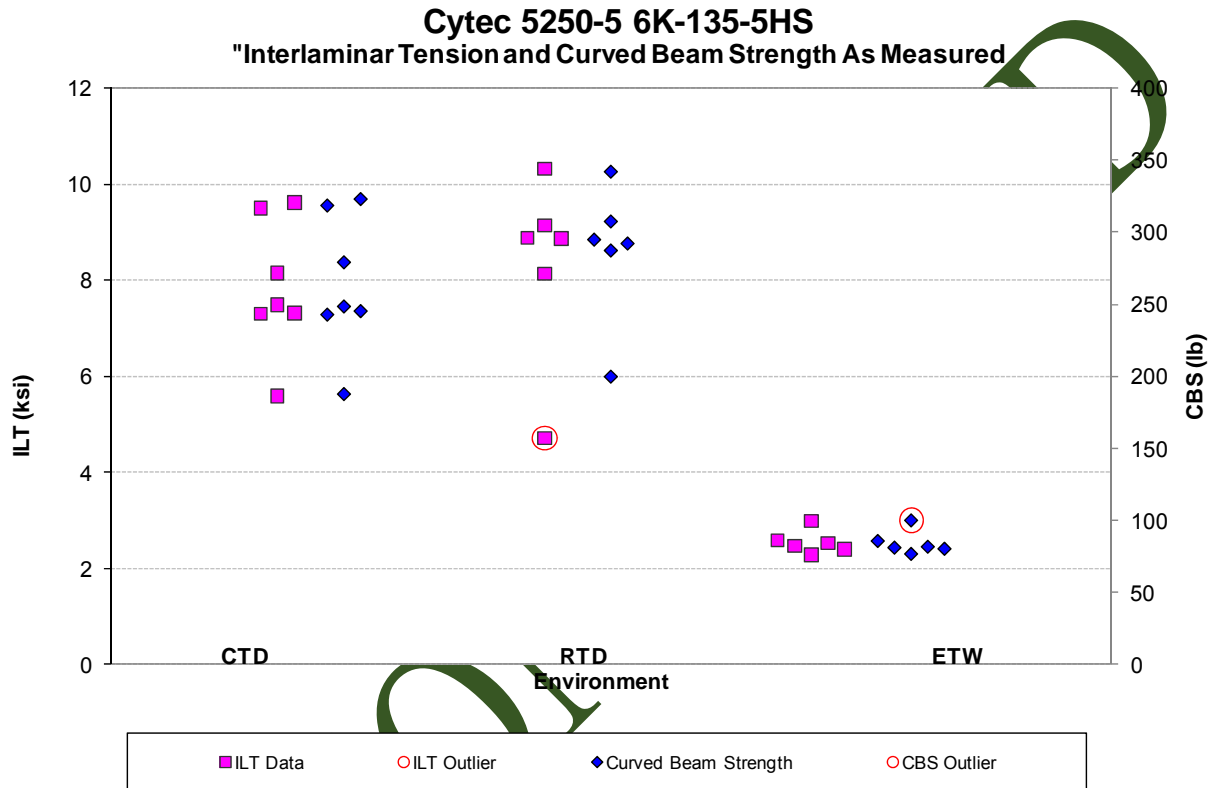


Figure 4-30: Plot for Interlaminar Tension and Curved Beam Strength

Interlaminar Tension (ILT) and Curved Beam Strength (CBS) Statistics						
Env	ILT (as measured)			CBS (as measured)		
	CTD	RTD	ETW	CTD	RTD	ETW
Mean	7.85	8.35	2.55	263.73	287.43	84.52
Stdev	1.40	1.91	0.24	47.50	47.18	8.23
CV	17.81	22.94	9.43	18.01	16.41	9.74
Modified CV	17.81	22.94	9.43	18.01	16.41	9.74
Min	5.59	4.72	2.29	187.91	199.97	77.01
Max	9.61	10.33	2.99	323.15	342.13	100.27
No. Batches	1	1	1	1	1	1
No. Spec.	7	6	6	7	6	6

Table 4-41: Statistics for ILT and CBS Strength Data



## 5. Outliers

Outliers were identified according to the standards documented in section 2.1.5, which are in accordance with the guidelines developed in section 8.3.3 of CMH-17 Rev G. An outlier may be an outlier in the normalized data, the as-measured data, or both. A specimen may be an outlier for the batch only (before pooling the three batches within a condition together) or for the condition (after pooling the three batches within a condition together) or both.

Approximately 5 out of 100 specimens will be identified as outliers due to the expected random variation of the data. This test is used only to identify specimens to be investigated for a cause of the extreme observation. Outliers that have an identifiable cause are removed from the dataset as they inject bias into the computation of statistics and basis values. Specimens that are outliers for the condition and in both the normalized and as-measured data are typically more extreme and more likely to have a specific cause and be removed from the dataset than other outliers. Specimens that are outliers only for the batch, but not the condition and specimens that are identified as outliers only for the normalized data or the as-measured data but not both, are typical of normal random variation.

All outliers identified were investigated to determine if a cause could be found. Outliers with causes were removed from the dataset and the remaining specimens were analyzed for this report. Information about specimens that were removed from the dataset along with the cause for removal is documented in this report or in the material property data report, NCAMP Test Report CAM-RP-2010-076 Rev B.

Outliers for which no causes could be identified are listed in Table 5-1. These outliers were included in the analysis for their respective test properties.

Test	Condition	Batch	Specimen Number	Normalized Strength	Strength As Measured	High/Low	Batch Outlier	Condition Outlier
WC	ETW	1	CNBLA11LJ	72.01	71.56	H	Y	N
WT	CTD	3	CNBJC118B	104.89	103.78	L	N	Y
SBS	CTD	3	CNBQC116B	NA	12.77	H	Y	N
IPS 0.2% Offset	RTD	1	CNBNA212A	NA	8.72	H	Y	N
IPS 0.2% Offset	CTD	1	CNBNA118B	NA	10.32	L	Y	N
IPS Peak before 5% Strain	CTD	2	CNBNB115B	NA	14.35	L	Y	N
INT3	RTD	1	CNBCA212A	102.40	NA	L	Y	N
FHC1	RTD	2	CNBGB113A	45.15	45.16	L	Y	N
FHT1	CTD	1	CNB4A216B	58.74	NA	H	N	Y
FHT1	ETW	1	CNB4A21AJ	48.51	48.77	L	Y	N
FHT2	CTD	1	CNB5A118B	NA	48.55	H	Y	Y
FHC1	RTD	3	CNB7C112A	83.21	83.09	H	Y	N
FHC2	ETW	3	CNB8C217J	NA	28.58	H	Y	N
SSB2 2% Offset	ETW	1	CNB2A115J	86.98	86.89	H	Y	N
SSB3 2% Offset	RTD	3	CNB3C212A	NA	82.94	L	N	Y
ILT	RTD	1	CNBMA112A	NA	4.72	L	Y	NA
CBS	ETW	1	CNBMA211J	NA	100.27	H	Y	NA

Table 5-1: List of outliers

## 6. References

1. Snedecor, G.W. and Cochran, W.G., *Statistical Methods*, 7th ed., The Iowa State University Press, 1980, pp. 252-253.
2. Stefansky, W., "Rejecting Outliers in Factorial Designs," *Technometrics*, Vol. 14, 1972, pp. 469-479.
3. Scholz, F.W. and Stephens, M.A., "K-Sample Anderson-Darling Tests of Fit," *Journal of the American Statistical Association*, Vol. 82, 1987, pp. 918-924.
4. Lehmann, E.L., *Testing Statistical Hypotheses*, John Wiley & Sons, 1959, pp. 274-275.
5. Levene, H., "Robust Tests for Equality of Variances," in *Contributions to Probability and Statistics*, ed. I. Olkin, Palo, Alto, CA: Stanford University Press, 1960.
6. Lawless, J.F., *Statistical Models and Methods for Lifetime Data*, John Wiley & Sons, 1982, pp. 150, 452-460.
7. *Metallic Materials and Elements for Aerospace Vehicle Structures*, MIL-HDBK-5E, Naval Publications and Forms Center, Philadelphia, Pennsylvania, 1 June 1987, pp. 9-166,9-167.
8. Hanson, D.L. and Koopmans, L.H., "Tolerance Limits for the Class of Distribution with Increasing Hazard Rates," *Annals of Math. Stat.*, Vol 35, 1964, pp. 1561-1570.
9. Vangel, M.G., "One-Sided Nonparametric Tolerance Limits," *Communications in Statistics: Simulation and Computation*, Vol. 23, 1994, p. 1137.
10. Vangel, M.G., "New Methods for One-Sided Tolerance Limits for a One-Way Balanced Random Effects ANOVA Model," *Technometrics*, Vol 34, 1992, pp. 176-185.
11. Odeh, R.E. and Owen, D.B., *Tables of Normal Tolerance Limits, Sampling Plans and Screening*, Marcel Dekker, 1980.
12. Tomblin, John and Seneviratne, Waruna, *Laminate Statistical Allowable Generation for Fiber-Reinforced Composites Material: Lamina Variability Method*, U.S. Department of Transportation, Federal Aviation Administration, May 2006.
13. Tomblin, John, Ng, Yeow and Raju, K. Suresh, *Material Qualification and Equivalency for Polymer Matrix Composite Material Systems: Updated Procedure*, U.S. Department of Transportation, Federal Aviation Administration, September 2003.
14. CMH-17 Rev G, Volume 1, 2012. SAE International, 400 Commonwealth Drive, Warrendale, PA 15096